

**CIHM
Microfiche
Series
(Monographs)**

**ICMH
Collection de
microfiches
(monographies)**



Canadian Institute for Historical Microreproductions / Institut canadien de microreproductions historiques

© 1997

DCC

CANADA
DEPARTMENT OF MINES
MINES BRANCH

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAANEL, PH. D., DIRECTOR.

BULLETIN No. 1.

INVESTIGATION OF THE PEAT BOGS AND
PEAT INDUSTRY OF CANADA, DURING
THE SEASON 1908-9.


SECOND EDITION

BY
ERIK NYSTRÖM, M.E.
AND
S. A. ANREP, PEAT EXPERT.



OTTAWA
GOVERNMENT PRINTING BUREAU
1200

856443

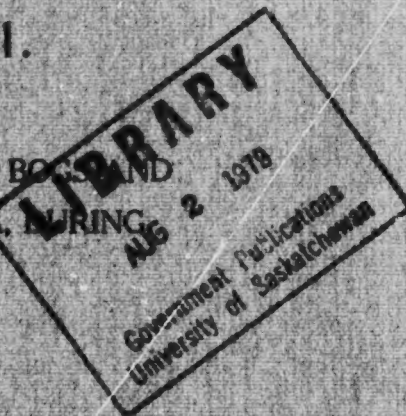

FRAGILE

Do not use
book drop.

Return directly to Main Circulation.

No. 30.

5 JUIN 1957

CANADA
DEPARTMENT OF MINES
MINES BRANCH

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAANEL, PH. D., DIRECTOR.

BULLETIN No. 1.

INVESTIGATION OF THE PEAT BOGS AND
PEAT INDUSTRY OF CANADA, DURING
THE SEASON 1908-9.

SECOND EDITION


BY
ERIK NYSTRÖM, M.E.,
AND
S. A. ANREP, PEAT EXPERT.



39236

OTTAWA
GOVERNMENT PRINTING BUREAU
1909

No. 30.

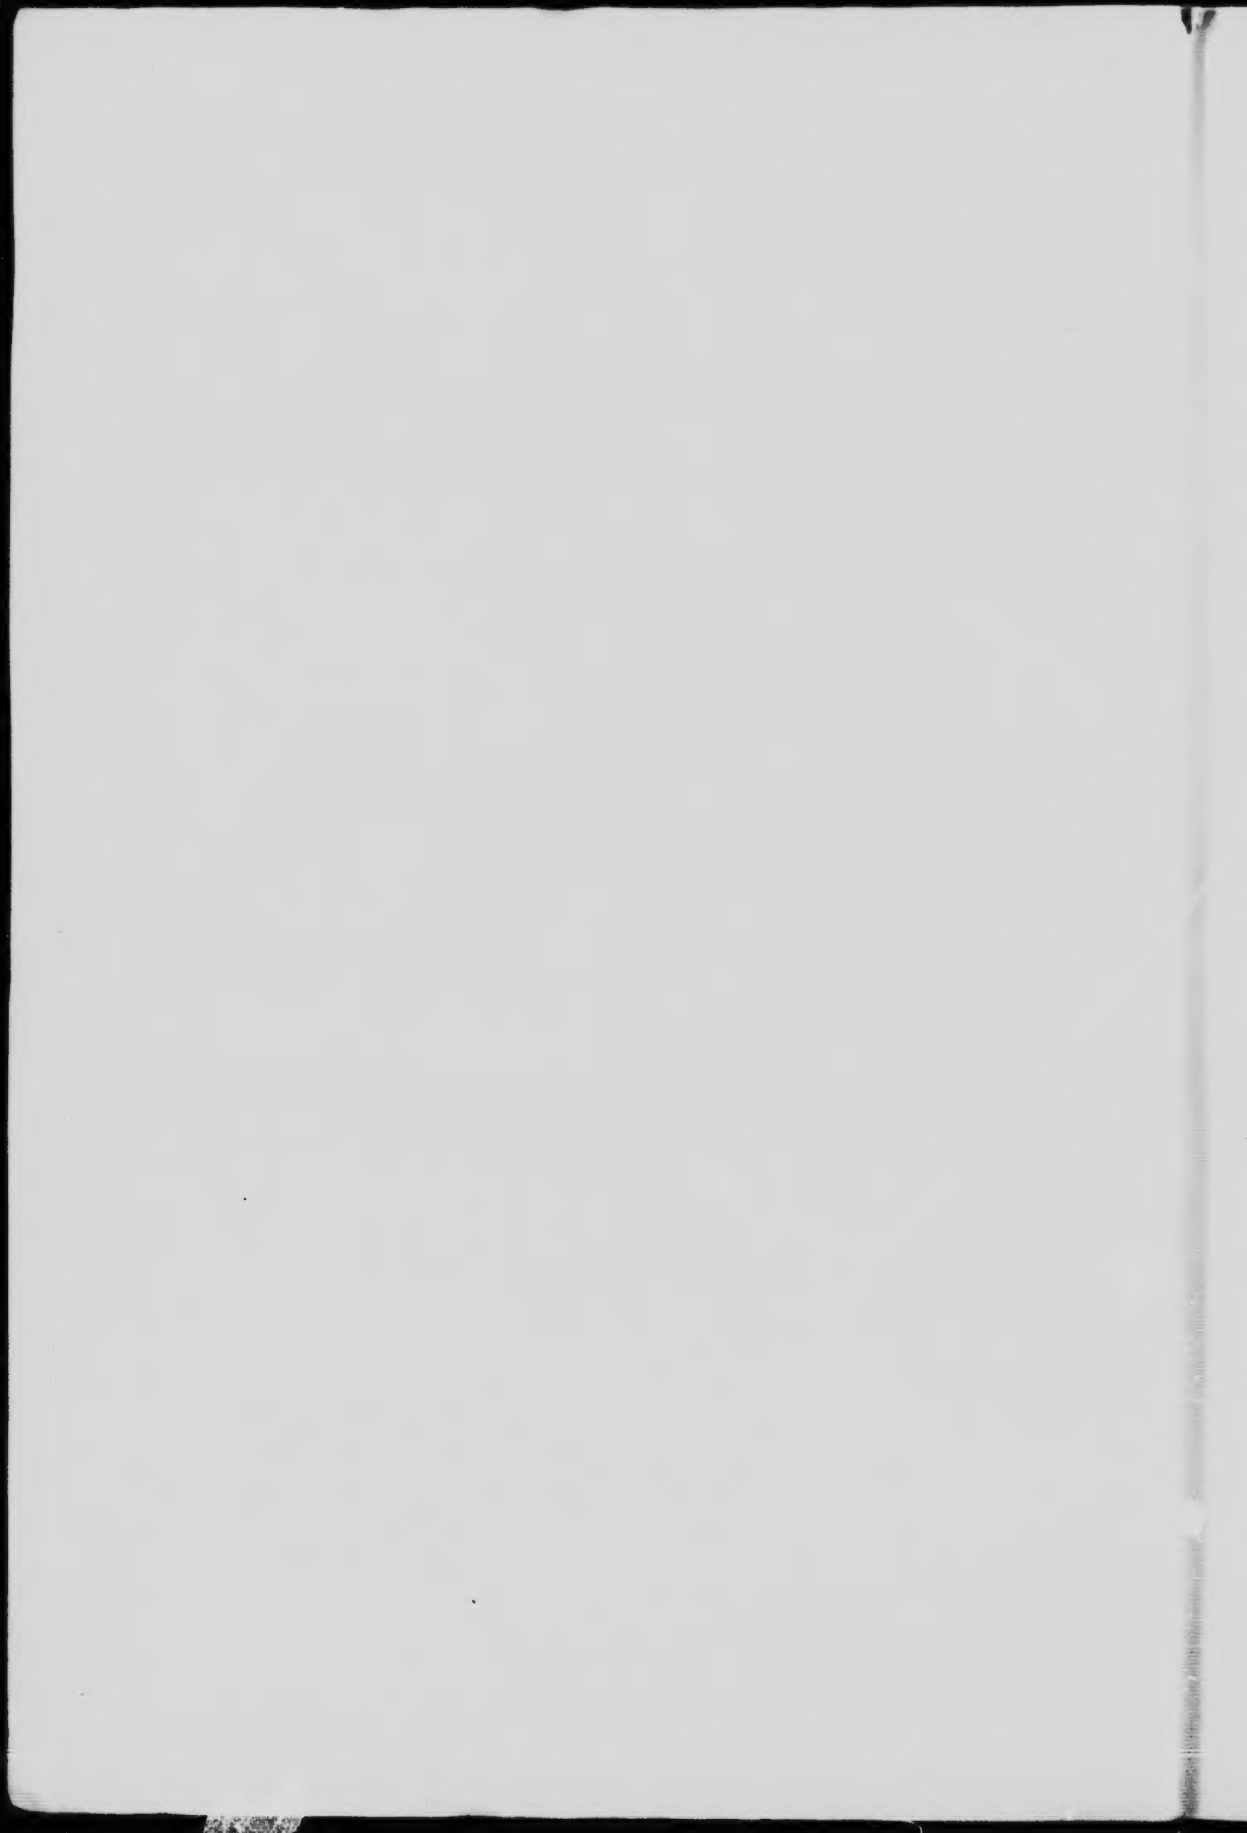

LETTER OF TRANSMITTAL.

OTTAWA, March 8, 1909.

SIR,—

During the season of 1908, I, with Mr. A. Anrep as assistant, started the investigation of our peat resources. The bogs first to be considered were those which were favourably located as to transportation and market.

Several of these bogs are of considerable extent, and in order to arrive at a fairly accurate estimate as to their extent, depth and quality of the peat contained, a great number of holes have to be drilled.

The drilling, as well as the cutting out of the necessary lines, especially where the bogs are heavily wooded, requires considerable time, and these investigations will, therefore, involve many years' work.

Part of the summer was spent at Victoria Road peat bog, where the Anrep peat pulping machine imported from Sweden was set up, in order to manufacture sufficient peat fuel to start the Körting peat gas producer plant at present under erection at Ottawa.

During the summer I also visited the greater number of the peat plants so far erected in Canada, and in October attended the meeting of the American Peat Society held in Toledo, Ohio.

In the following report the bogs so far investigated are separately described, and accompanied by maps showing their areas, as well as the depths of the peat and the average degree of humification for each drill hole.

Yours respectfully,

(Signed) E. NYSTRÖM.

DR. EUGENE HAANEL,
Director of Mines,
Ottawa.

CONTENTS.

	PAGE
Letter of Transmittal.....	5
Method of Investigation.....	7
Canadian Bogs.....	8
Characteristic Plants of the Peat Bogs of Ontario.....	8
Description of Individual Peat Bogs.....	10
Mer Bleue Peat Bog.....	10
Alfred Peat Bog.....	12
Welland Peat Bog.....	14
Newington Peat Bog.....	15
Perth Peat Bog.....	17
Victoria Road Peat Bog.....	18
Present Status of the Peat Industry in Canada.....	19
Victoria Road Peat Plant.....	21
Guelph Peat Plant.....	23
Farnham Peat Plant.....	23
Lac du Bonnet Peat Plant.....	25
Drying, Carbonizing, etc.....	25

ILLUSTRATIONS.

PLATES.

Mer Bleue Peat Bog.....	10
Alfred Peat Bog.....	12
Welland Peat Bog.....	14
Newington Peat Bog.....	16
Perth Peat Bog.....	18
Victoria Road Peat Bog.....	22

INVESTIGATION OF THE PEAT BOGS AND PEAT FUEL INDUSTRY OF CANADA, 1908.

BY
ERIK NYSTRÖM and S. A. ANREP.

METHOD OF INVESTIGATION.

In order to map the surface of the bogs, lines were run at certain intervals, generally 1,000 feet apart. Drillings were made in each of these lines at intervals of 500 feet, and samples of the peat collected from different depths. Unless the peat was very different in appearance, all these samples were made into one general sample covering a certain section of the bog; but the degree of humification was noted for each drill hole, and for the different depths.

The different degrees of humification are expressed in letters in accordance with the following scale:—

C		B	
C +	} indicating a peat more or less suitable for moss litter.	B +	} indicating a peat more or less suitable for peat fuel.
B C —		A B —	
B C		A B	
B C +		A B +	
B —		A —	
		A	

The peat classified in accordance with this scale from C to B— is only suitable for the manufacture of moss litter or similar products, and that from B to A for peat fuel. B, for instance, indicates that the peat fuel produced from such peat is light and consequently bulky, and A B a heavier peat, well suited for the manufacture of fuel. In the same manner C indicates a peat, or rather moss, well suited for moss-litter, and B— a less suitable material. The signs + and — after the letter respectively increase or decrease the degree indicated.

For the purpose in view, viz., to obtain a fairly accurate idea of our peat resources, it is quite sufficient, at least for the larger bogs, to run the lines 1,000 feet, or even further apart, as it would otherwise require a very long time to reach any conclusions; but where manufacture of peat products is intended, drillings ought to be made closer.

In Canada the method chiefly used for the manufacture of peat fuel has been to harrow the surface of the bog, or some similar method, and collect the partly air-dried peat in horizontal layers. In such cases the part of the bog which is intended to be worked should be carefully investigated, and the quality and properties of the different layers separately ascertained. The peat, in many cases, is of different nature in different layers, even in the

same bog, and in several cases some layers are entirely unsuitable for the method above referred to. In Europe the method generally used for the production of peat fuel is different; the peat is there dug out of the bog in vertical trenches, the different layers of peat are mixed, and a uniform product is obtained.

CANADIAN BOGS.

The vegetation forming our bogs is in most cases identical, or very similar to that forming the European bogs.

In the following list, supplied by Mr. J. M. Macoun of the Geological Survey, the principal plants forming our bogs are enumerated:—

CHARACTERISTIC PLANTS OF THE PEAT BOGS OF ONTARIO.

While the number of species of *Sphagnum* growing on our eastern bogs is very large, the general bog covering is made up of a few species only, of which the following are the most abundant:—

- Sphagnum acutifolium*, Russ. and Warnst.
- Sphagnum recurvum*, Russ. and Warnst. and its varieties.
- Sphagnum fuscum*, von Klinggraeff, and its varieties.
- Sphagnum cymbifolium*, Ehrh.
- Sphagnum medium*, Limpr.

Next to *Sphagnum* the moss family which is most common is *Hypnum*. More than a score of species are to be found on almost any large bog, but many of these are not in sufficient abundance to affect the quality of the peat in any great degree. The most important are:—

- Thuidium Blandowii*, Bruch and Schimp.
- Camptothecium nitens*, Schimp.
- Hypnum fluitans*, Linn.

On tussocks and other raised parts of bogs a great variety of other mosses and lichens are always to be found, but few of these are worth noting, as they do not form large masses. Almost any hummock will be found to be composed chiefly of the following:—

- Polytricum strictum*, Banks. Hair-cap moss.
- Cladonia rangiferina*, Hoffm., Reindeer moss.

Other species of *Polytricum* and *Cladonia* will almost always be noted, but those mentioned form the mass.

The order *Cyperaceæ* is always well represented on and around bogs. In the wetter parts, where there is no *Sphagnum* covering, many species of *Carex* are always to be found, among them: *C. utriculata*, Boott; *C. vulpinoides*, Michx.; *C. teretiuscula*, Good; *C. Sartwellii*, Dewey; *C. riparia*, Curtis; and *C. aquatilis*, Wahl.

On the bog itself the most important species are:—

- Carex exilis*, Wahl.
- Carex sterilis*, Willd.
- Carex oligosperma*, Michx.
- Carex trisperma*, Dewey.

The only other genus of Cyperaceæ that is represented is *Eriophorum*, of which four or five species occur on every bog. Of these the most valuable is:—

Eriophorum callitrix, Cham.
or *E. vaginatum*, as it was formerly called. The other species are:—

- Eriophorum Chamissonis*, C. A. Meyer.
- Eriophorum gracile*, Roth.
- Eriophorum angustifolium*, Roth.
- Eriophorum Virginicum*, L.

While not properly bog plants, a large number of aquatic species¹ grow in ponds, or wet, marshy spots in the bog or along its borders. These are frequently mixed together, but often large areas will be covered by one or two species, such as: *Typha*, *Sagittaria*, *Sparganium*, *Utricularia*, or *Potamogeton*.

Only the most abundant species are enumerated below:—

- Sagittaria latifolia*, Willd. Broad-leaved arrowhead.
- Utricularia vulgaris*, L. Greater bladderwort.
- Iris versicolor*, L. Larger blue flag.
- Scirpus lacustris*, L. Lake bulrush.
- Sparganium simplex*, Michx. . . Bur-reed.
- Typha latifolia*, L. Cut-tail.
- Glyceria nervata*, Willd. Nerved manna-grass.
- Glyceria Americana*, Torr. Tall manna-grass.
- Potamogeton*, Several species . . . Pond-weed.
- Scirpus cyperinus*, Kunth. Woll-grass.
- Nymphaea odorata*, Ait. White water lily.
- Nuphar advena*, Ait. Yellow water lily.

Of herbaceous plants there are more than 100 species, in addition to those mentioned above, which may properly be called bog plants, but the majority of these are either so insignificant in size or grow so far apart that they effect no appreciable change in the composition of the peat. The most common and valuable species are:—

- Menyanthes trifoliata*, L. Buckbean.
- Drosera rotundifolia*, L. Round-leaved sundew.
- Chiogenes hispidula*, T. and G. . . Creeping snowberry.
- Scheuchzeria palustris*, L. Scheuchzeria.
- Habenaria dilatata*, Pursh Tall white bog orchis.
- Habenaria hyperborea*, L. Tall green orchis.

¹In cases where the bogs have been formed by the growing over of lakes the remains of these plants generally form the deeper layers of the bogs.

Vaccinium macrocarpon, Ait. Large cranberry.
Vaccinium oxycoccus, L. Small cranberry.
Sarracenia purpurea, L. Pitcher plant.

Even the most open bogs are usually covered in great part by shrubs or shrubby plants, and in boggy woods they occur frequently in even greater profusion. The most widely distributed and best known species are:—

Ledum Groelandicum, O. Eder. . Labrador tea.
Andromeda glaucophylla, Link. . Andromeda.
Kalmia glauca, L. Mountain laurel.
Cassandra calyculata, L. Leather leaf.
Spiraea salicifolia, L. Meadowsweet.
Vaccinium Canadense, Rich. Canada blueberry.
Vaccinium Pennsylvanicum, Lam. Low blueberry.
Vaccinium nigrum, Britton Low black blueberry.
Salix myrtilloides, L. Myrtle-leaved willow.

The only trees that may be said to be truly characteristic of bogs are black spruce, *Picea Mariana*, B.S.P. and tamarack, *Larix laricina*, Koch., but along the margins of most bogs, and on many old bogs where there is good drainage, cedar, hemlock, balsam, ash, and a few other species will generally be found.

DESCRIPTION OF INDIVIDUAL PEAT BOGS.

MER BLEUE PEAT BOG.

This bog is situated about 8 miles from Ottawa, Ont., in the townships of Gloucester and Cumberland (see accompanying map) and covers more or less of:—

Lots 13-16, con. III, township of Gloucester.
 Lots 3-15, con. IV, " "
 Lots 1-16, con. V, " "
 Lots 1-9, con. VI, " "
 Lots 1-2, con. VII, " "
 Lots 9-16, con. XI, township of Cumberland.
 Lots 12-16, con. X, " "

The total area covered by this bog is, approximately, 5,004 acres. Of this area

1,564 acres have a depth of less than 5 feet, average depth 2'-9"

2,237 acres have a depth of 5 to 10 feet, average depth 6'-8"

856 acres have a depth of 10 to 15 feet, average depth 11'-8"

347 acres have a depth of more than 15 feet, average depth 16 feet.

The volume of the peat contained is:—

In the area with a depth of less than 5 feet	6,938,946	cub. yds.
5 to 10 feet deep	24,036,117	" "
10 to 15 feet deep	16,102,611	" "
more than 15 feet deep	8,973,037	" "

CON. III


BLACKBURN STA.

CON. IV

GLOUCESTER

16


15

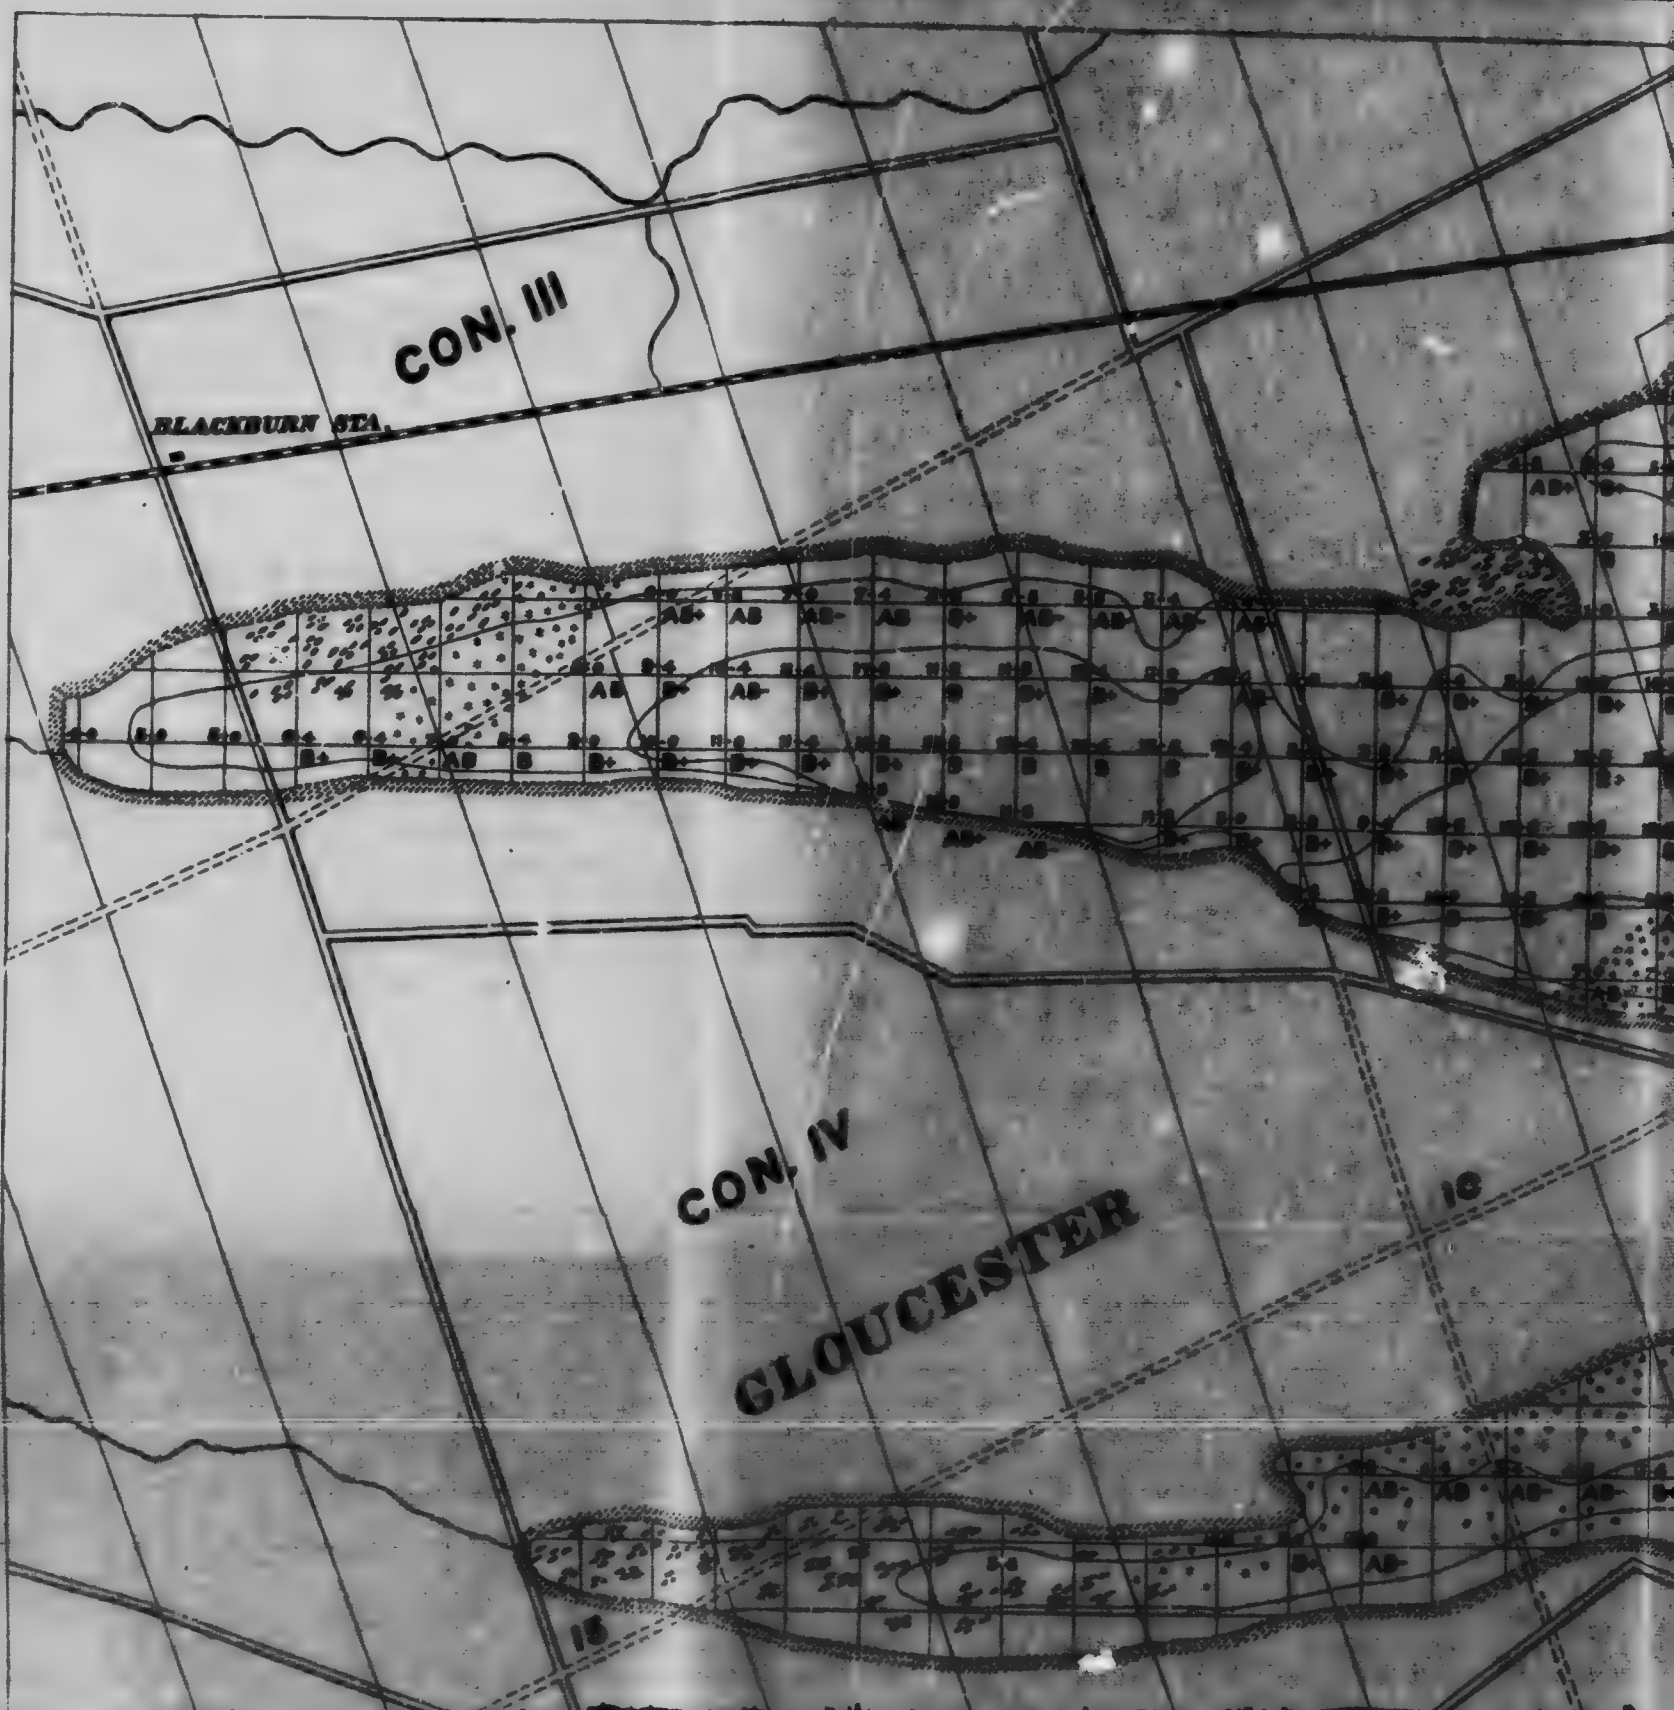

CANADA
DEPARTMENT OF MINES
MINING BRANCH

HON. W. TIERNEYMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAASKE, PH.D., DIRECTOR.


MER BLEUE PEAT BOG

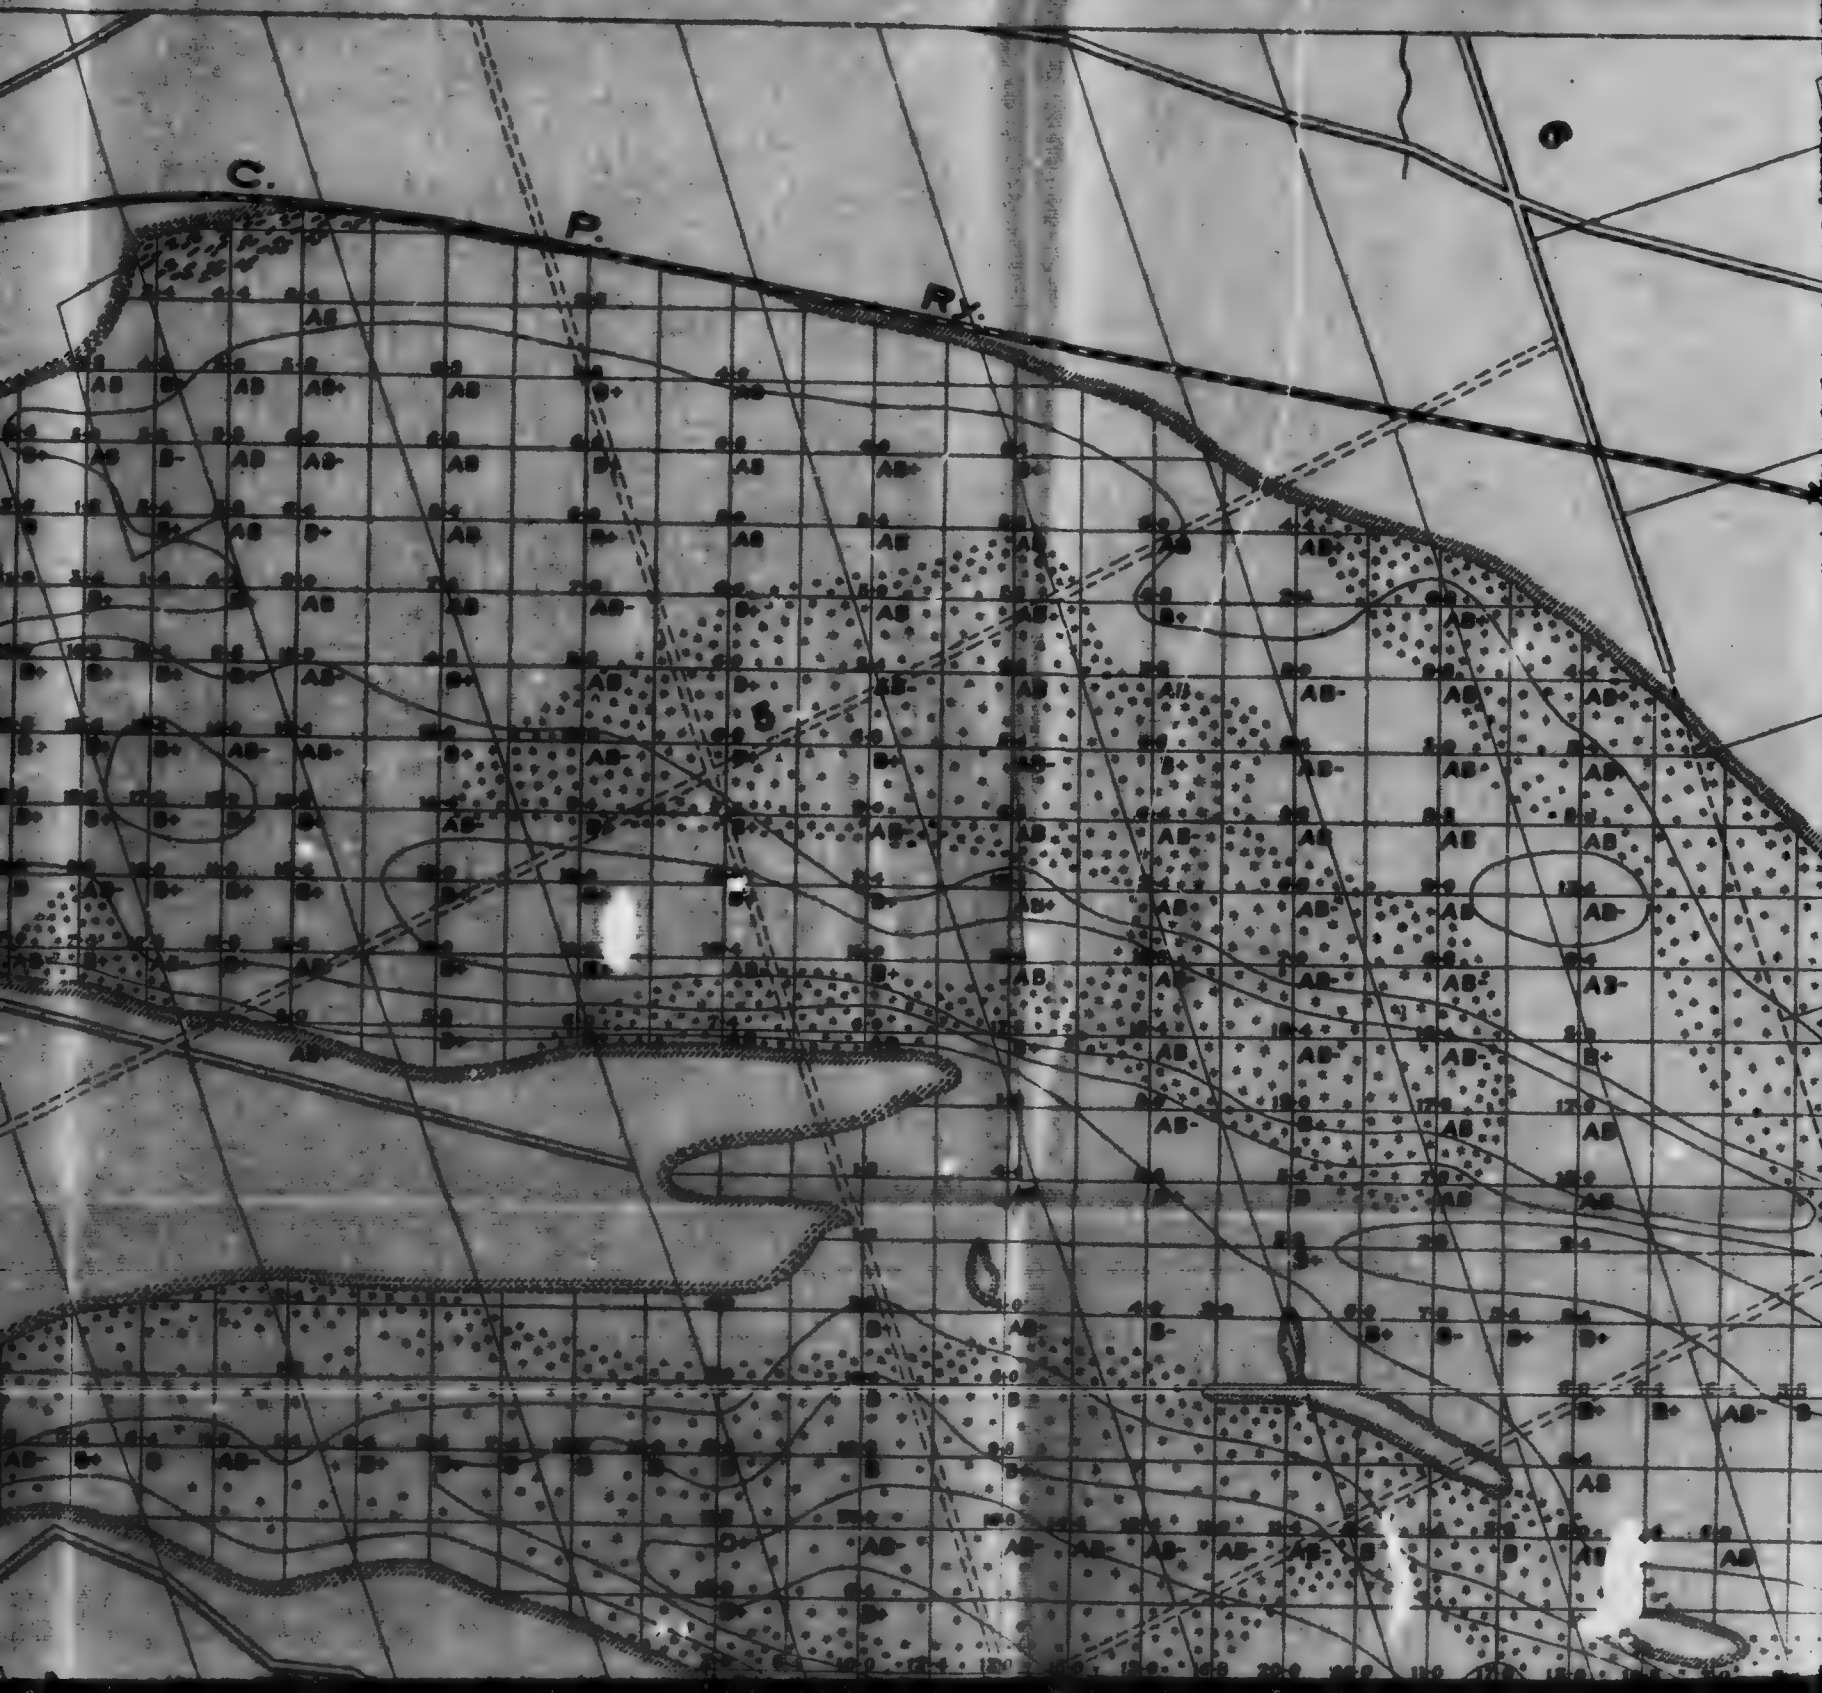


CANADA
DEPARTMENT OF MINES
MINES BRANCH

MINISTER; A. P. LOW, LL.D. DEPUTY MINISTER;
F. HAANEL, Ph.D., DIRECTOR.


THE PEAT BOG

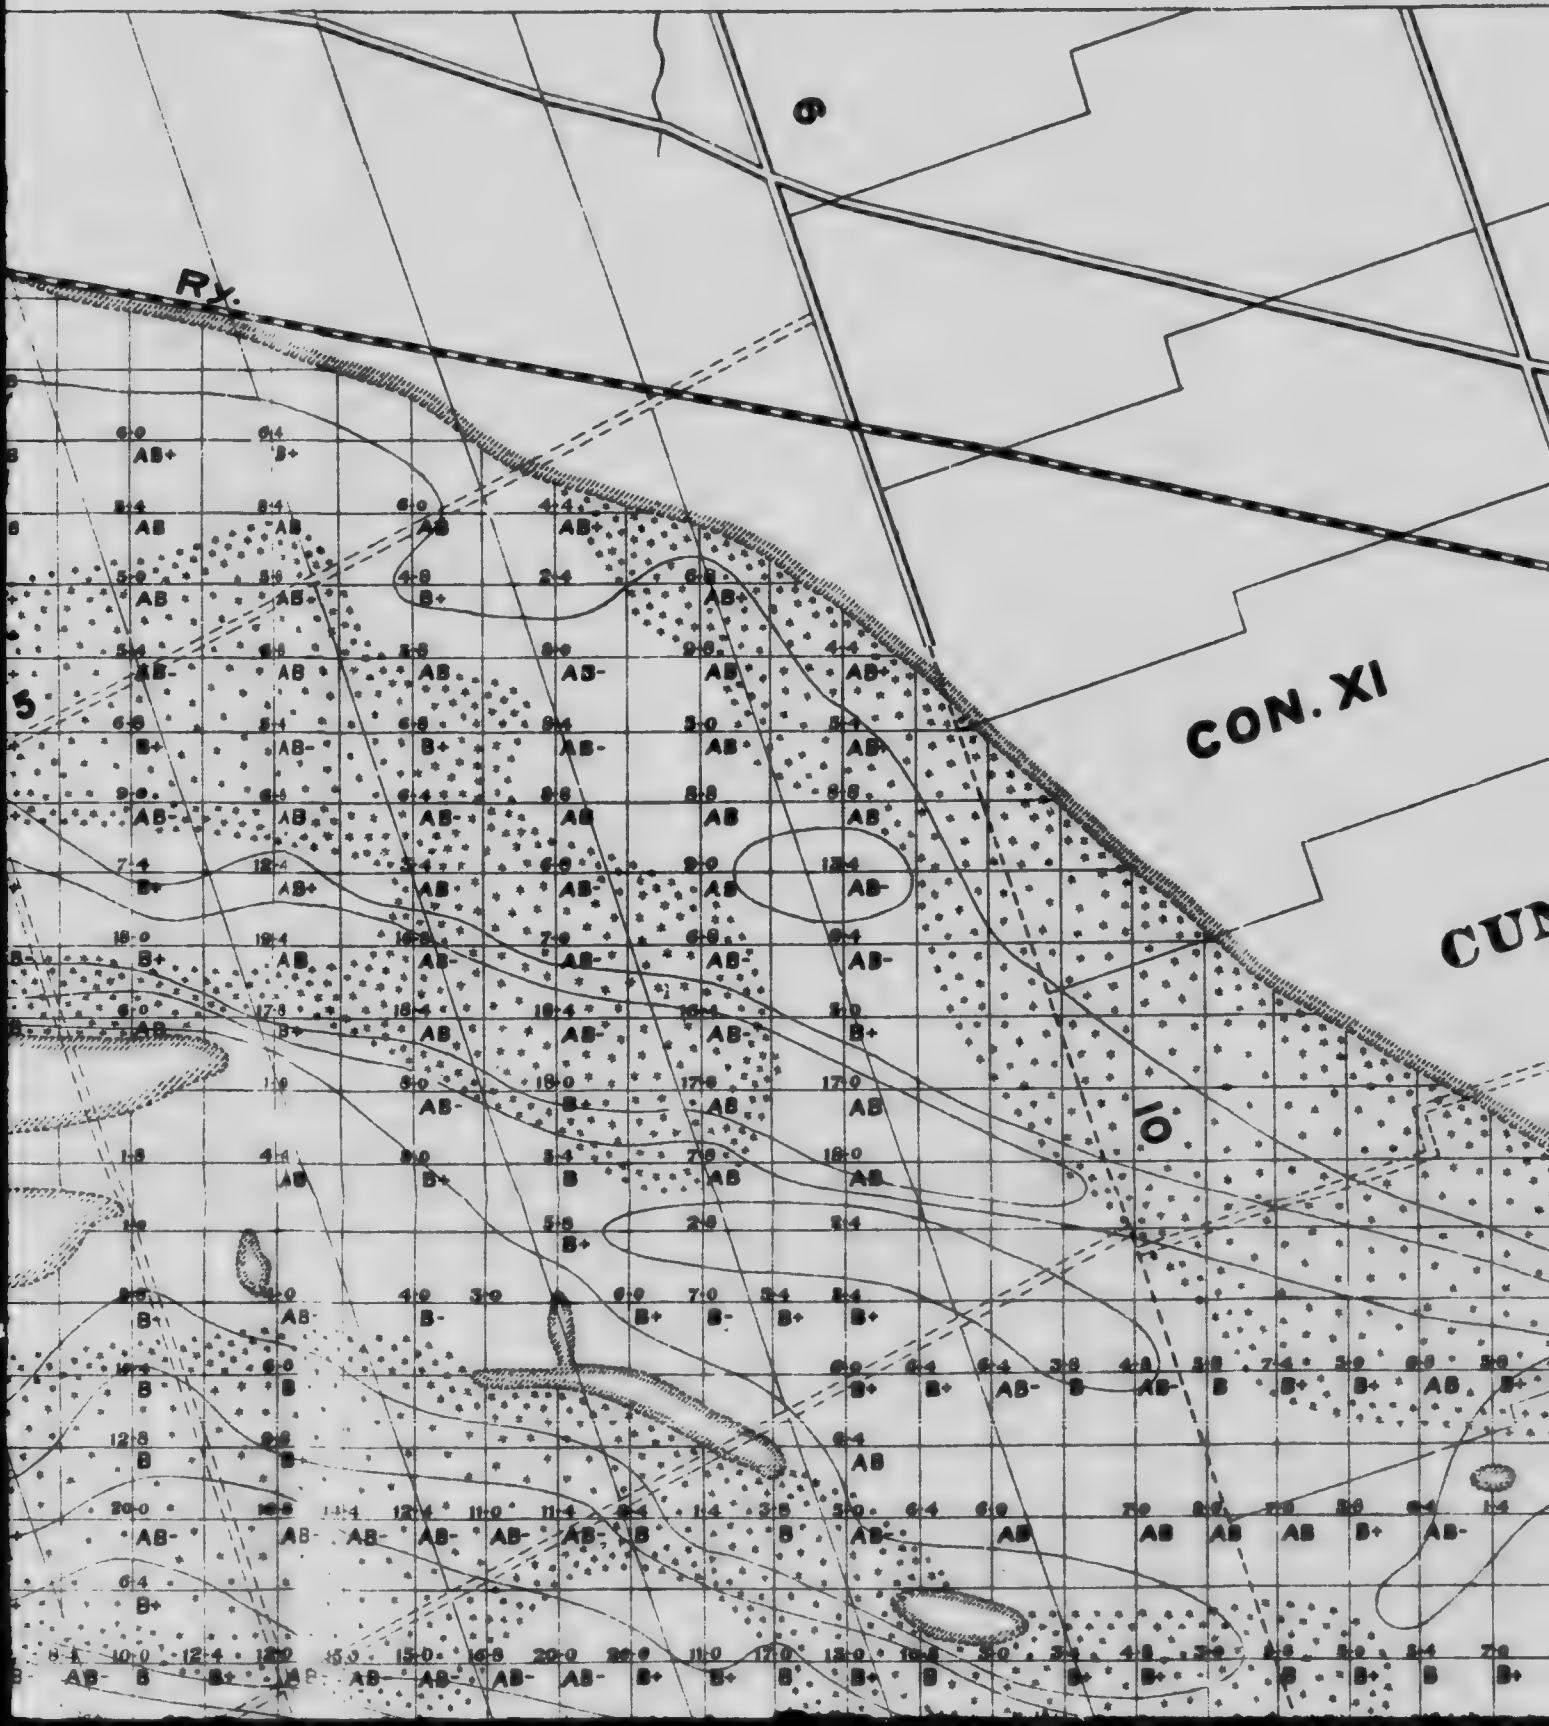



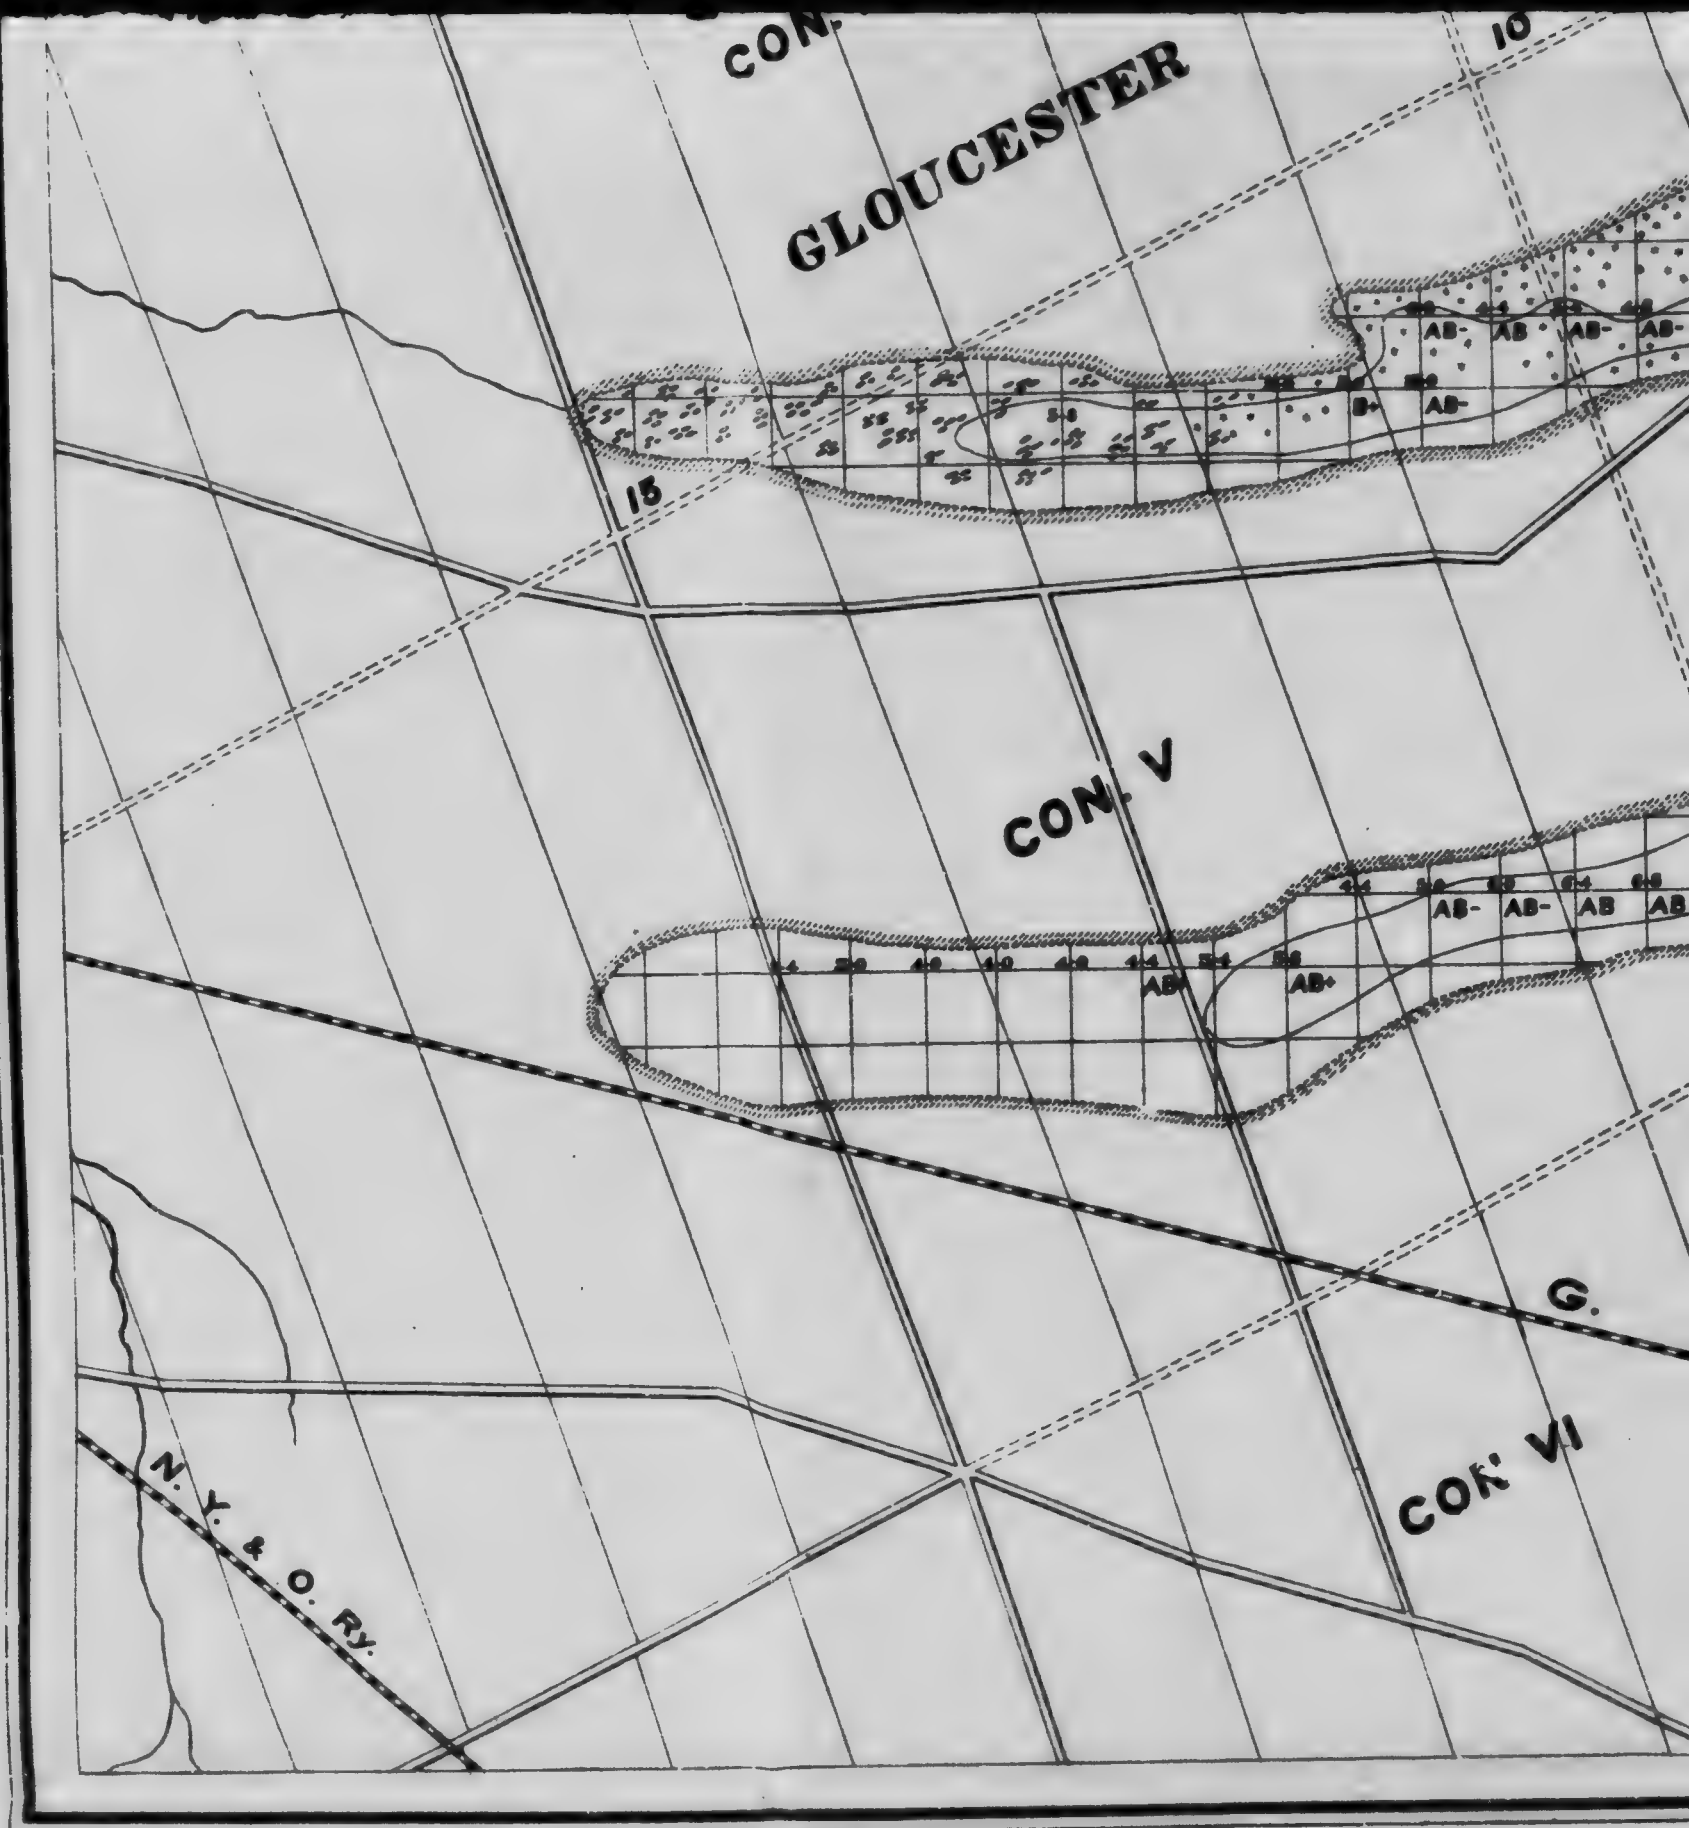


ERIK NYSTRÖM, Mining Engineer.
S. A. ANREP, Post Expert.

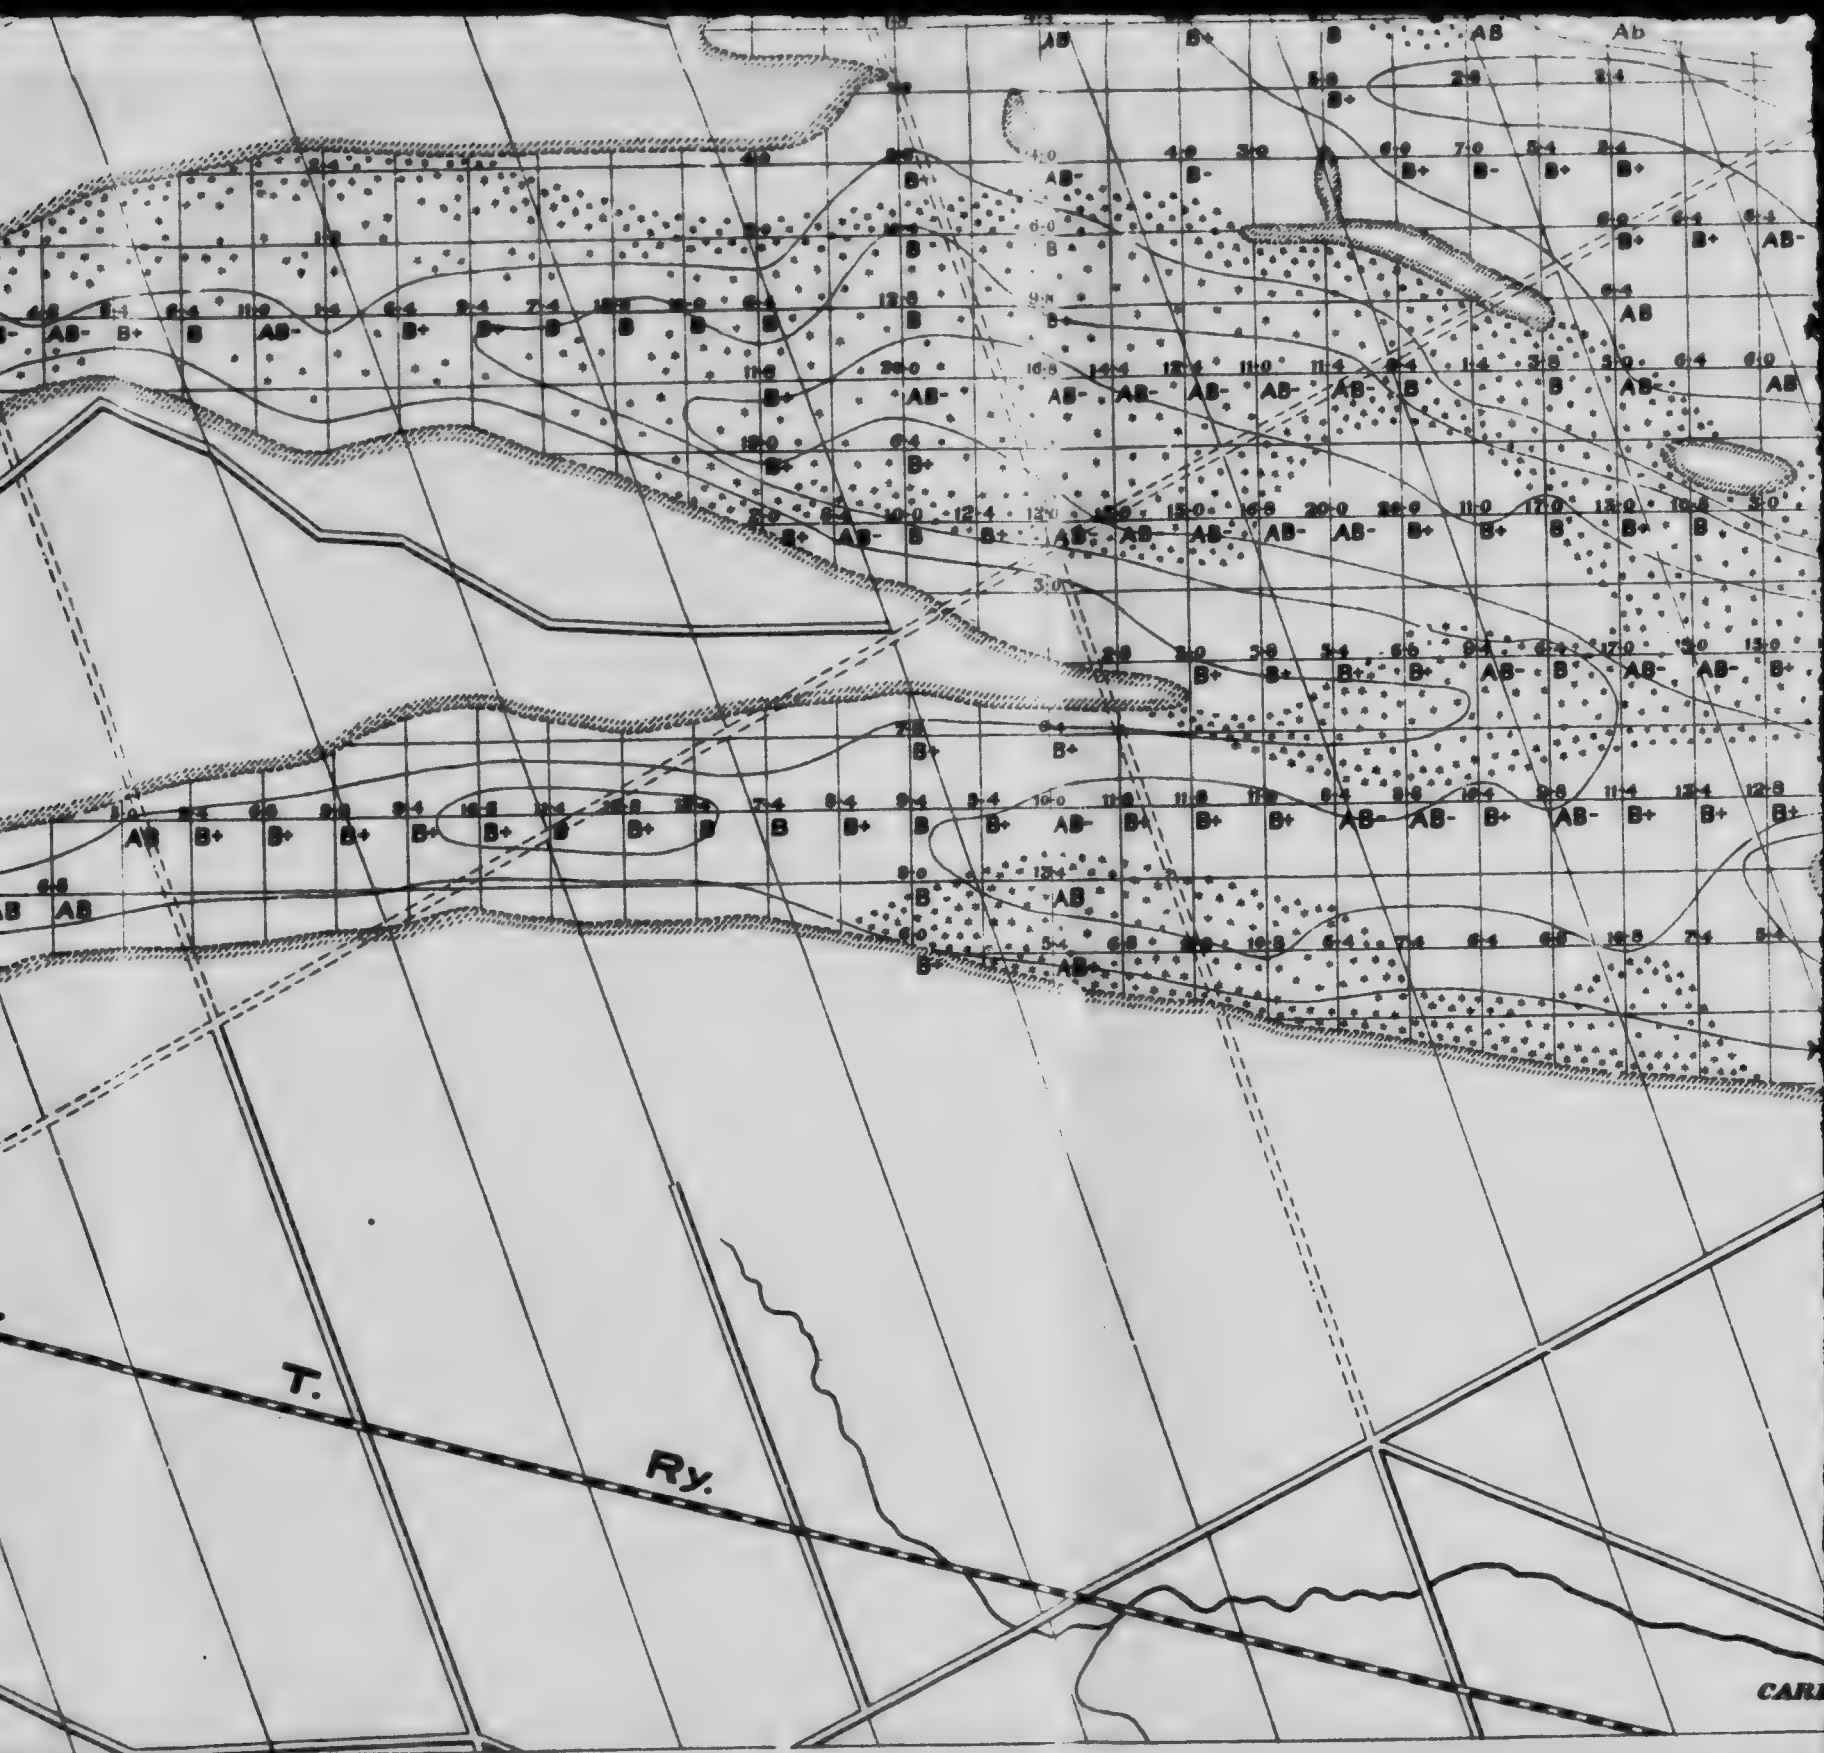

Scale 5 inches = 1 mile

היה זה חתונה

● ● ● ● ● ● ● ● ● ●
● ● ● ● ● ● ● ● ● ●
● ● ● ● ● ● ● ● ● ●
● ● ● ● ● ● ● ● ● ●

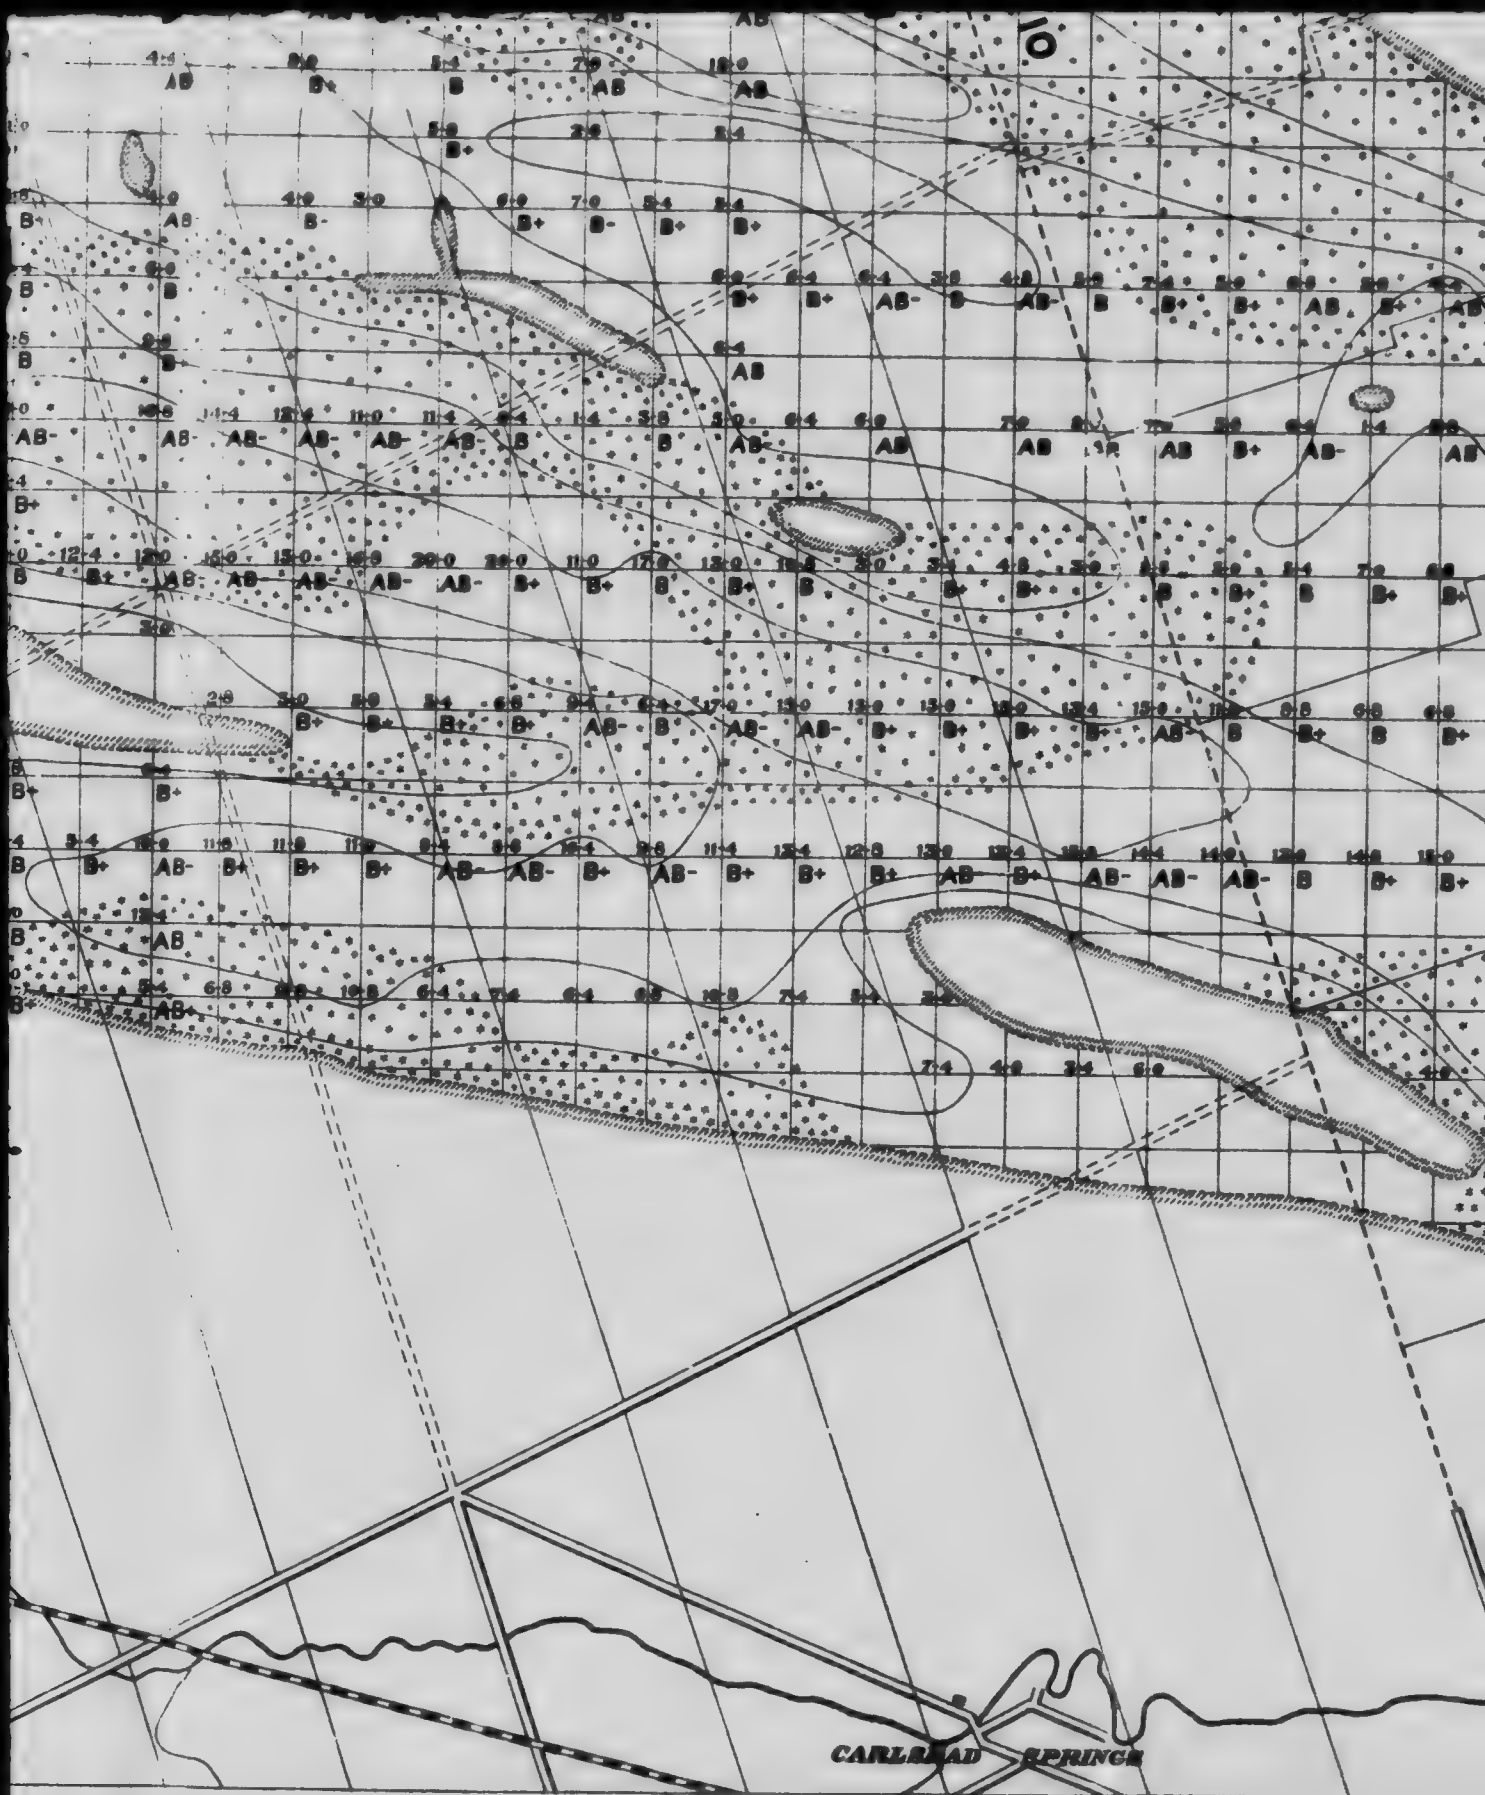

ches = 1 mile
f bog.
ooded areas.



No. 36

The peat is fairly well humified and uniform in quality, and, with proper treatment, will produce a comparatively good peat fuel.

The peat, after the bog is thoroughly drained, will probably settle down from one to three feet.

Deducting, therefore, the 1,564 acres, which at present have an average depth of about three feet and which are not likely to be profitably worked by machinery, and also allowing for the decrease in depth through drainage, we have left:—

2,237 acres with an average depth of approximately . . . 5 feet.

856 acres with an average depth of approximately . . . 9½ "

347 acres with an average depth of approximately . . . 13 "

with a total volume of 38,442,494 cubic yards of peat.

Assuming that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total tonnage of dry peat substance available is 3,844,249 tons of 2,000 lbs., or 5,125,655 tons peat fuel, with 25% moisture.

The bog consists of three distinct basins, partly separated by two comparatively high ridges. These ridges are east of lot 5 in Gloucester township, partly submerged in the bog, but in places form what may properly be called islands in the bog. The bottom of the bog is a compact blue clay.

The principal vegetation forming the peat in this bog is *Sphagnum*, more or less mixed with *Eriophorum* and most of the other plants given in the preceding tables.

Large areas of the surface of the bog are covered by a more or less heavy growth of spruce and tamarack, and the peat itself is intermixed with large quantities of roots, trunks, and stumps of trees.

Analyses of Peat (absolutely dry).

	1	2	3	4	5	6	7
Volatile matter	65.90	67.57	68.40	63.22	68.76	68.73	69.49
Fixed carbon	24.22	25.35	25.00	24.86	25.73	26.27	26.04
Ash	10.88	7.18	6.60	11.92	5.51	5.00	4.47
Phosphorus		0.026				0.024	
Sulphur		0.314				0.317	
Nitrogen		1.40				1.13	
Caloric value B.T.U. per lb.	8821	9021		8805	9126	9441	9301

The content of ash, although in some cases comparatively high, is not excessive, and the calorific value is satisfactory.

In order to work this bog profitably on a larger scale, it has to be thoroughly drained. Such drainage will, undoubtedly, involve a large expenditure of money, but considering the value of the land that would be recovered and which at present is practically valueless, and also the improvement which would result in the surrounding farming land through such drainage, such an undertaking would eventually be a paying proposition. The greater part of the bog could then be utilized, either for the manufacture of peat fuel, for agricultural purposes, or both.

The bog is exceedingly well situated both in regard to shipping facilities and probable market, the centre of the bog being only about eight miles from Ottawa. The Canadian Pacific railway (Ottawa-Montreal line) passes on the north side of the bog, and the Grand Trunk railway (Ottawa-Montreal line) on the south side.

ALFRED PEAT BOG.

This bog is situated about 40 miles from Ottawa, in the townships of Alfred and Caledonia (see accompanying map) and covers more or less of:—

Lots 6-10, con. VII,	township of Alfred,
Lots 6-13, con. VIII,	" "
Lots 8-13, con. IX,	" "
Lots 13-24, con. I,	township of Caledonia,
Lots 9-24, con. II,	" "
Lots 9-18, con. III,	" "

also extending into the township of Longueuil.

The total area covered by this bog is approximately 6,800 acres. Of this area

1,377 acres have a depth of less than 5 feet, average depth 3'-10"

3,084 acres have a depth of 5 to 10 feet, average depth 8 feet.

1,316 acres have a depth of 10 to 15 feet, average depth 11'-10"

1,014 acres have a depth of more than 15 feet, average depth 16'-5"

The volume of the peat contained is:—

In the area with a depth of less than 5 feet 8,441,928 cub. yds.

5 to 10 feet deep 39,800,592 " "

10 to 15 feet deep 25,093,136 " "

more than 15 feet deep 26,846,800 " "

The peat in the part of the bog located in Alfred township is, with the exception of that immediately surrounding the small pond shown on the map, comparatively well humified and will produce a good fuel.

The upper layers of the part of the bog located in Caledonia township are, especially in the centre of that part, comparatively poorly humified, and a fairly light fuel can there be expected.

Deducting the 1,377 acres with a depth of less than five feet, and allowing for the decrease in depth through drainage, we have left:—

3,084 acres with an average depth of approximately . . . 6 feet.


1,316 acres with an average depth of approximately . . . 9 "

1,014 acres with an average depth of approximately . . . 13 "

with a total volume of 70,270,200 cubic yards of peat.

Calculating that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total tonnage of dry peat substance available is 7,027,000 tons of 2,000 lbs., or 9,369,000 tons peat fuel, with 25% moisture.

The bog consists of one large basin, the deeper part of which is located in Caledonia township. In the northern part of the bog in Alfred township a

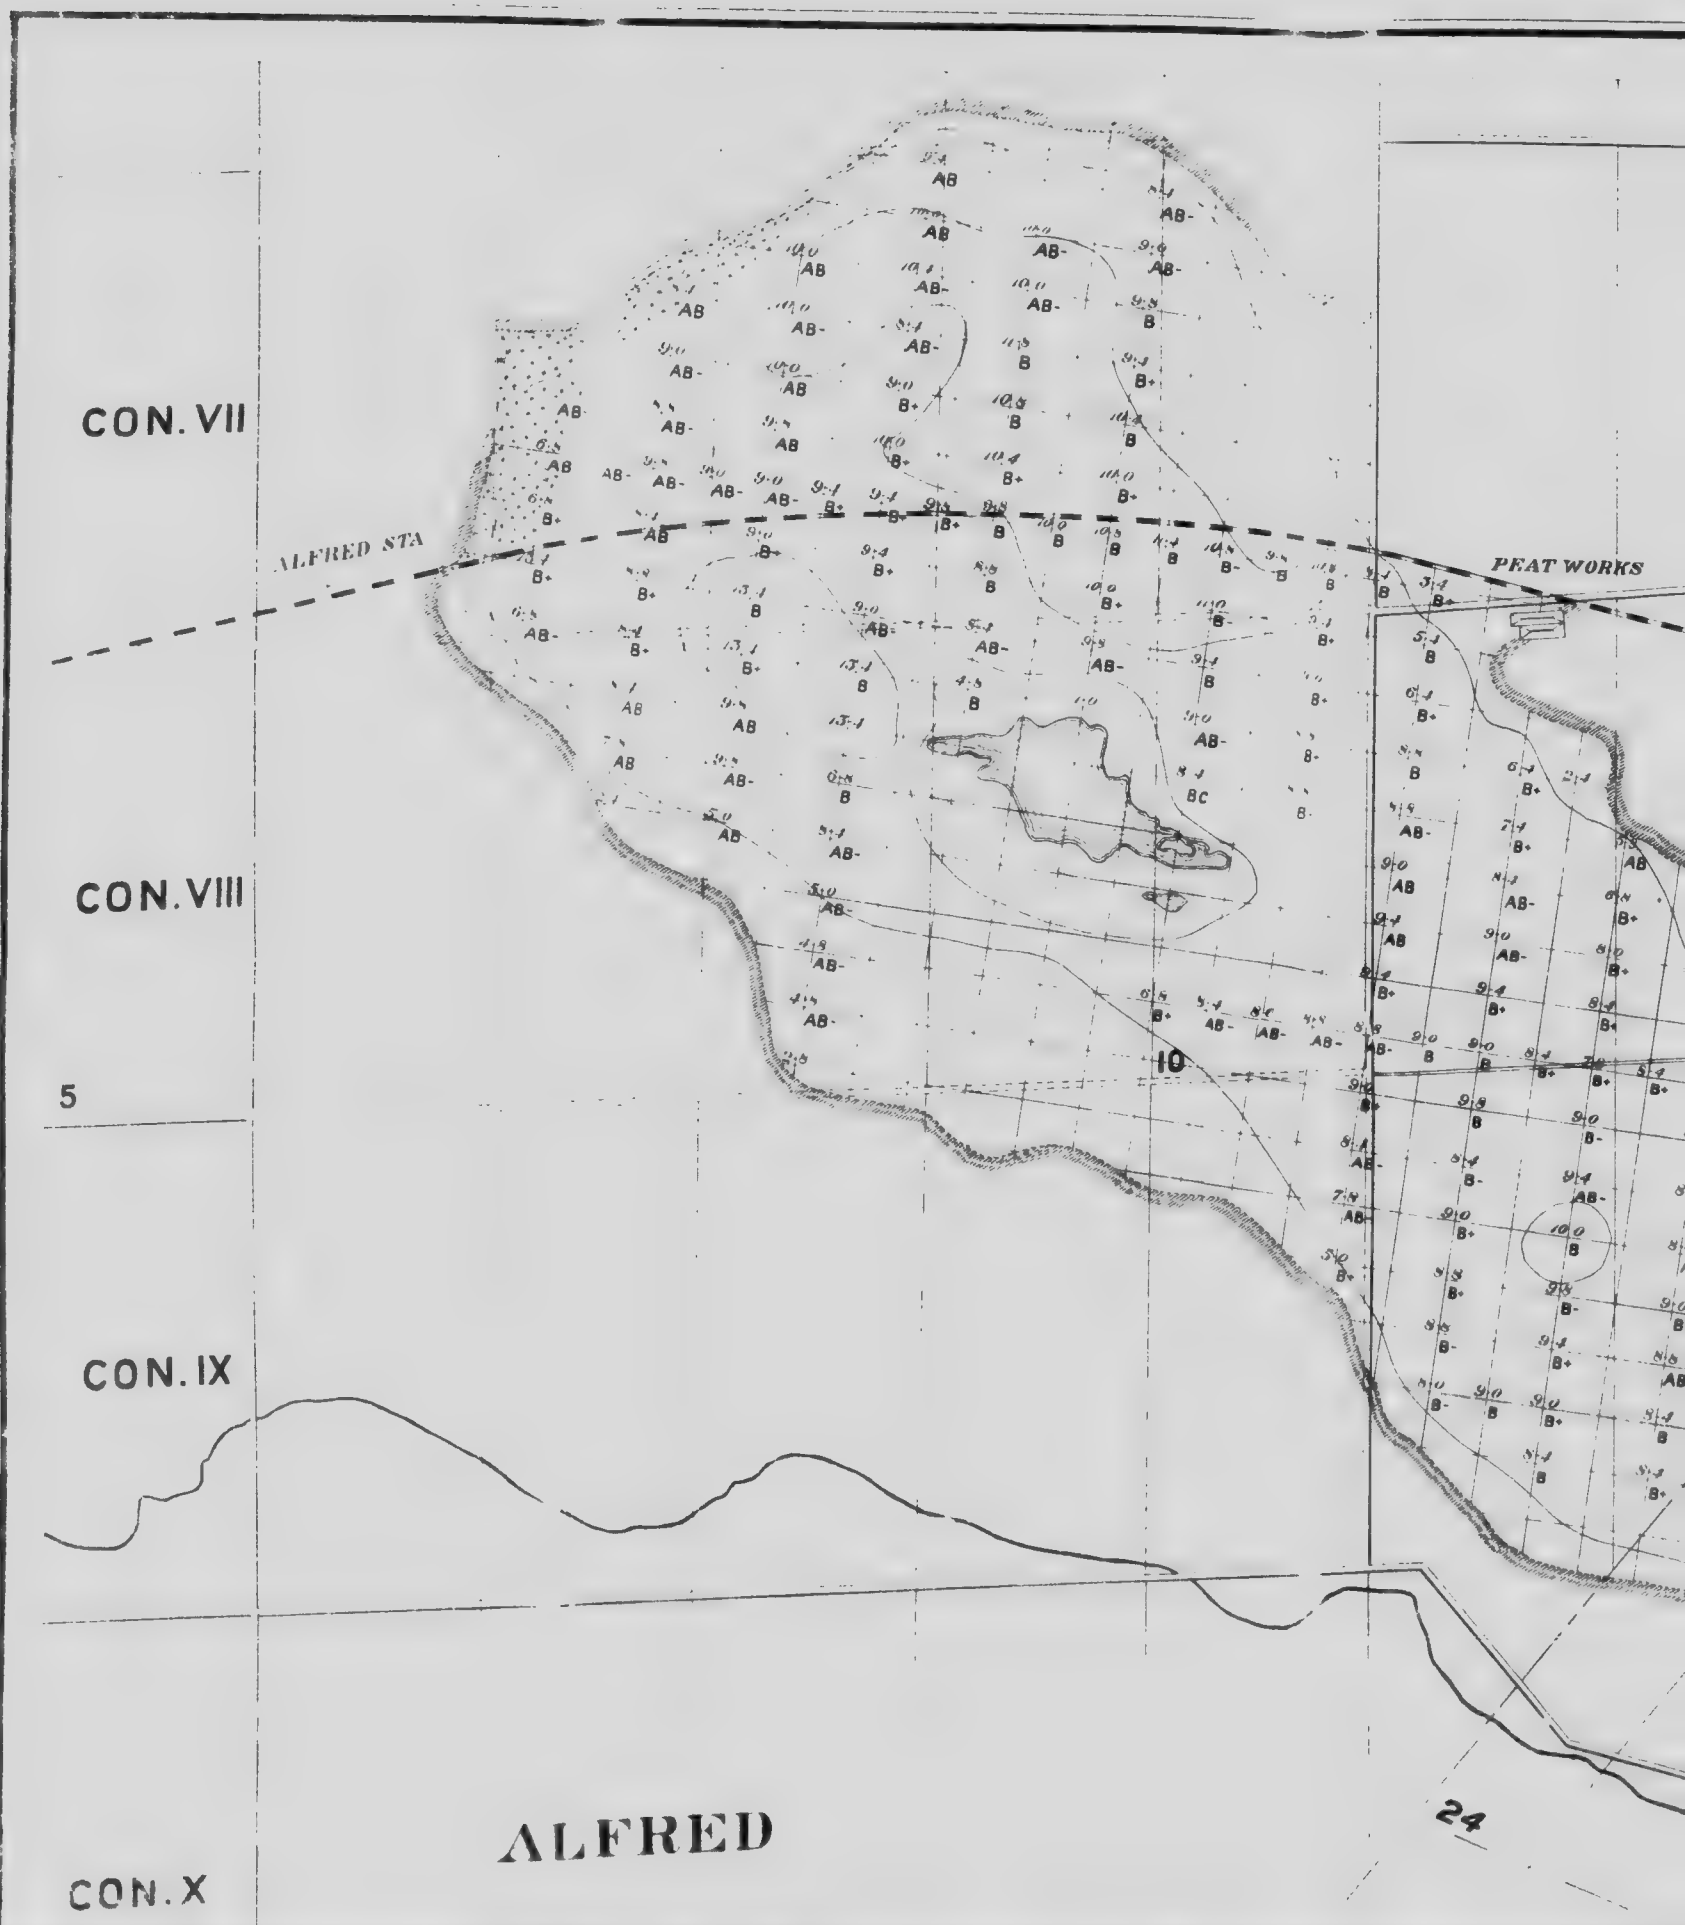

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL. D., DEPUTY MINISTER;
FNE HAASEL, PH. D., DIRECTOR

E



Hon. W. J. KEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAASEL, PH.D., DIRECTOR.

ALFRED PEAT BOG



LONGEUIL



CON.X

ALFRED

24

CON.XI

CON. III


CALEDONIA

CON.XII

CON. IV

CON.XIII

CON. V

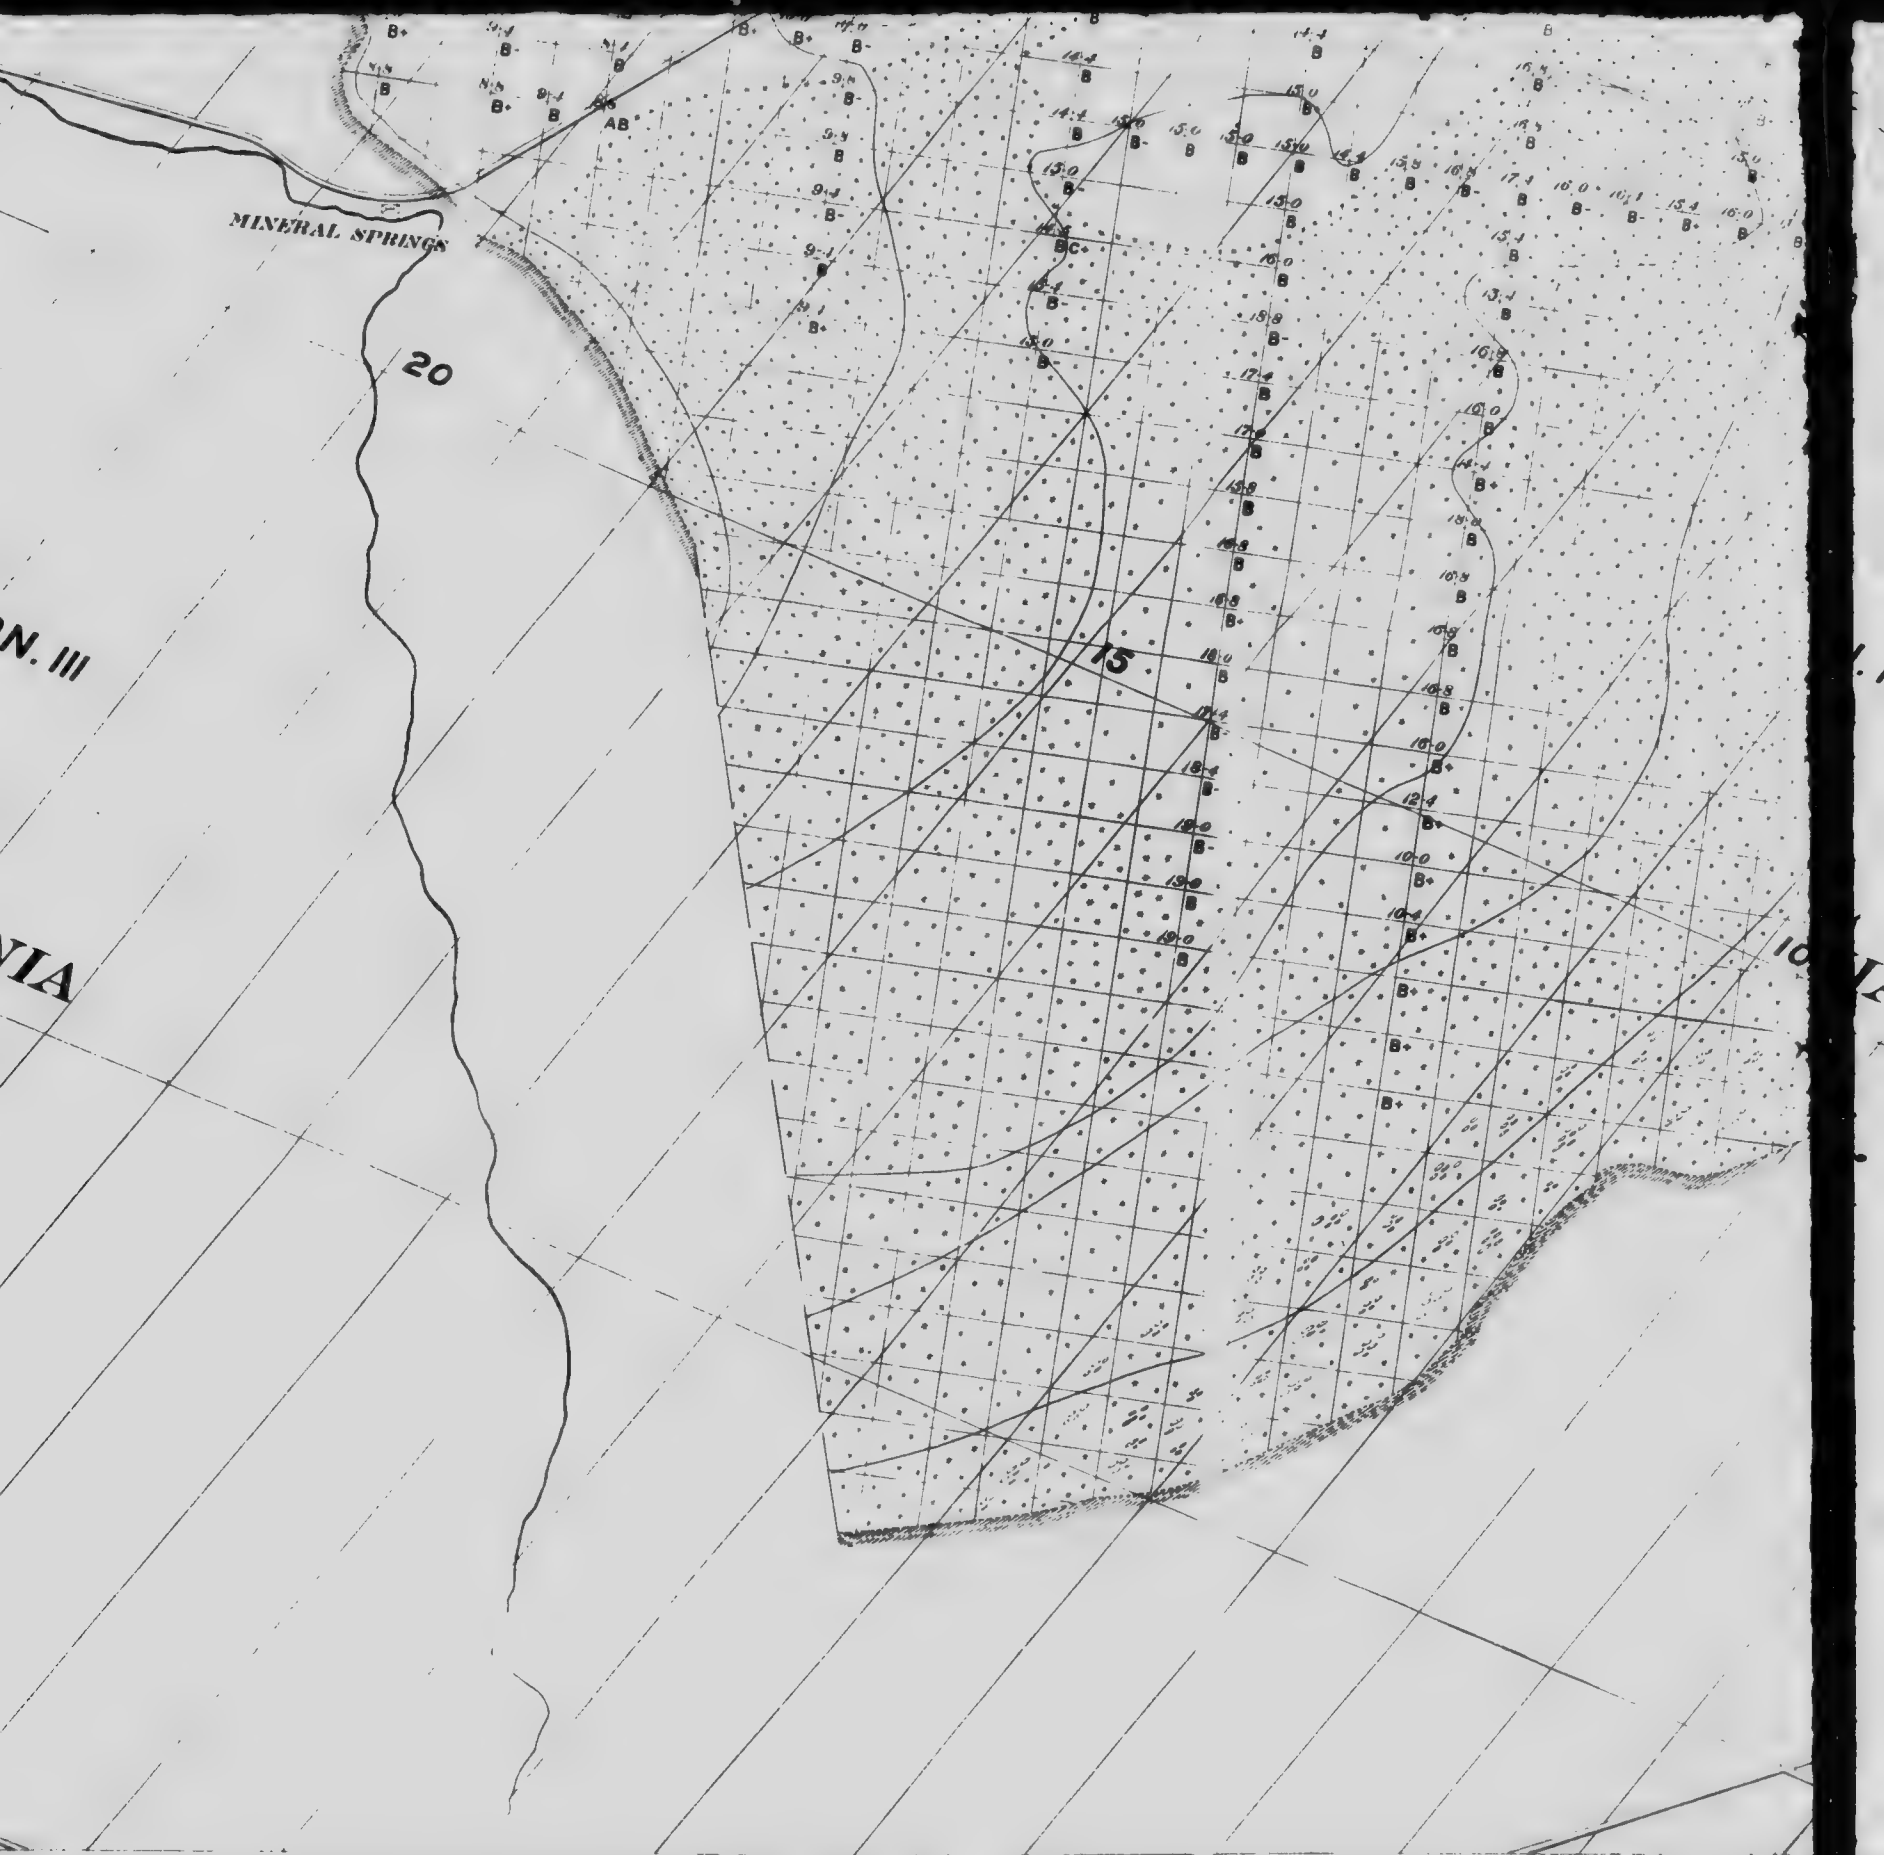

Scale 5 inches = 1 mile

 Margin of bog.

 Heavily wooded areas.

MINERAL SPRINGS


20

15

Scale 5 inches = 1 mile

 Margin of bog.

 Heavily wooded areas.

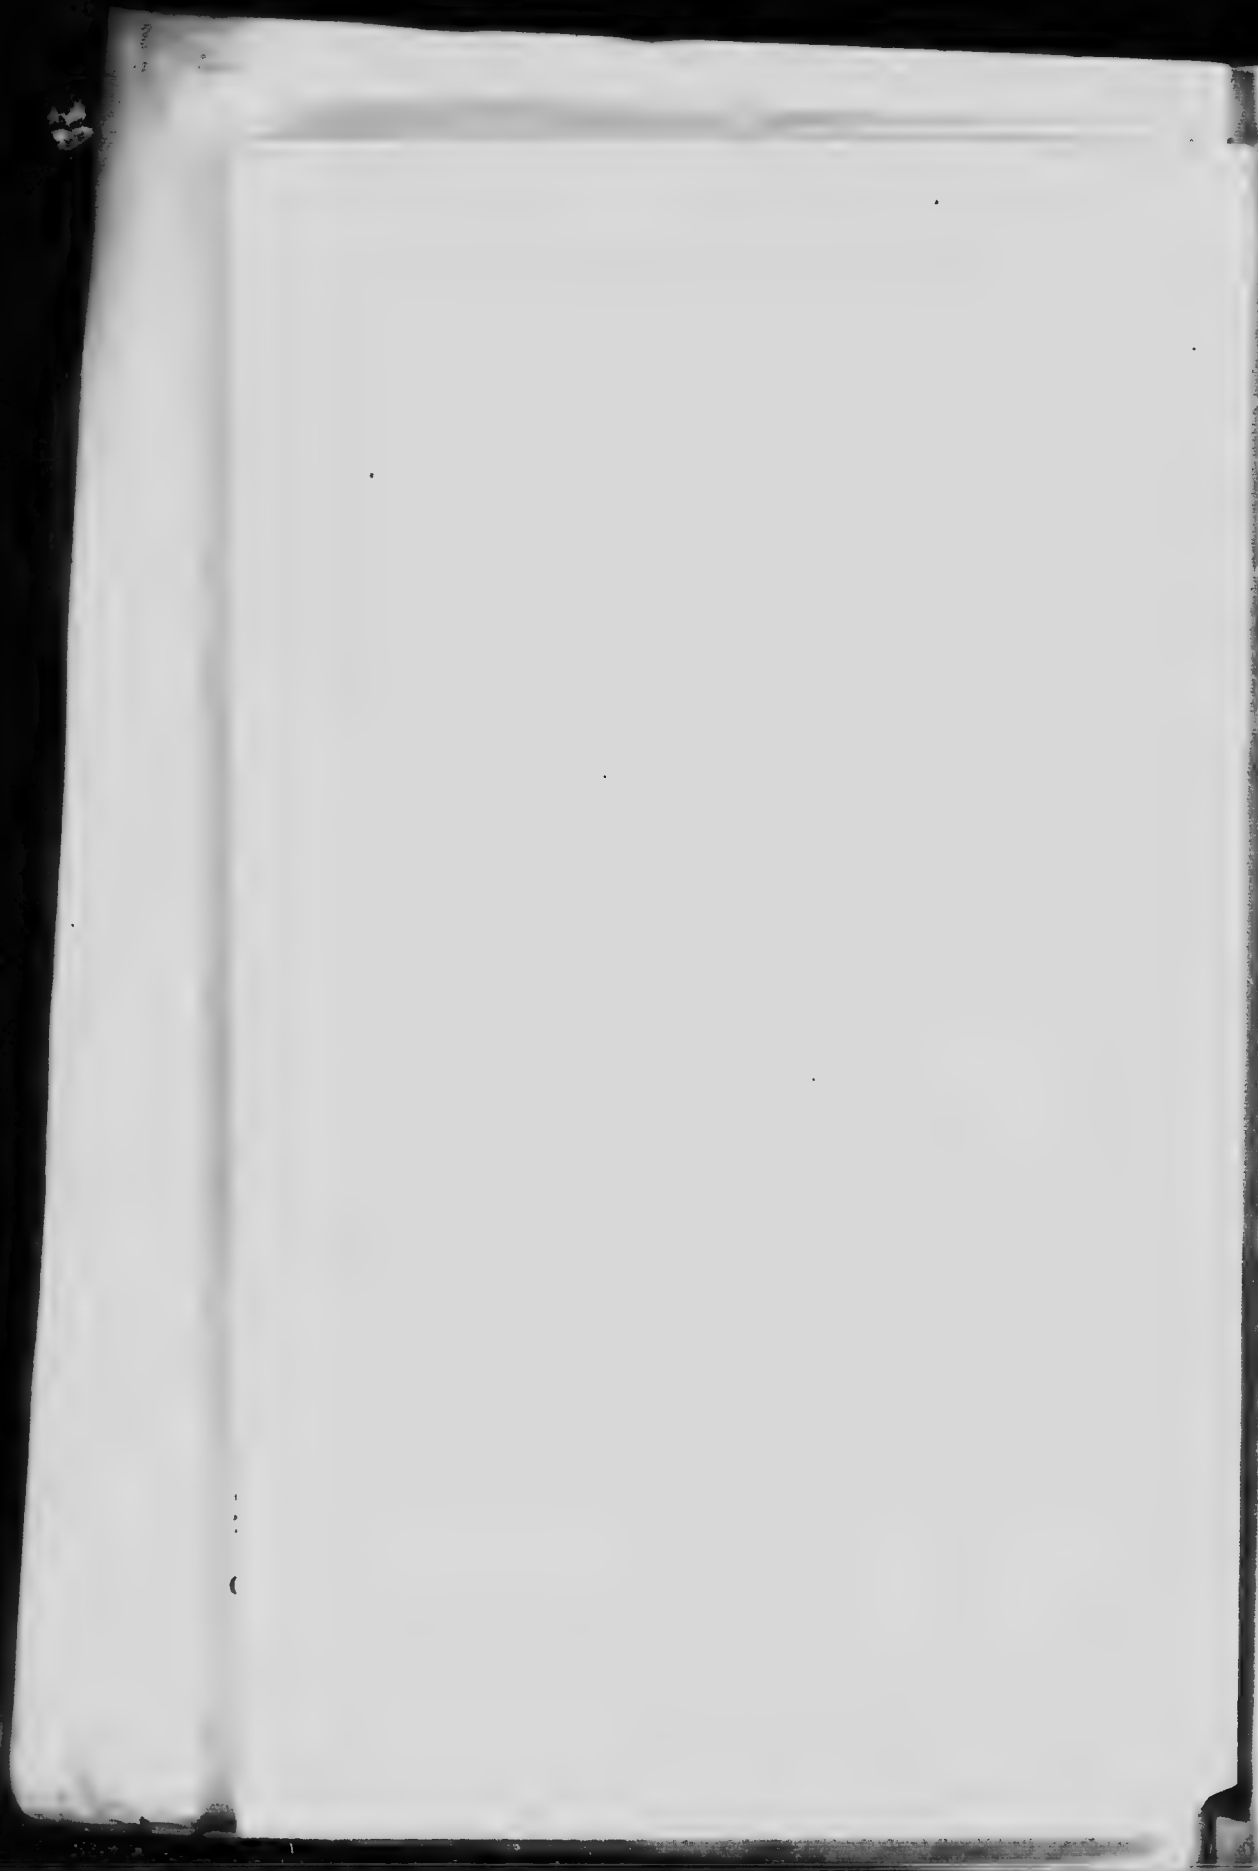

comparatively deep depression also occurs, and the peat contained in this part of the bog is well suited for the production of fuel.

The peat is principally formed by *Sphagnum*, but in certain parts of the bog it is also mixed with *Eriophorum*, *Hypnum*, *Carex*, and, especially around the small pond, with the remains of typical aquatic plants. The northwestern part of the bog in Alfred township, for instance, is strongly mixed with *Eriophorum*, *Hypnum*, and, towards the margin, with *Carex*. The southeastern part of the bog in the same township is principally formed by *Sphagnum*, only slightly mixed with *Eriophorum* and the remains of grasses. The northern part of the bog in Caledonia township is strongly mixed with *Hypnum*, and the southern and eastern part with the remains of plants, such as *Vaccinium* and similar plants. In Caledonia township the bog is more or less heavily wooded with spruce and tamarack, and towards the margin with cedar and hardwood trees.

Certain parts of the bog contain large amounts of roots and stumps, especially in the southern part of Caledonia township, where in places it was impossible to get the drill through to the bottom, on account of these obstacles.

The bottom of the bog is a compact blue clay.

Analyses of Peat (absolutely dry).

	1	2
Volatile matter.....	68.13	68.72
Fixed carbon.....	26.56	24.22
Ash.....	5.31	7.06
Phosphorus.....	0.029	0.022
Sulphur.....	0.292	0.375
Nitrogen.....	1.23	1.92
Calorific value B.T.U. per lb.....	8730	9058

The content of ash is about the average, and the calorific value satisfactory.

Part of this bog in Alfred township is traversed by the Canadian Pacific railway (Ottawa-Montreal line), which also touches a part of the bog in Caledonia township. As regards transportation facilities the bog is, therefore, well situated, and the distance to Ottawa being only some forty miles the freight rates ought not to be excessive.

The greater portion of the bog in Alfred township is already fairly well drained and the balance of the water could probably be handled by a pump. Large areas of the shallow parts of the bog are yearly burnt off by the farmers and the land utilized for agricultural purposes.

Some years ago the Montreal and Ottawa Peat Company erected a peat plant at this bog, and started to manufacture peat briquettes in accordance with the Dobson method. (For description of this method see Bulletin No. 5 published by the Ontario Bureau of Mines, Toronto, and also Report on Peat and Lignite, by E. Nystrom, published by the Mines Branch, Department of

Mines, Ottawa). Only a few hundred tons of briquettes were made, however, and the plant has been closed down for several years.

The Company owns the north half of lots 9, 10 and 11, con. VIII, township of Alfred.

The bog contains a large amount of the fibrous and less humified variety of peat, which is less suitable for the Dobson process.

WELLAND PEAT BOG.

This bog is situated in the townships of Wainfleet and Humberstone, six miles north of the town of Welland, and between the Welland canal and its feeder (see accompanying map) and covers more or less of:—

Lots 1- 8, con. IV, township of Wainfleet.
 Lots 1-13, con. III, " "
 Lots 4-13, con. II, " "
 Lots 27-33, con. IV, township of Humberstone.
 Lots 27-33, con. III, " "

The total area covered by this bog is approximately 4,900 acres. Of this area

1,423 acres have a depth of less than 5 feet, average depth 3 feet.

2,877 acres have a depth of 5 to 10 feet, average depth 7'-3"

588 acres have a depth of more than 10 feet, average depth 11 feet.

The volume of the peat contained is:—

In the area with a depth of less than 5 feet . . .	6,885,170	cub. yds.
5 to 10 feet deep	33,662,231	" "
more than 10 feet deep	10,427,600	" "

In the western and eastern parts of the bog and around the margins the peat is well humified, and is mainly formed by the remains of *Hypnum* and *Eriophorum*, with only a small amount of *Sphagnum*, *Carex* and aquatic plants. In the central part of the bog the peat is mainly formed by *Sphagnum*, with small amounts of *Eriophorum* and other plants. The peat in this part, especially in the upper layers, is very poorly humified and unsuitable for the manufacture of fuel, but will furnish a fairly good material for the production of moss litter.


The bog, as shown above, is comparatively shallow, and deducting the 1,423 acres with a depth of less than 5 feet, allowing for the decrease in depth through drainage, and assuming that the balance could be utilized, we have left:—

2,877 acres with an average depth of approximately5 feet.

588 acres with an average depth of approximately8 "
 with a total volume of 30,796,480 cubic yards of peat.

With the assumption that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total onnage of dry peat substance is 3,079,600 tons of 2,000 lbs., or 4,106,000 tons peat fuel, with 25% moisture.

THE

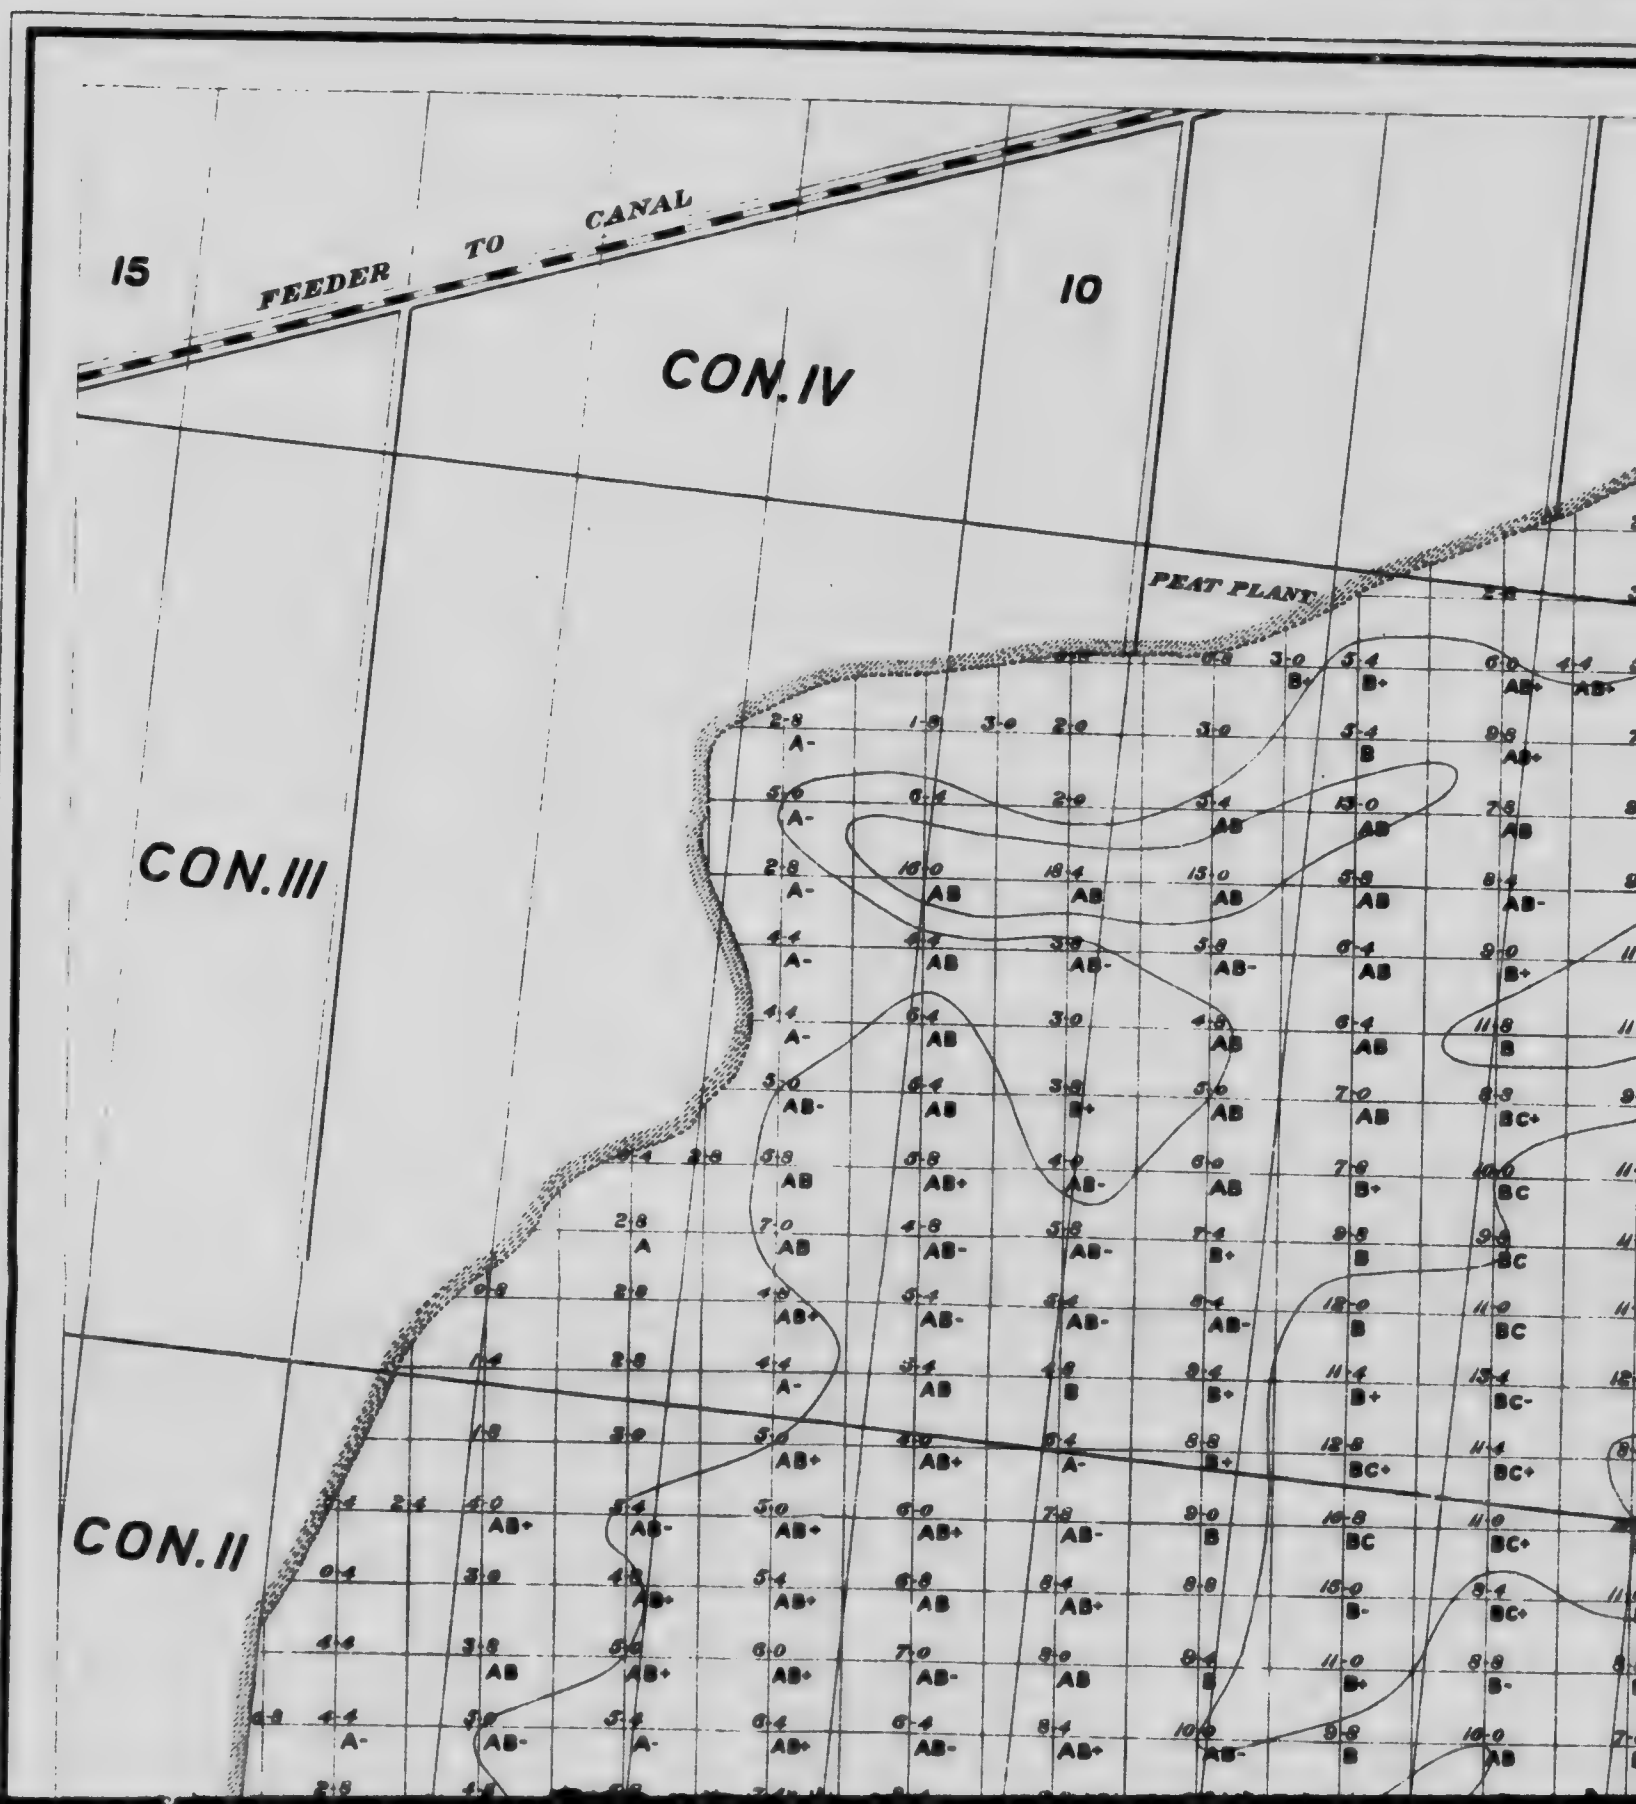

CANADA
DEPARTMENT OF MINES
MINES BRANCH

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAANEL, PH.D., DIRECTOR.

E WELLAND PEAT BOG



ADA
OF MINES

RANCH
P. LOW, LL.D., DEPUTY MINISTER;
W.D., DIRECTOR.

D PEAT BOG



30


26

CON. IV



ON. III

CON.II

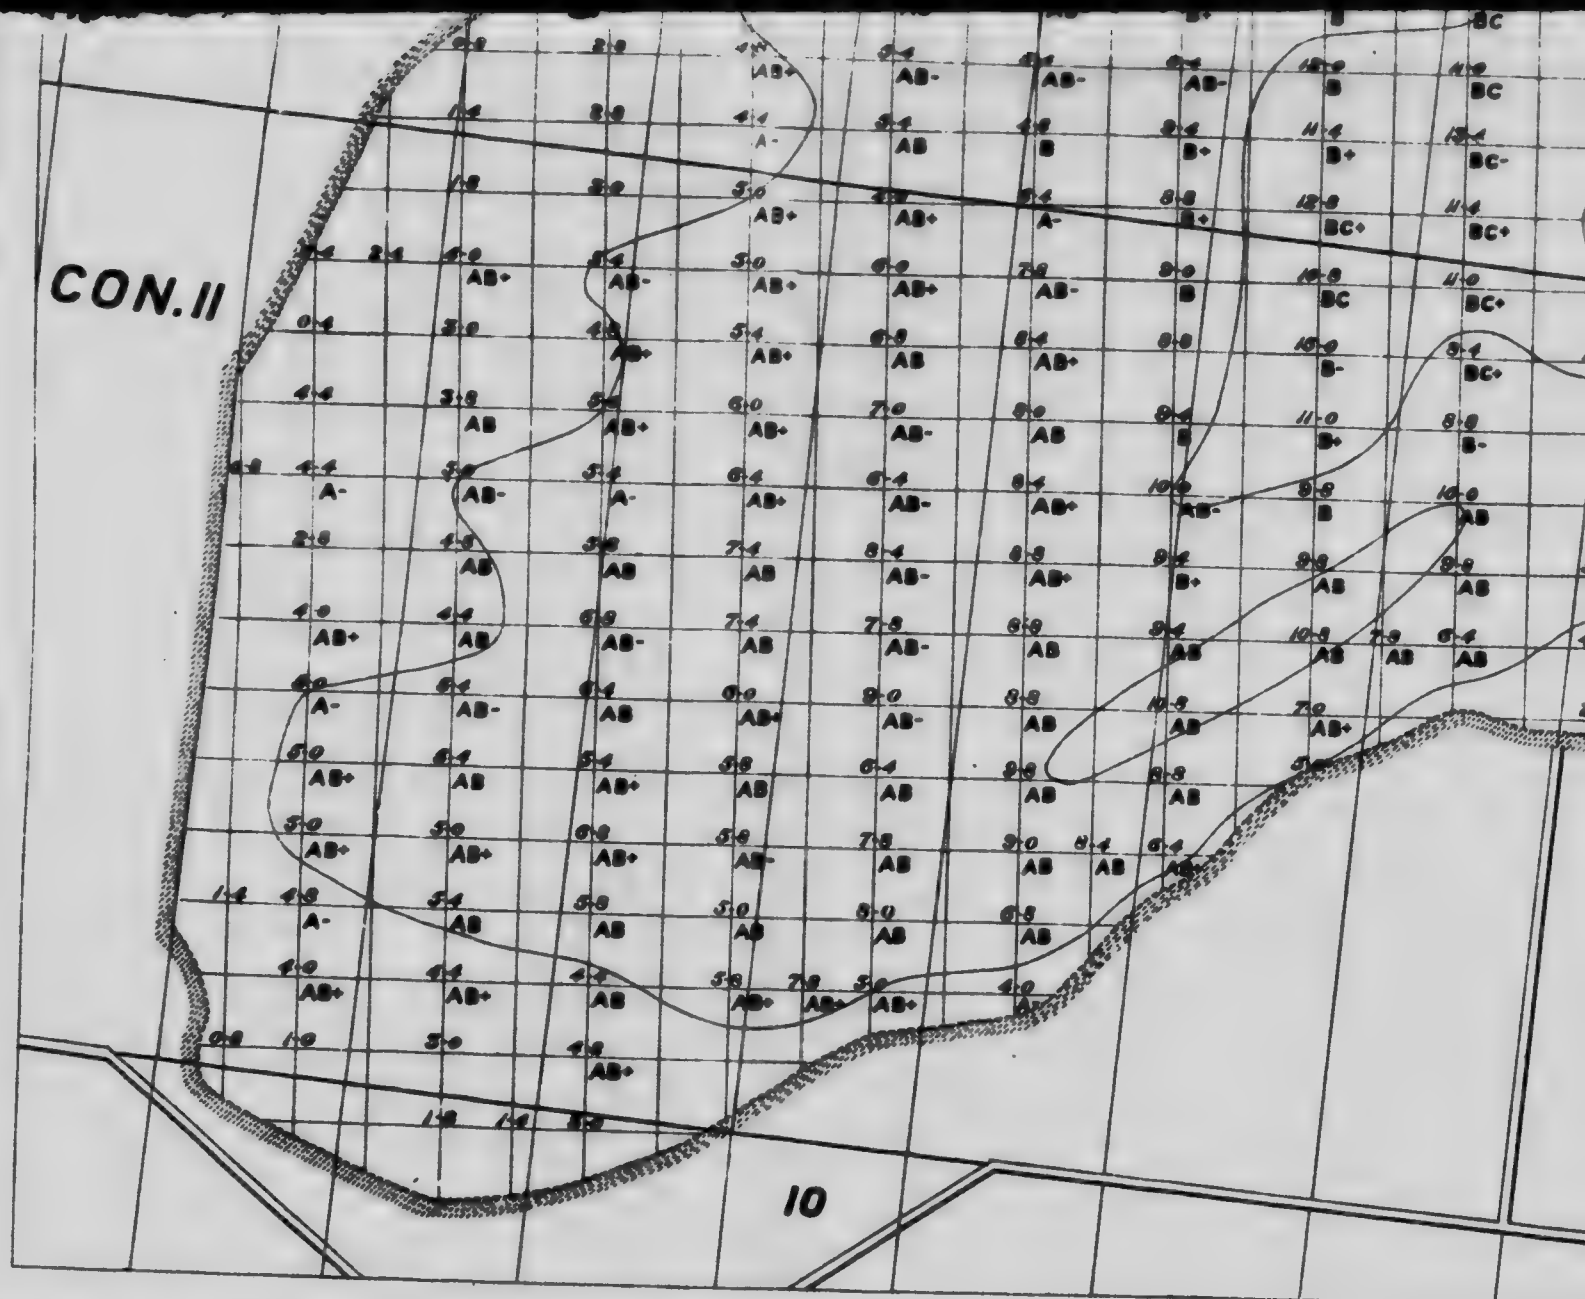


ERIK NYSTRÖM, Mining Engineer.
S. A. ANREP, Post Expert.



Scale 5 inches. 1 mile

 *Margin of bog.*

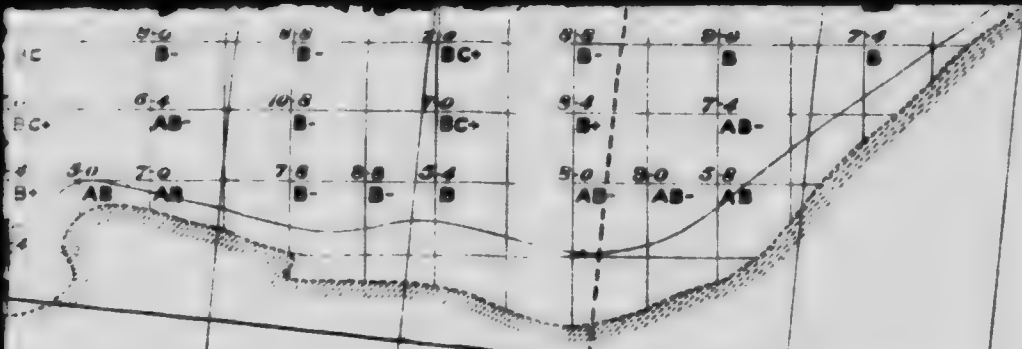

CON

HUMBERSTONE

CON. II

1

33

30

nches- 1 mile
margin of bog.

CON. III

ONE

II

WELLAND CANAL

25

No. 38

A very great amount of roots and stumps of trees are intermixed with the peat and large areas have been burnt to considerable depth. Taking into account also the large area of poorly decomposed peat, this bog is not well adapted for the manufacture of fuel on a large scale.

The bog consists of one large basin with clay bottom. The surface of the bog is comparatively free from growing trees, with the exception of some small areas in its central parts and around the margin.

Analyses of Peat (absolutely dry).

	1	2	3
Volatile matter.....	67.14	70.90	70.53
Fixed carbon.....	26.48	24.84	24.28
Ash.....	6.38	4.26	5.19
Phosphorus.....	0.027	0.024	
Sulphur.....	0.317	0.248	
Nitrogen.....	1.13	1.74	
Calorific value B.T.U. per lb.....	9118	8596	8667

The bog is held under lease by the Peat Industries, Ltd., of Brantford, which Company some years ago erected a plant and carried out extensive experiments. The results obtained must have been unsatisfactory, since no work has been done for several years. (For description of the methods used, see Bulletin No. 5, published by the Ontario Bureau of Mines, and Report on Peat and Lignite by E. Nystrom).

NEWINGTON PEAT BOG.

This bog is situated in the townships of Osnabrock, Roxborough, and Cornwall, county of Stormont, on the New York and Ottawa railway, some 40 miles from Ottawa, close to the village of Newington (see accompanying map) and covers more or less the following areas:

Lots 1-5, con. VII.	township of Osnabrock
Lots 1-6, con. VII.	" "
Lots 2-3, con. VI.	" "
Lots 17-35, con. II.	township of Roxborough.
Lots 17-39, con. I.	" "
Lots 20-23, con. IX.	township of Cornwall.
Lots 26-30, con. IX.	" "
Lots 31-36, con. VI.	" "

The total area covered by this bog is approximately 3,800 acres. Of this area

- 929 acres have a depth of less than 5 feet, average depth 2 feet.
- 1,191 acres have a depth of 5 to 10 feet, average depth 8 feet.
- 748 acres have a depth of 10 to 15 feet, average depth 12 feet.
- 696 acres have a depth of 15 to 20 feet, average depth 17'-4"

158 acres have a depth of 20 to 25 feet, average depth 21' 4"

120 acres have a depth of more than 25 feet, average depth 26 feet.

The volume of the peat contained is:—

In the area with a depth of less than 5 feet.	2,996,704	cub. yds.
5 to 10 feet deep	15,378,518	" "
10 to 15 feet deep	14,491,111	" "
15 to 20 feet deep	19,542,777	" "
20 to 25 feet deep	5,464,926	" "
more than 25 feet deep	5,037,777	" "

The western part of the bog in Osnabruck township is a pure *Sphagnum* bog. The northern part in the same township is badly damaged on the surface by fires, and more or less unsuitable for the manufacture of fuel by ordinary processes, at least where the surface of the bog is used for a drying field.

The western part of the bog in Roxborough township is principally formed by *Sphagnum*, only slightly mixed with the remains of aquatic plants. This part will furnish fairly good material for the manufacture of moss-litter. The eastern part of the bog in the same township is heavily wooded and of a swampy character. The peat is here mixed with herbaceous plants.

The bog is fairly free from stumps and roots, and large areas are, as shown above, of considerable depth. With the exception of the part of the bog in the western part of Roxborough township, the peat is fairly well humified and suitable for fuel.

Deducting the 929 acres with a depth of less than 5 feet, and allowing for the decrease in depth through drainage, we have left:—

1,191 acres with an average depth of approximately 6 feet.

748 acres with an average depth of approximately 9 "

696 acres with an average depth of approximately 14 "

158 acres with an average depth of approximately 17 "


120 acres with an average depth of approximately 21 "

with a total volume of 46,566,478 cubic yards of peat.

With the assumption that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total tonnage of dry peat substance is 4,656,600 tons of 2,000 lbs., or 6,208,800 tons peat fuel, with 25% moisture.


Analyses of Peat (absolutely dry).

	1	2	3	4	5	6	7
Volatile matter	66.75	67.07	68.84	71.32	69.54	65.77	66.97
Fixed carbon	25.77	26.27	26.65	24.44	26.75	27.30	26.70
Ash	7.48	6.66	4.51	4.24	3.71	6.93	6.33
Phosphorus	0.028	0.030		0.032			
Sulphur	0.530	0.494		0.345			
Nitrogen	1.85	1.80		1.63			
Calorific value B.T.U. per lb.	8721	8465	8877	8636	9102	8210	8312

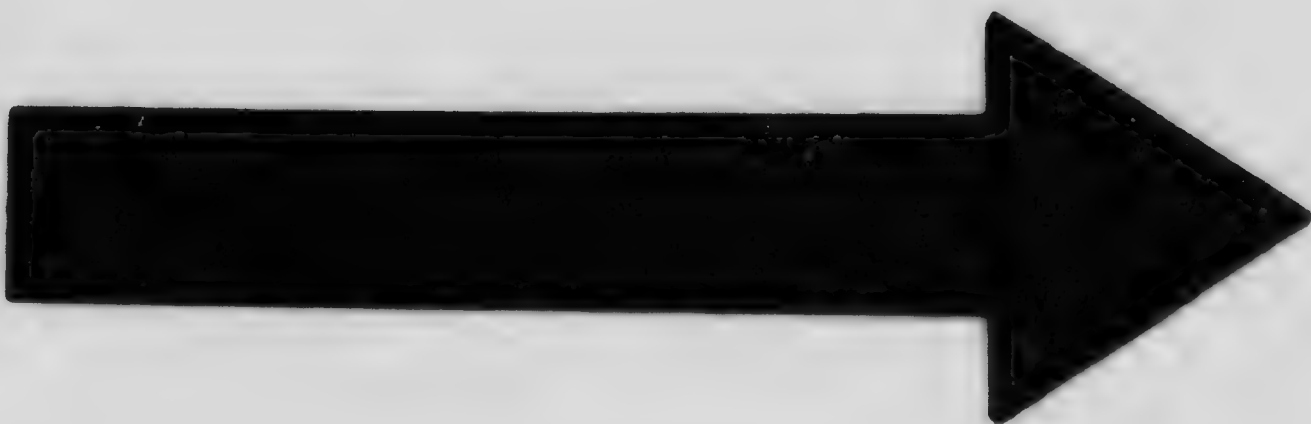

MICROCOPY RESOLUTION TEST CHART

(ANSI and ISO TEST CHART No. 2)

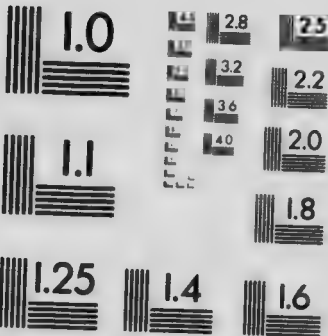

APPLIED IMAGE Inc

1653 East Main Street
Rochester, New York 14609 USA
(716) 482 - 0300 - Phone
(716) 288 - 5989 - Fax

CON. VIII

OSNABRUCK

NEW

NEWINGTON STA.

YORK

CON. VII



THE NEWINGTON

ROXBORO

35


30




NINES BRANCH

EUGENE HAANEL, Ph.D., DIRECTOR.

ROXBOROUGH

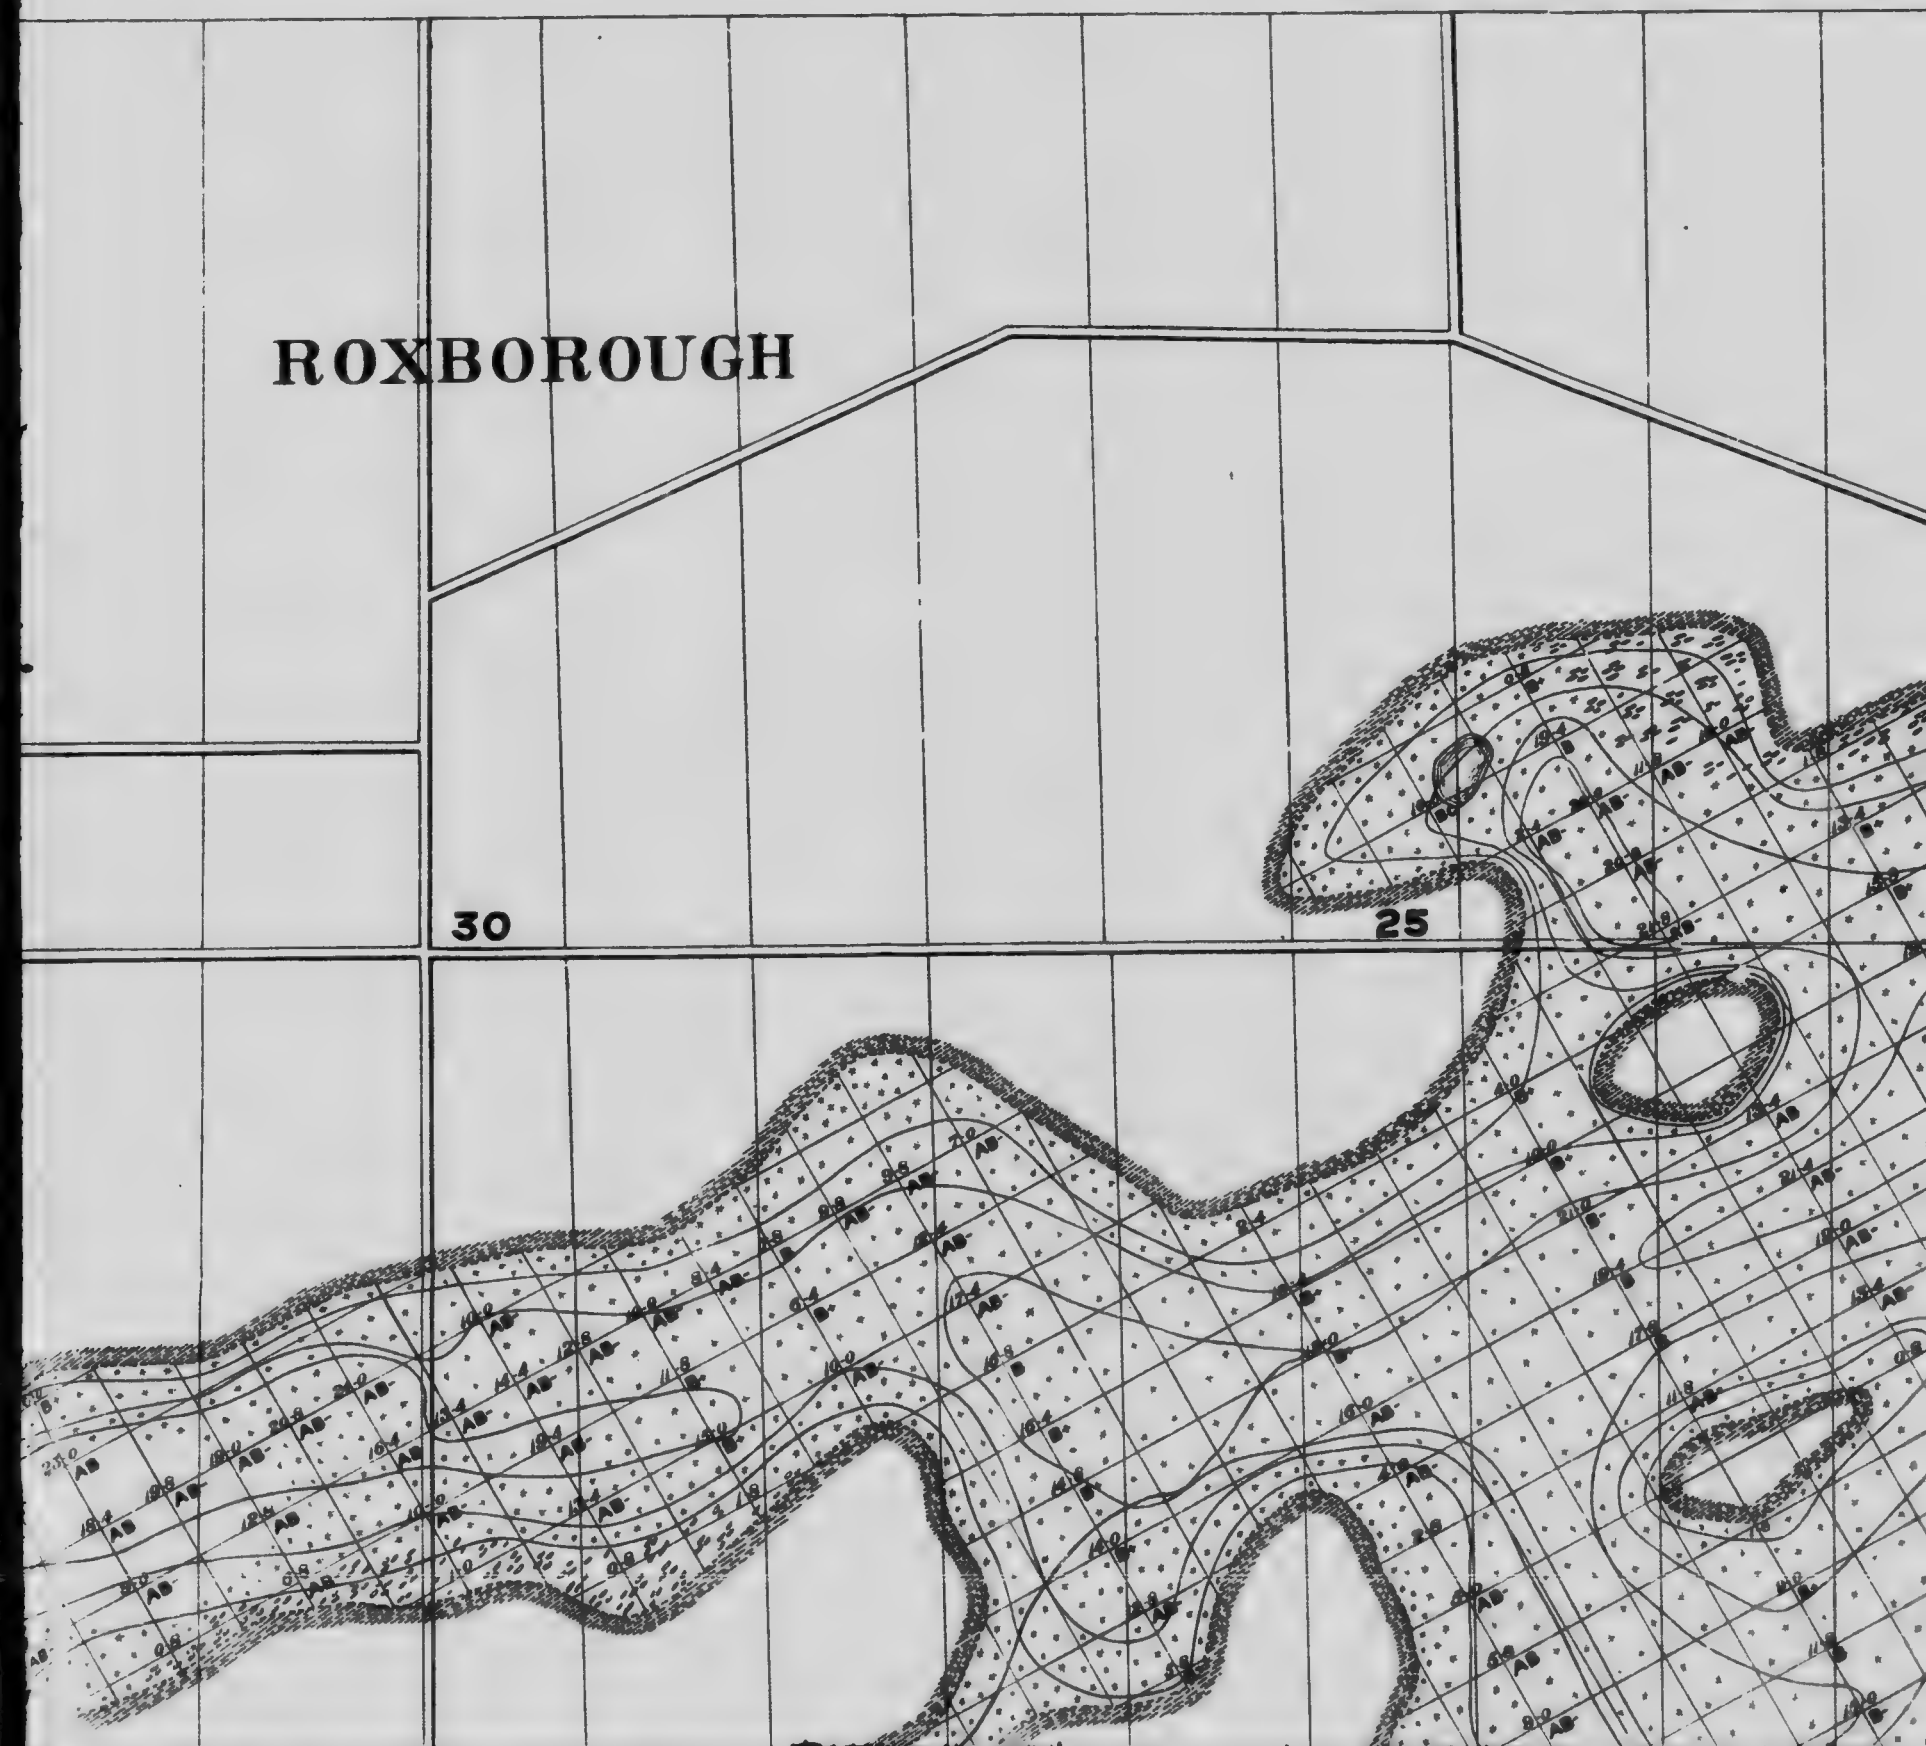

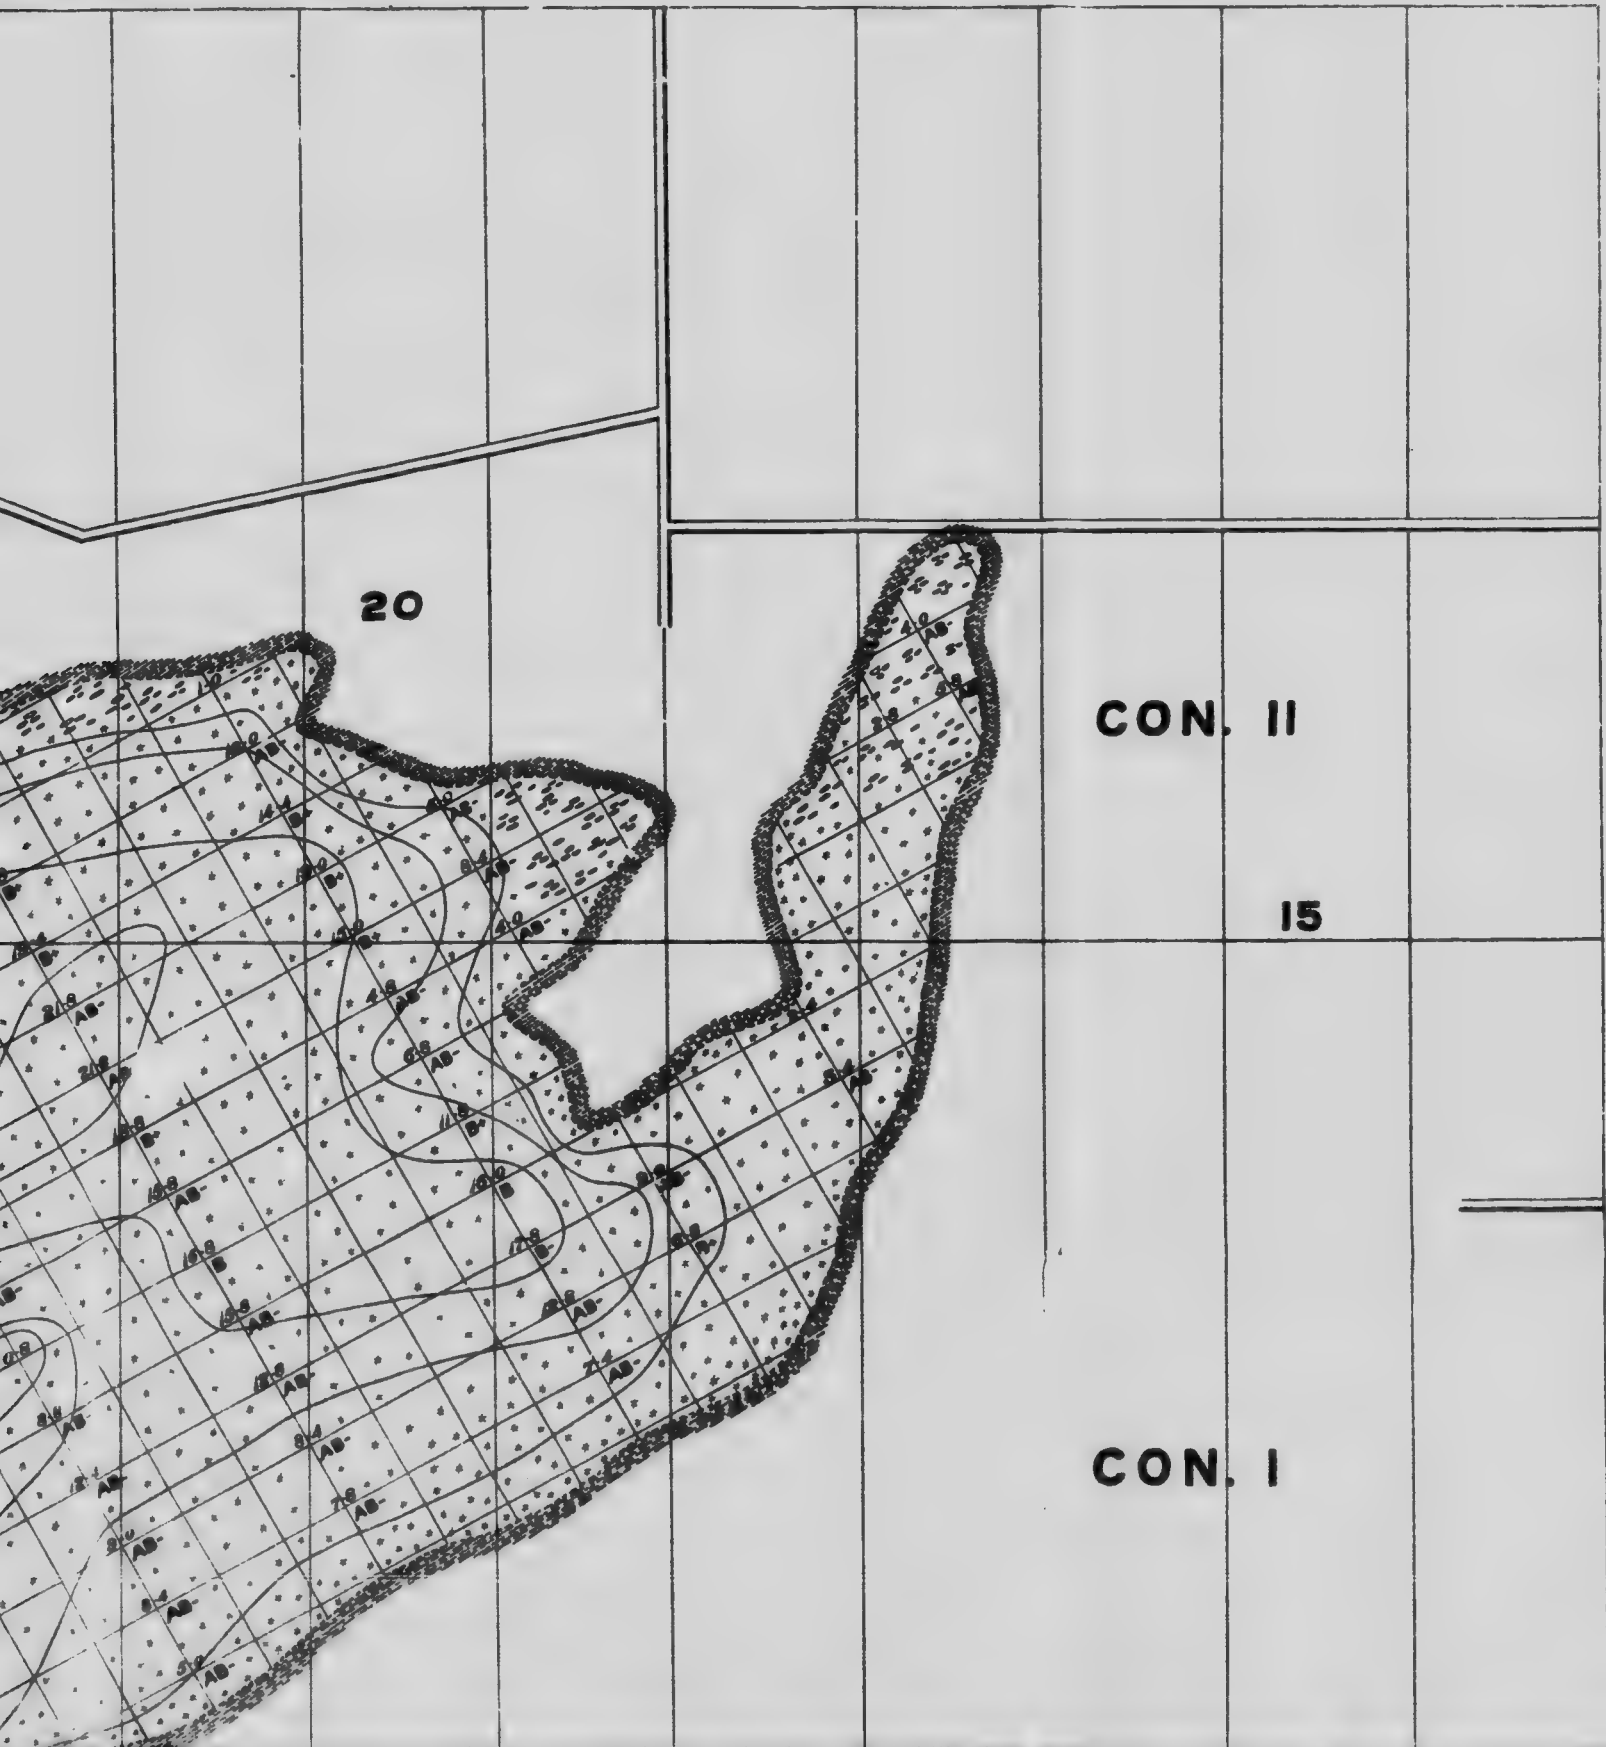

CON. VII


5

CON. VI

DIXON P.O.

5


ERIK NYSTRÖM, Mining Engineer.
S. A. ANREP, Peat Expert.

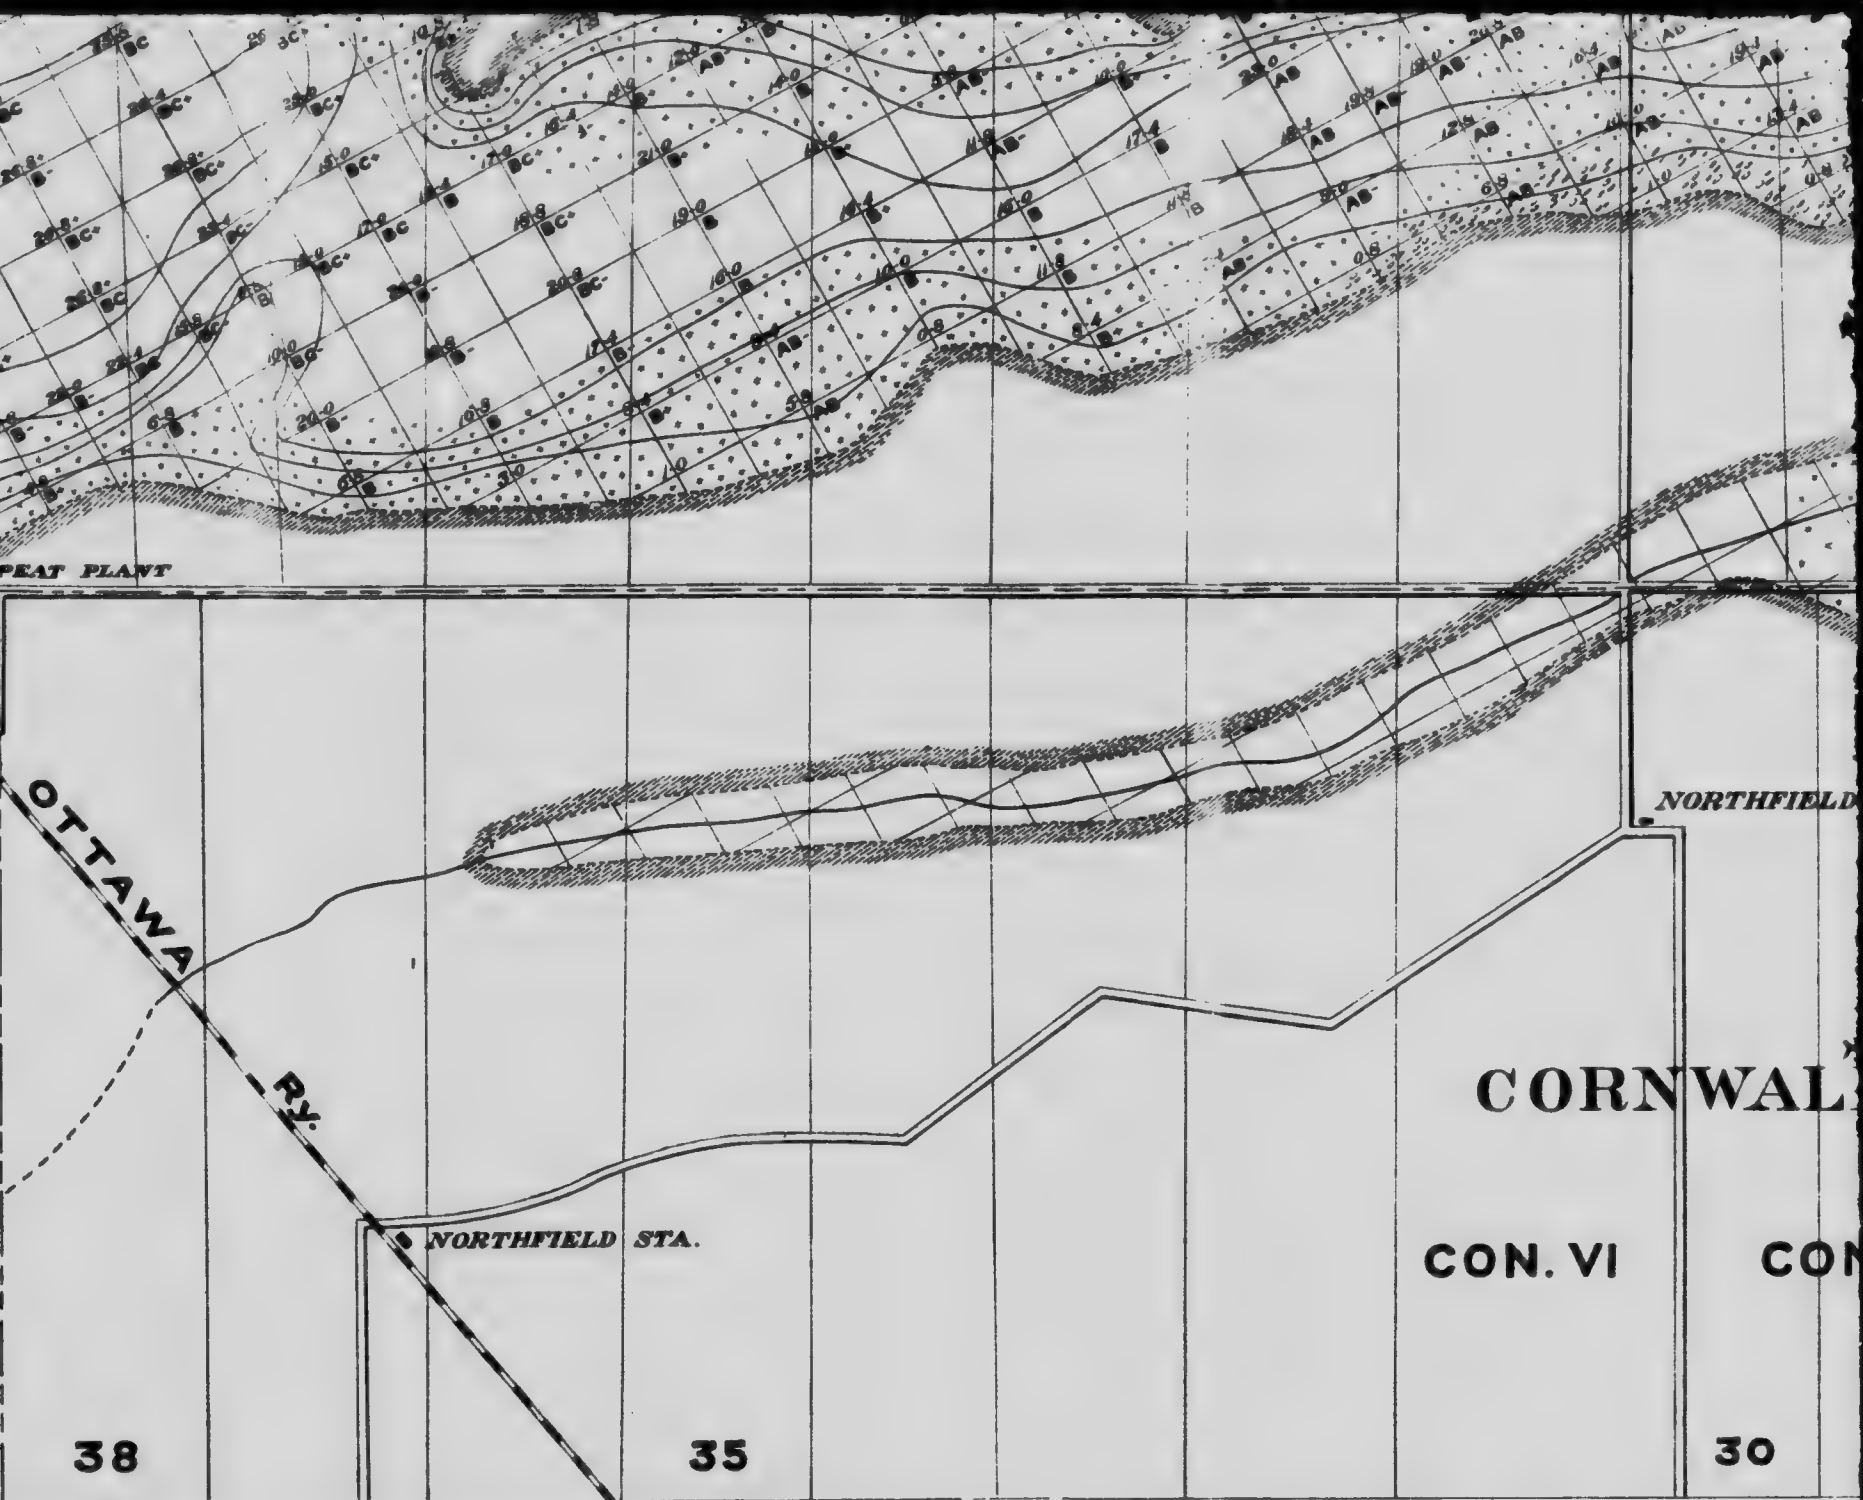

Scale 5 inches = 1

 *Margin of bog.*


 *Heavily wooded area*

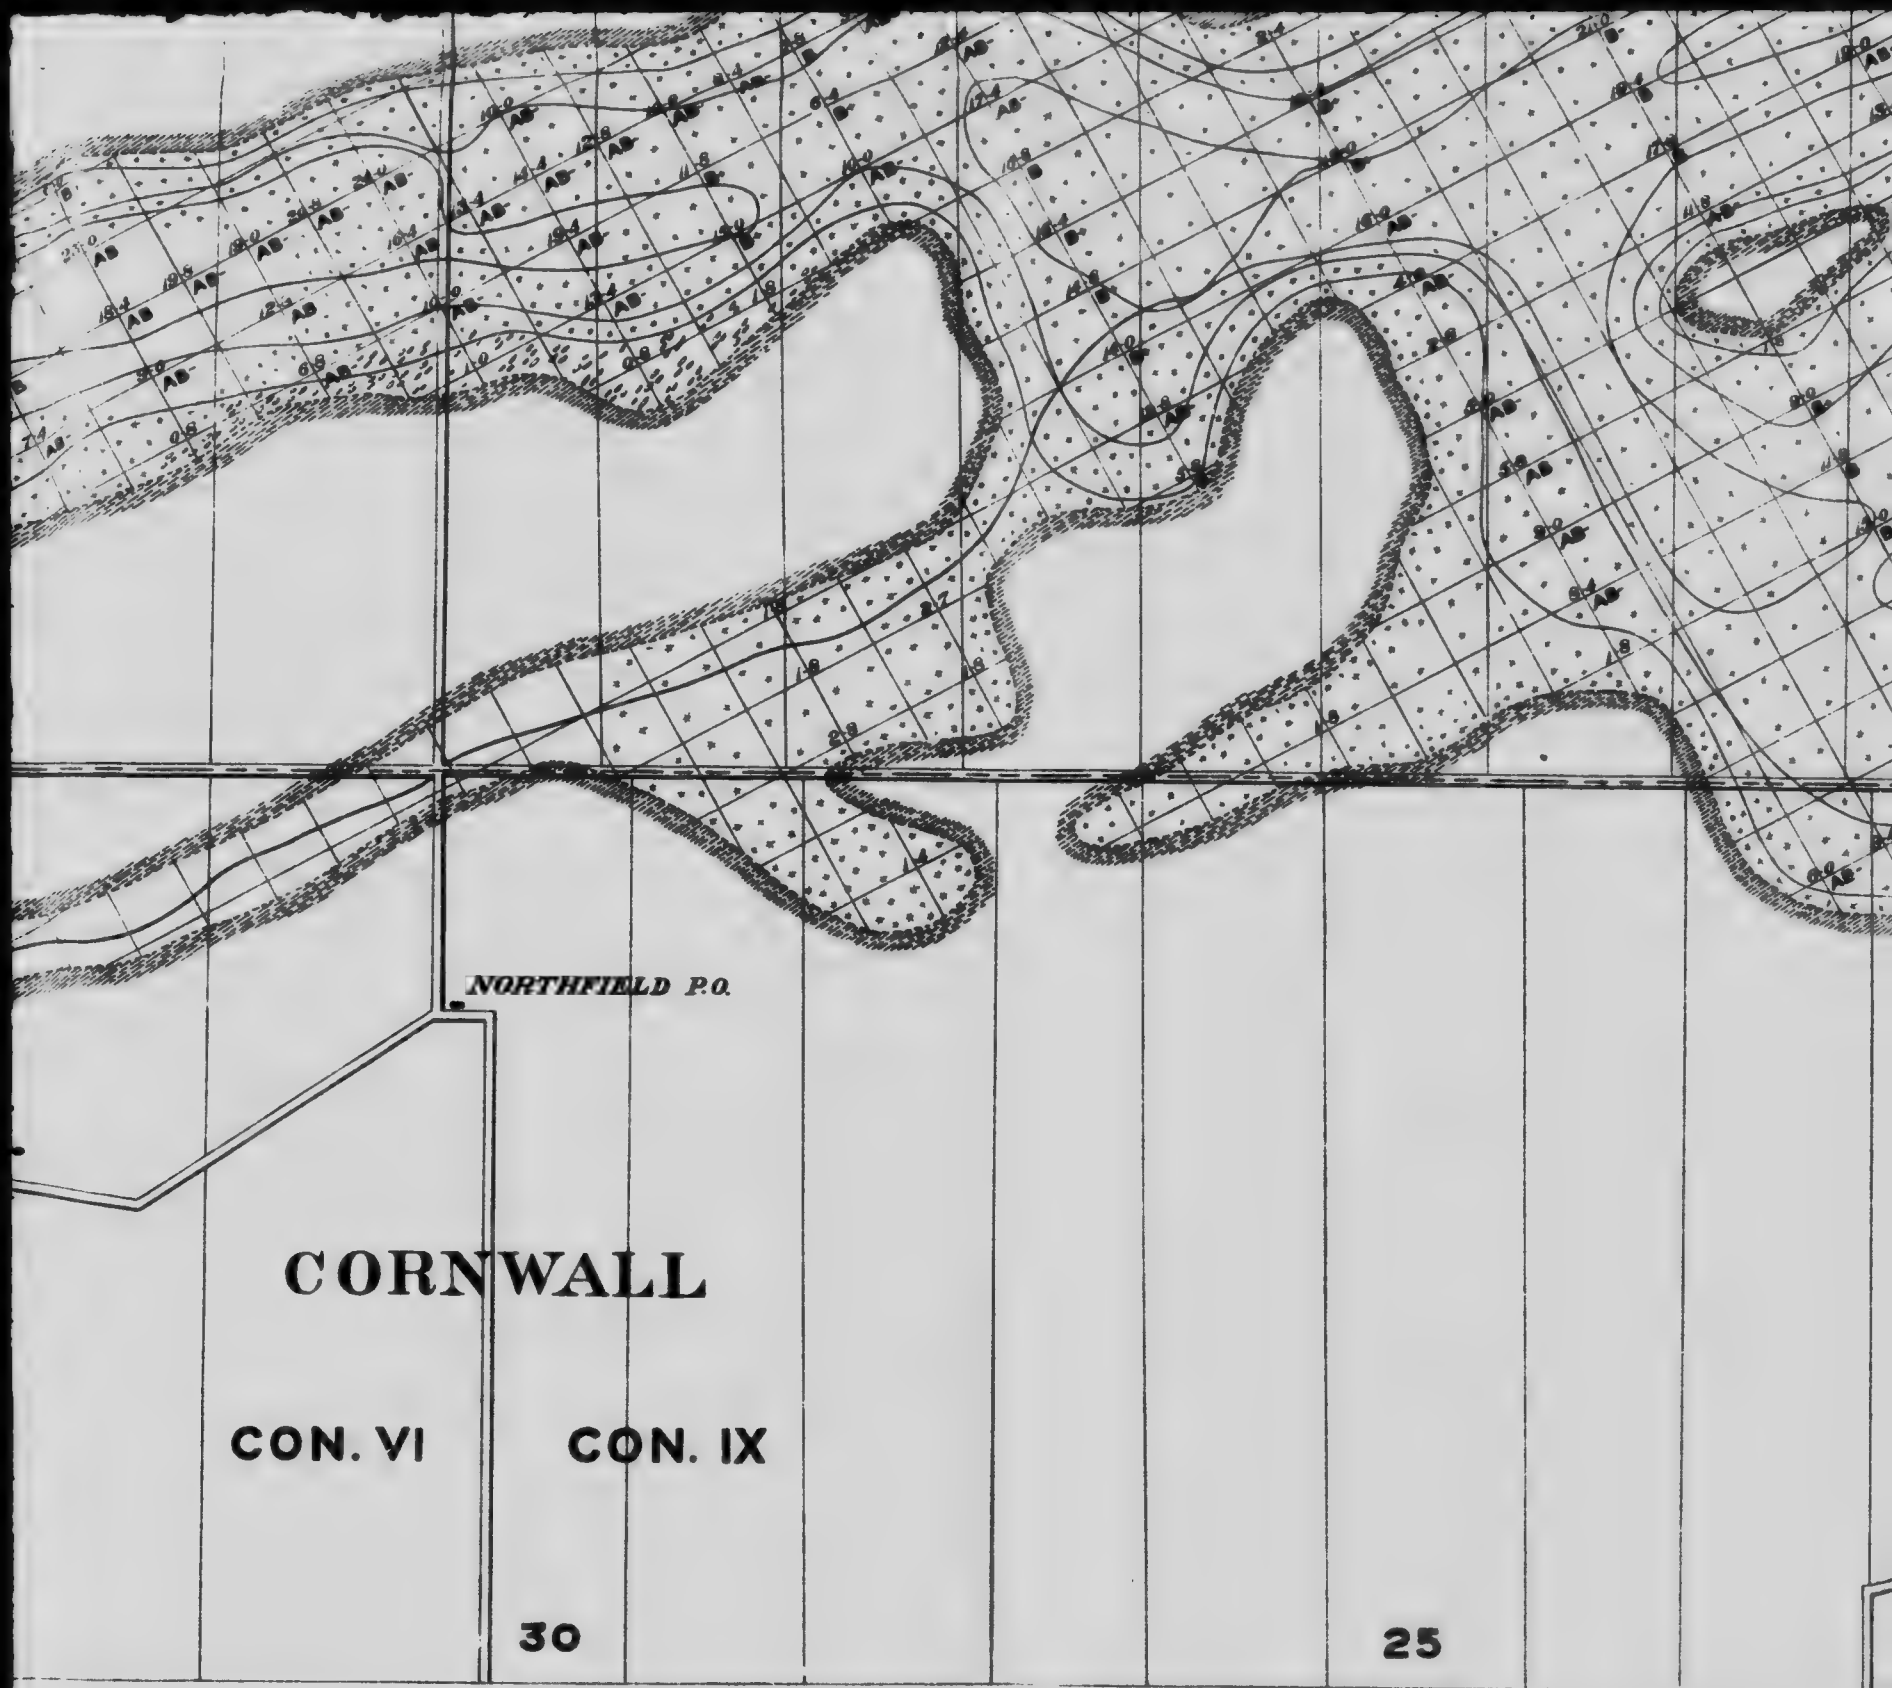

Scale 5 inches = 1 mile

 *Margin of bog.*

 *Heavily wooded areas.*

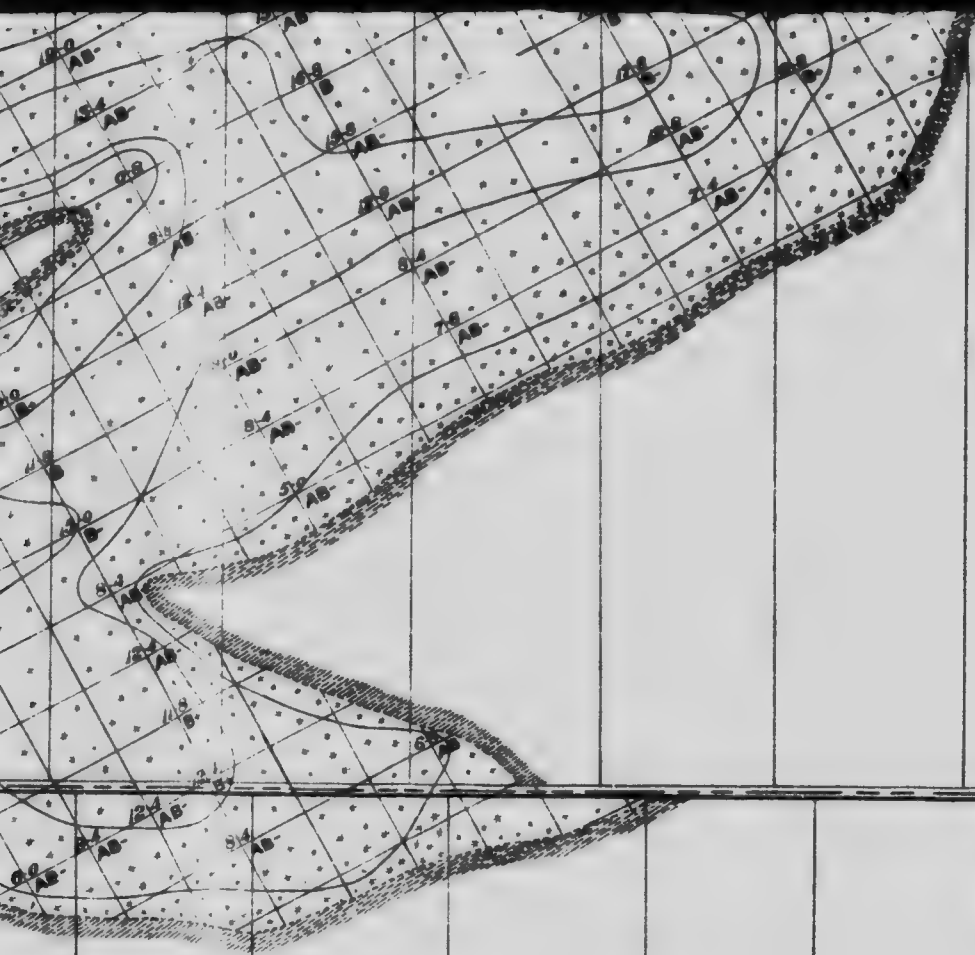

CON. I



20

15

A peat plant was erected at this bog (see map) by the Dominion Peat Products Company, Ltd., of Brantford. A description of the method intended to be used is given in the Bulletin on Peat issued in 1904 by the Geological Survey. The peat was to be cut out of the bog by means of Dolberg cutting machines, and conveyed, by means of a conveyor, to the plant, where it was put through a Dolberg peat machine. The peat bricks were then loaded on iron trucks, which were made to fit a tunnel furnace, where the drying was to be accomplished. In order to dry the peat, hot air was forced through the furnace by means of a fan. The impossibility of such a method is evident from the calculation given on page 24. The process was claimed to be in successful operation in Europe, but although processes of this kind have been tried, none have proved successful.

For several years the plant has been closed down.

PERTH PEAT BOG.

This bog is situated in the township of Drummond, about a mile and a half north of the town of Perth, and covers (see accompanying map) more or less of:—

Lots 1- 5, con. III,	township of Drummond.
Lots 2- 6, con. IV,	" "
Lots 3-11, con. V,	" "
Lots 4-13, con. VI,	" "
Lots 12-13, con. VII,	" "

The total area covered by this bog is approximately 3,800 acres. Of this area

678 acres have a depth of less than 5 feet, average depth 2'-8".

958 acres have a depth of 5 to 10 feet, average depth 8 feet.

2,098 acres have a depth of 10 to 15 feet, average depth 11 feet.

106 acres have a depth of more than 15 feet, average depth 16 feet.

The volume of the peat contained is:—

In the area with a depth of less than 5 feet	3,064,133	cub. yds.
5 to 10 feet deep	12,362,963	" "
10 to 15 feet deep	37,235,000	" "
more than 15 feet deep	2,860,888	" "

The peat is formed by Sphagnum, Hypnum and Eriophorum, in places mixed with the remains of aquatic plants and grasses. The peat in the open part of the bog is principally formed by Sphagnum and Hypnum, only slightly mixed with Eriophorum, but in the wooded parts of the bog the peat is more mixed with the remains of various plants and also with roots and trunks of trees. The surface of the latter parts is covered with a layer of Sphagnum moss, 1 to 2 feet in thickness. Certain parts of the bog, which are more or less drained, are heavily grown over with willow brushes, and in places with hardwood trees. The peat suitable for the manufacture of fuel is comparatively little humified, and the fuel produced will be comparatively light.

Deducting the 678 acres with a depth of less than 5 feet, and allowing for the decrease in depth through drainage, we have left:—

958 acres with an average depth of approximately 6 feet.
 2,098 acres with an average depth of approximately 8 "
 106 acres with an average depth of approximately 12 "
 with a total volume of 38,445,222 cubic yards.

With the assumption that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total tonnage of dry peat substance is 3,844,500 tons of 2,000 lbs., or 5,126,000 tons peat fuel, with 25% moisture.

Analyses of Peat (absolutely dry).

	1	2
Volatile matter.....	70.34	71.51
Fixed carbon.....	25.35	24.60
Ash.....	4.31	3.89
Phosphorus.....	0.030	0.027
Sulphur.....	0.405	0.334
Nitrogen.....	1.66	1.94
Caloric value B.T.U. per lb.....	9067	9148

A peat plant was erected at this bog (see map) by the Lanark County Peat Fuel Company of Perth. The part of the bog in the immediate vicinity of the plant had formerly been used for agricultural purposes and was consequently well drained. The peat had, however, been exposed to frost and its cohesive properties were very poor, and content of ash high.

Analysis of Peat from the Bog in the Vicinity of the Peat Plant.

Volatile matter.....	64.80%
Fixed carbon.....	21.74%
Ash.....	13.46%
Caloric value.....	8319 B.T.U. per lb.

To judge from the work done, hardly any peat fuel has been manufactured and the plant has been closed down for several years.

VICTORIA ROAD PEAT BOG.


This bog is situated in the townships of Bexley and Carden, about one mile from Victoria Road station on the Midland division of the Grand Trunk railway, and covers (see accompanying map) more or less of:—

Lots 3-4, con. I, township of Bexley.

Lots 3-4, con. X, township of Carden.


The total area covered by this bog is only 67 acres. Of this area 36 acres have a depth of less than 5 feet, average depth 2 feet. 15 acres have a depth of 5 to 10 feet, average depth 6'-4"

THE PERTH

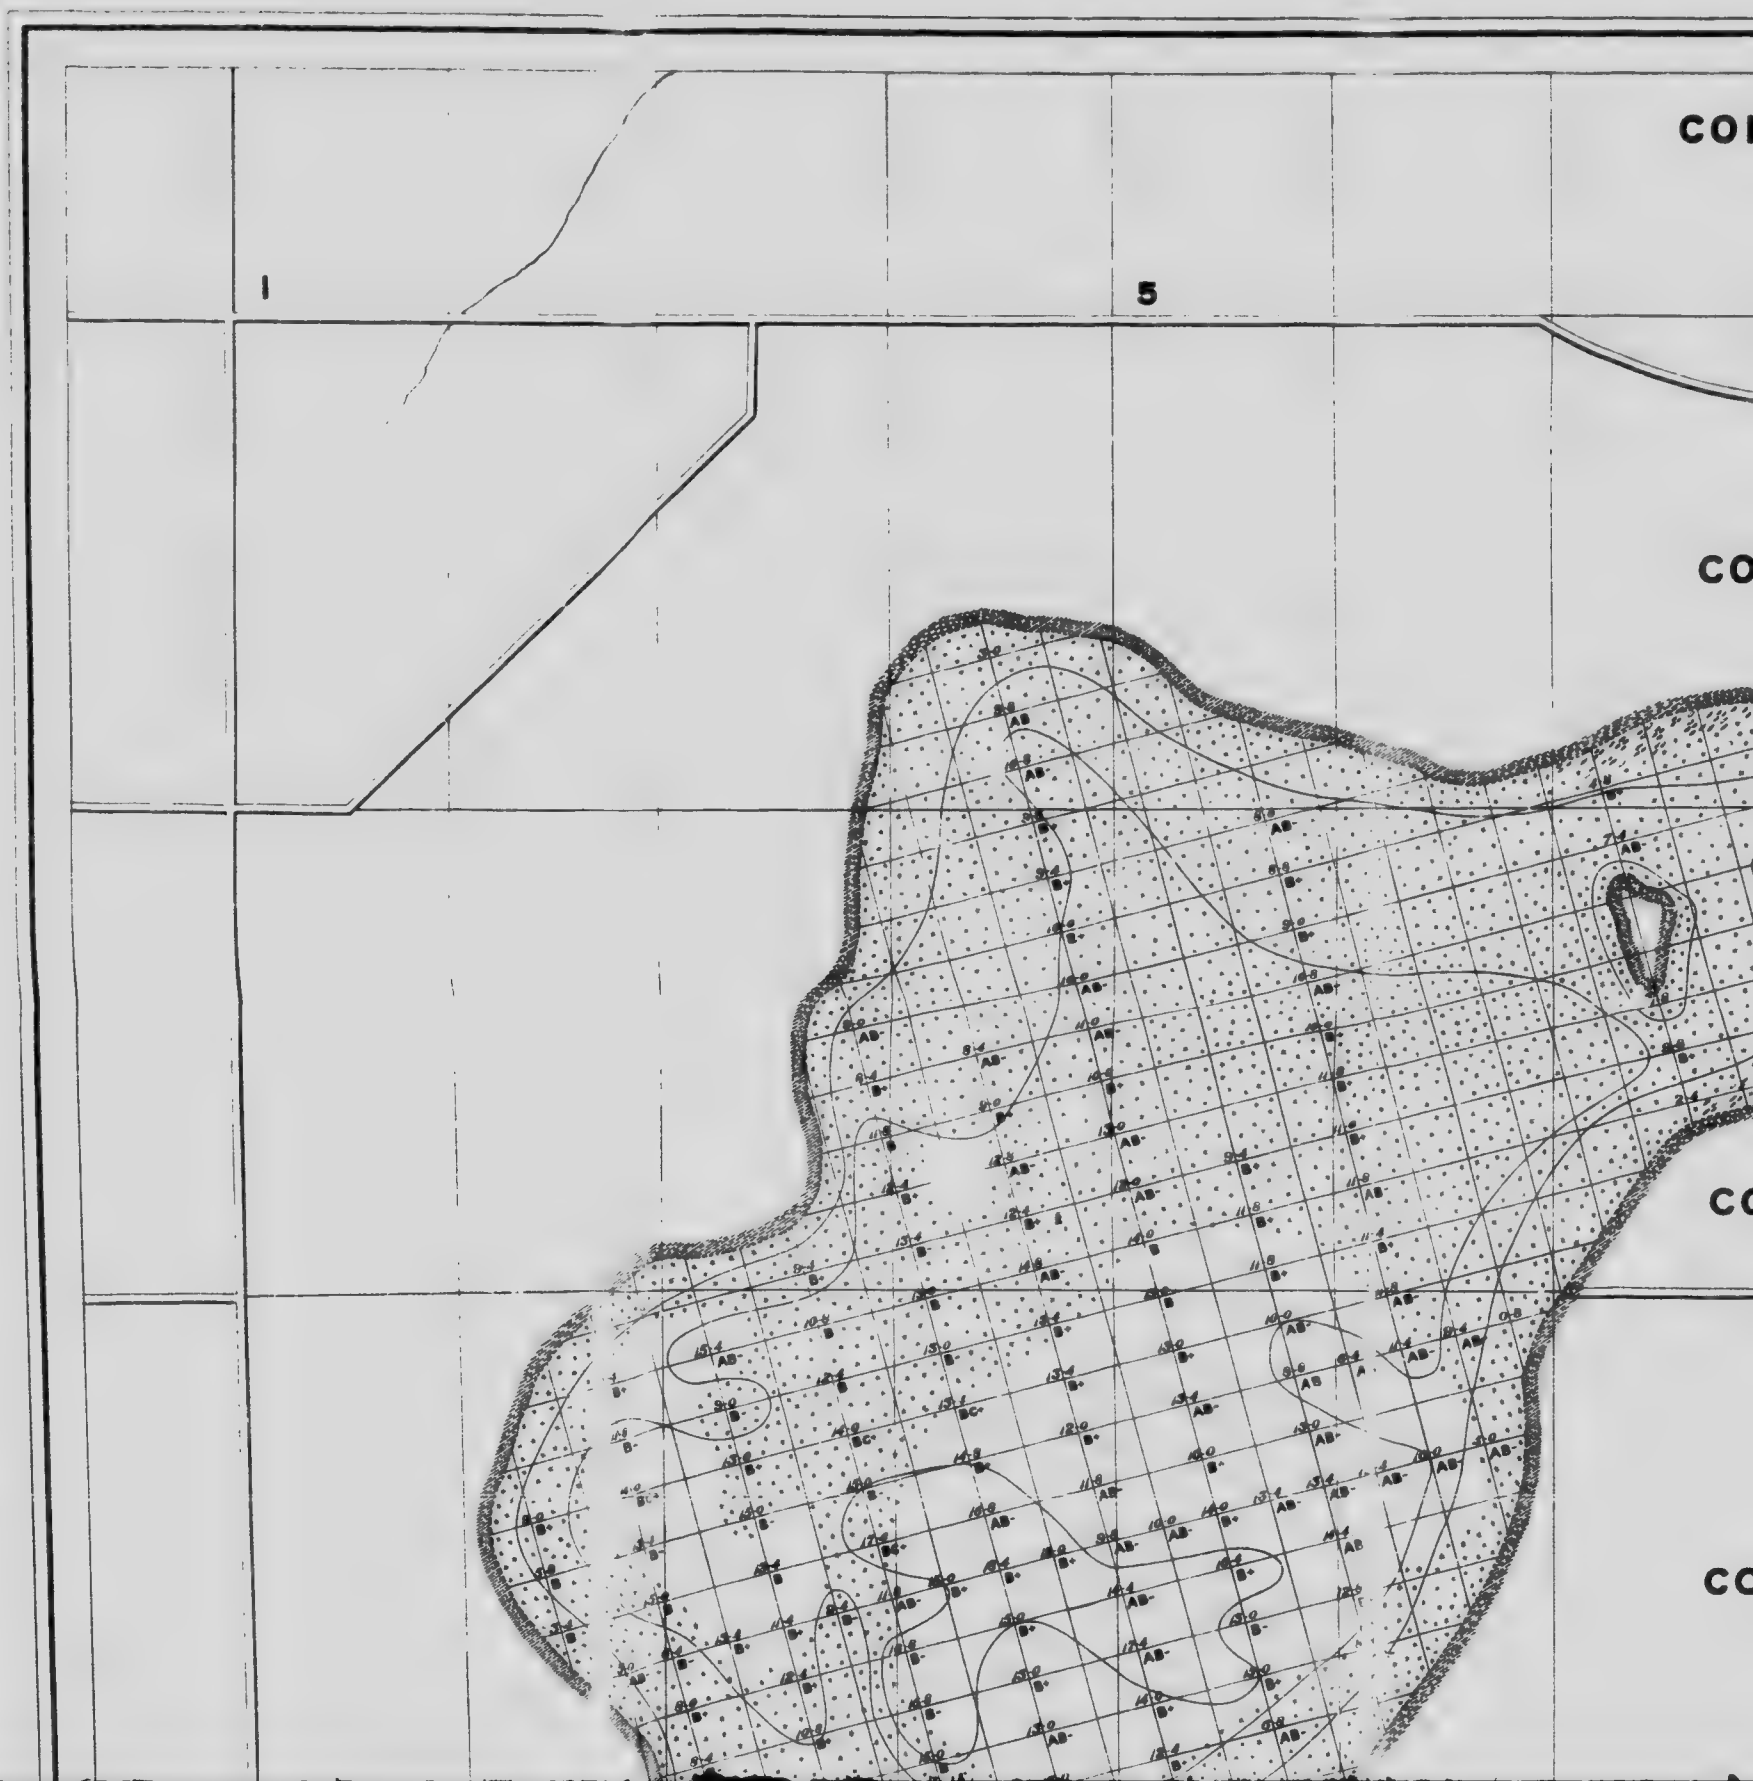

CANADA
DEPARTMENT OF MINES
GEOLOGICAL BRANCH
SIR A. P. LOW, LL.D., DEPUTY MINISTER:
SIR F. D. D. DIRECTOR

PEAT BOG

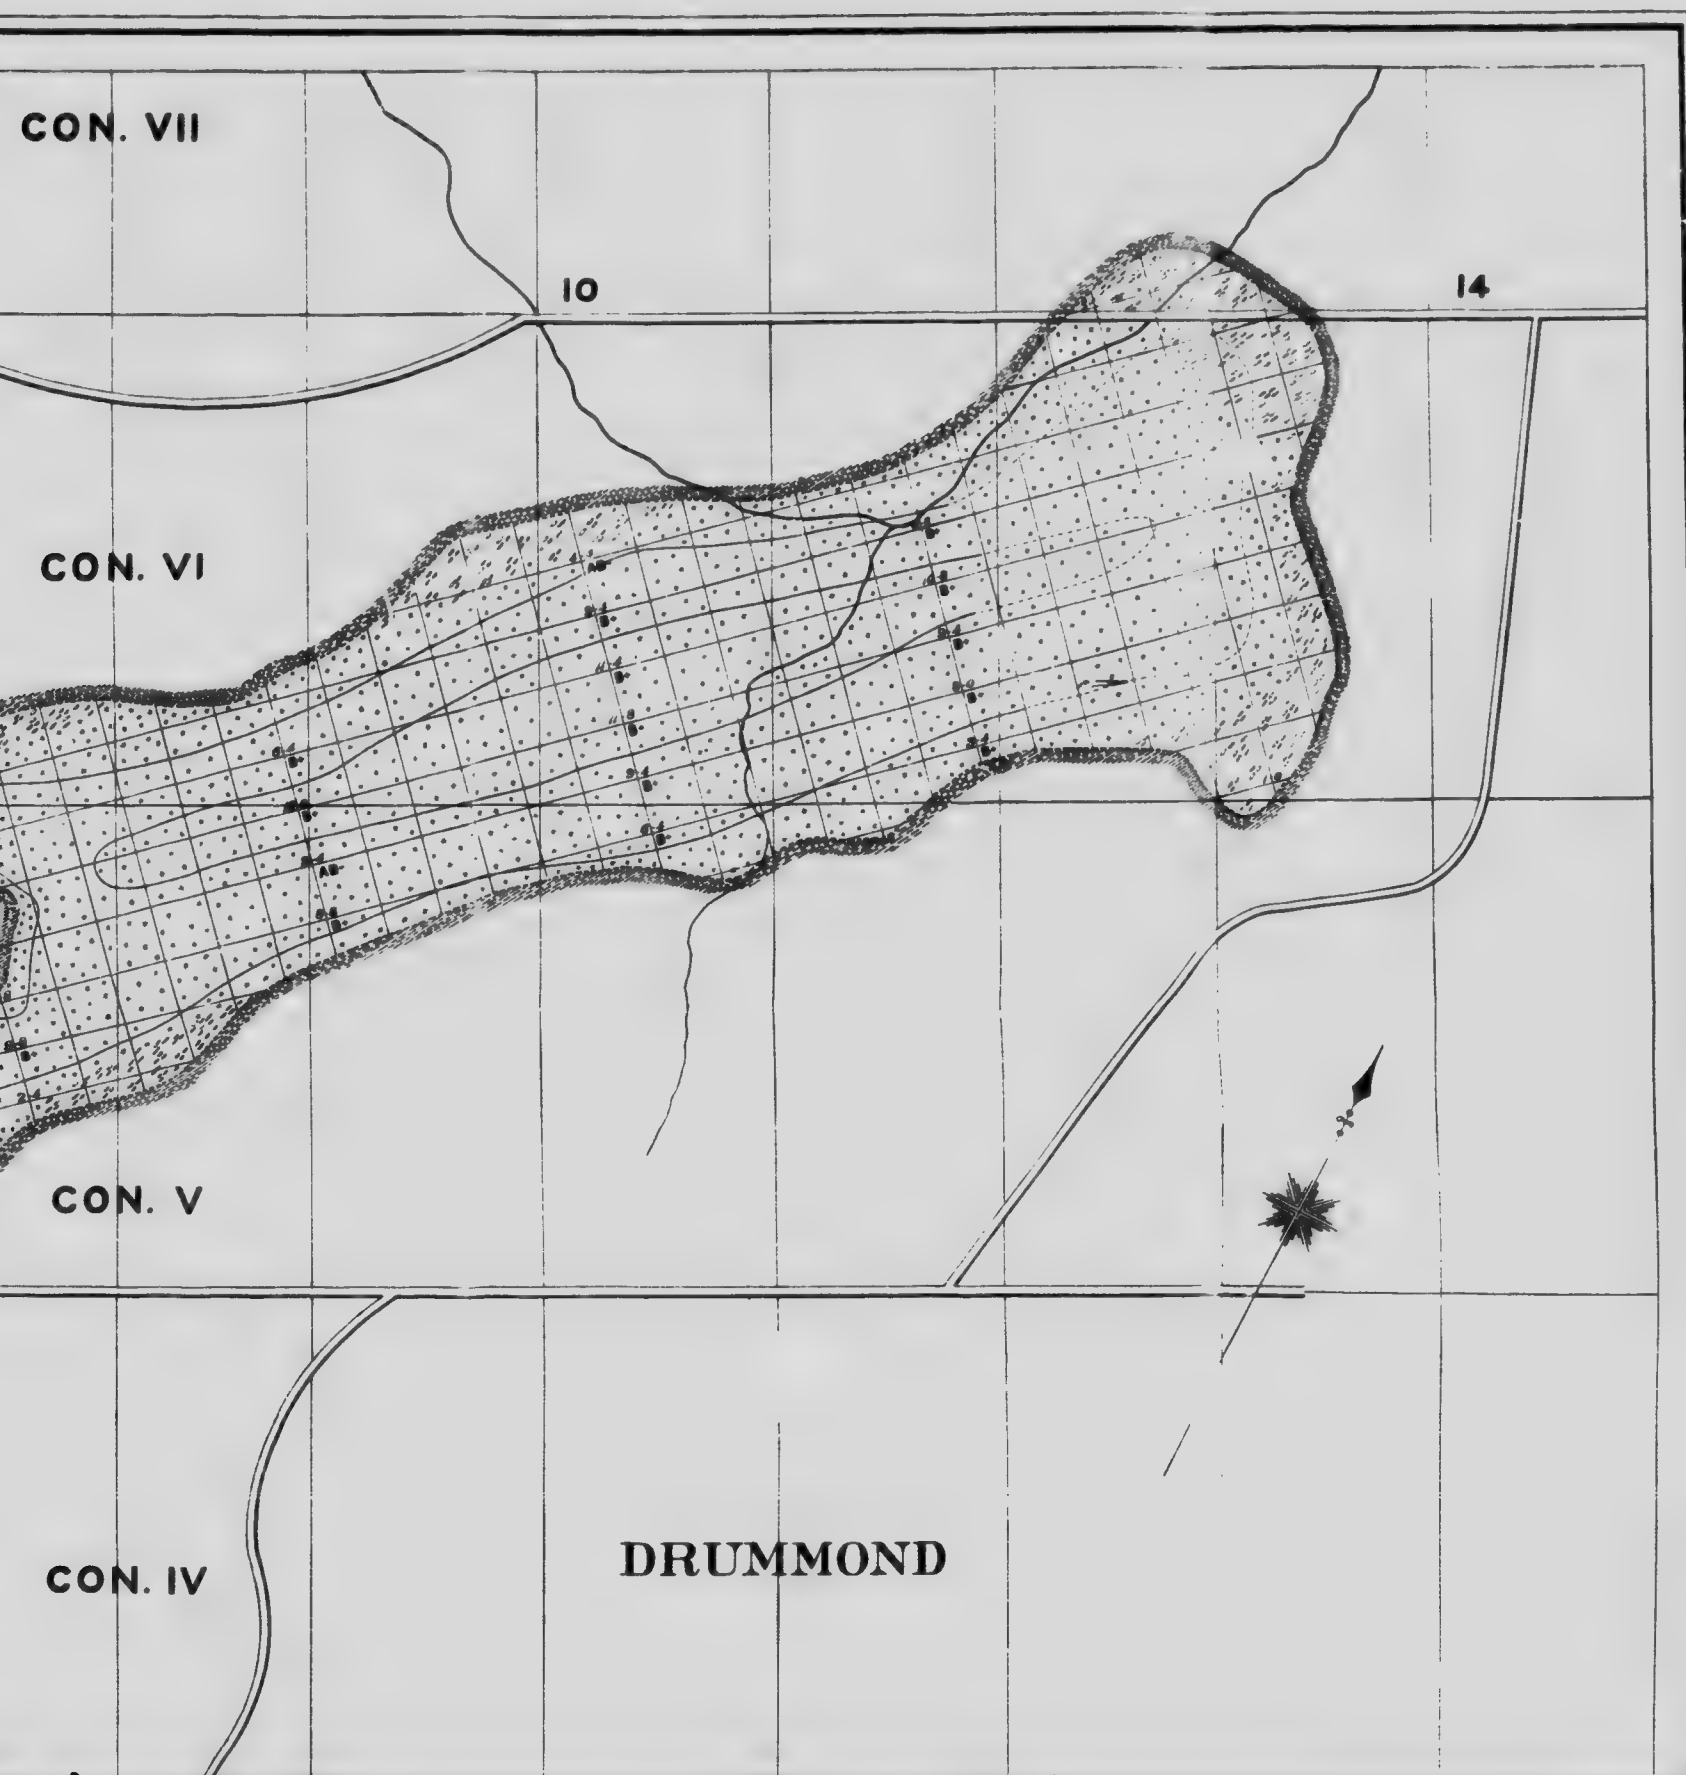




ERIK NYSTRÖM, Mining Engineer.
S. A. ANREP, Peat Expert.

Scale 5 in

 Margi

 Heavily

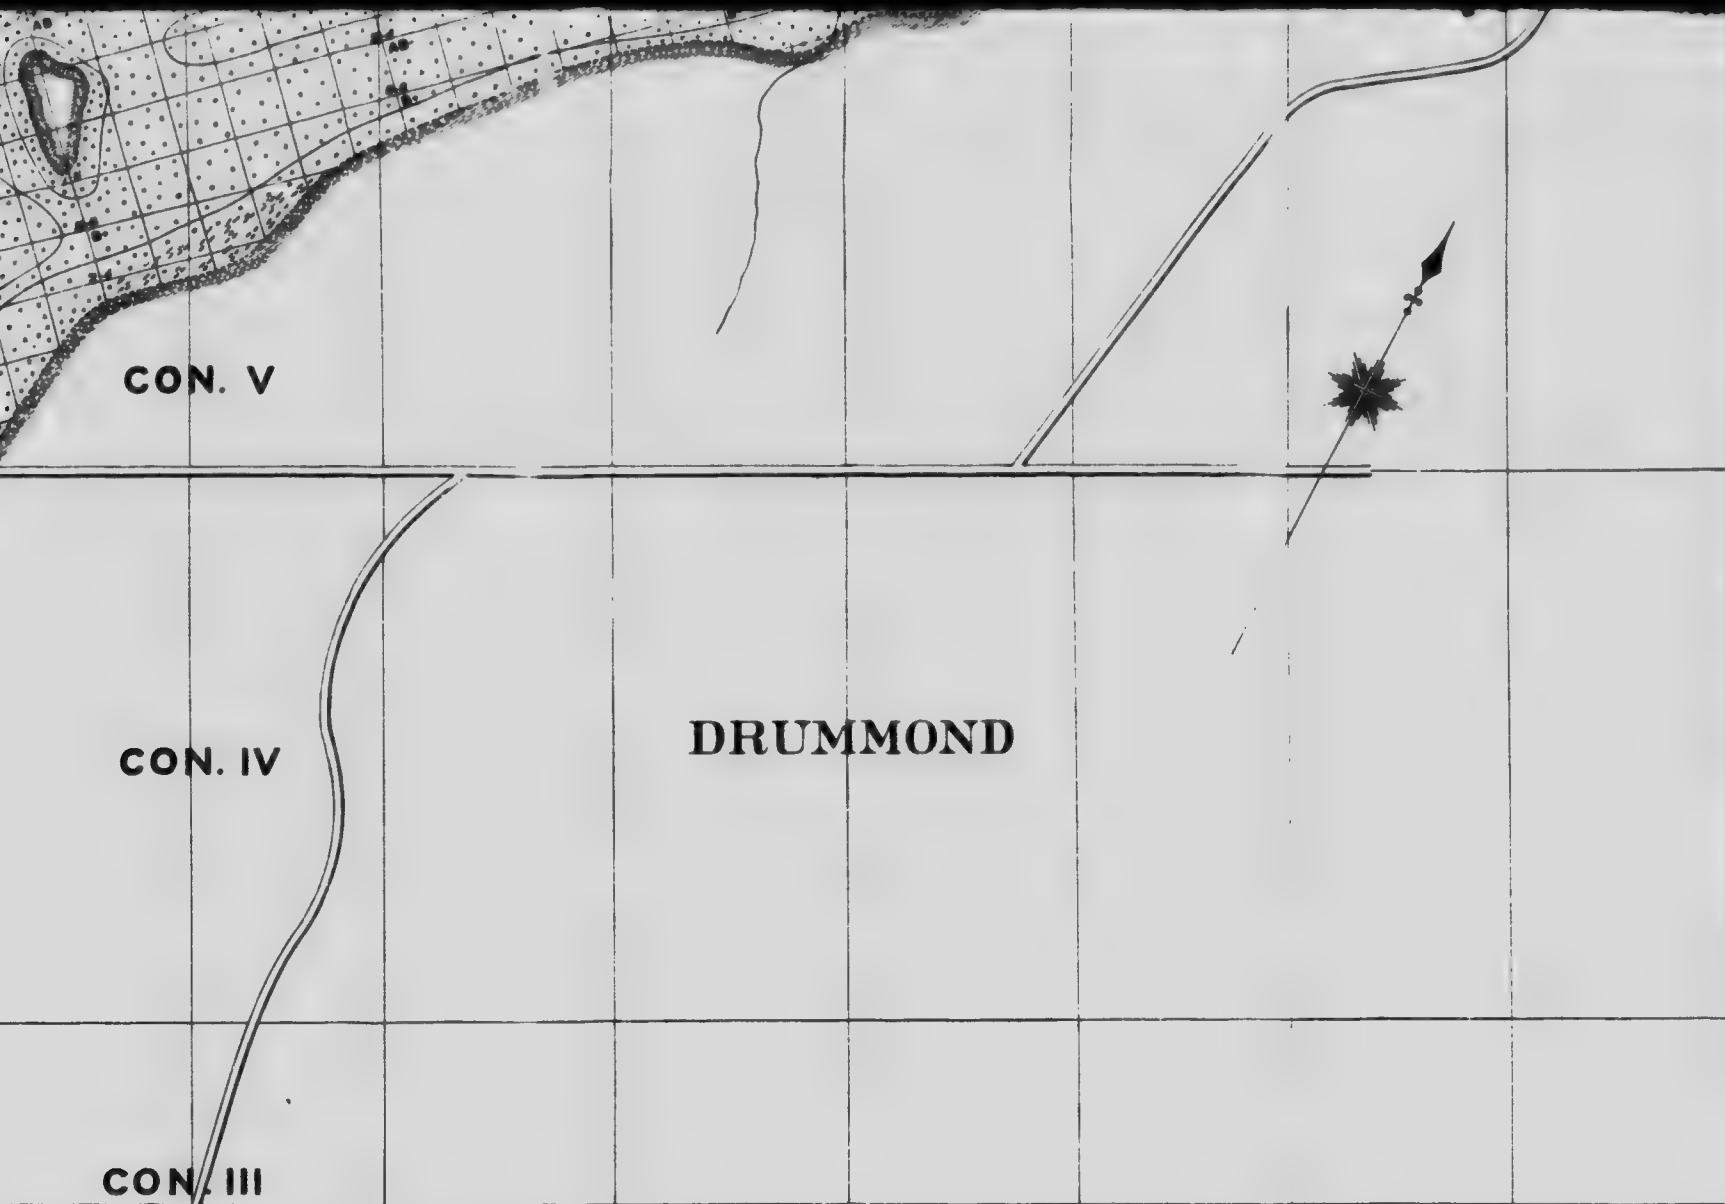

5 inches = 1 mile.

Margin of bog.

heavily wooded areas.

No. 40

12 acres have a depth of 10 to 15 feet, average depth 12 feet.
 3 acres have a depth of 15 to 20 feet, average depth 15 feet.
 1 acre has a depth of more than 20 feet, average depth 23 feet.

The volume of the peat contained is —

In the area with a depth of less than 5 feet . . .	116,481 cubic yds.
5 to 10 feet deep . . .	157,444 " "
10 to 15 feet deep . . .	237,555 " "
15 to 20 feet deep . . .	78,333 " "
more than 20 feet deep . . .	52,896 " "

The peat is principally formed by *Hypnum* mixed with *Sphagnum*, and in places with the remains of aquatic plants and *Carex*.

The peat is well humified and will produce a comparatively heavy fuel, but in the more shallow parts of the bog the cohesive properties are poor and the dried peat has a tendency to crack.

Deducting the 36 acres with a depth of less than five feet, and allowing for the decrease in depth by drainage, we have left:—

15 acres with an average depth of approximately . . . 5 feet.
12 acres with an average depth of approximately . . . 9 " "
3 acres with an average depth of approximately . . . 12 " "
1 acre with an average depth of approximately . . . 19 " "

with a total volume of 402,441 cubic yards.

With the assumption that one cubic yard of such drained bog will furnish 200 lbs. dry peat substance, the total tonnage of dry peat substance is approximately 40,000 tons of 2,000 lbs., or 53,000 tons peat fuel, with 25% moisture.

Analysis of Peat (absolutely dry).

Volatile matter	69.52%
Fixed carbon	25.18%
Ash	5.30%
Calorific value B.T.U. per lb.	8649

A peat plant was erected at this place by Mr. E. V. Moore who carried out some experiments. The details of this plant are described on pages 21-22.

PRESENT STATUS OF THE PEAT INDUSTRY IN CANADA.

During the year 1908 only one small peat plant was in operation, during part of the season, and only a few hundred tons of peat fuel were obtainable for local consumers. This deplorable fact is, undoubtedly, due to the failures of the peat companies formerly started, to lack of knowledge of the properties of peat, and to the employment of impracticable methods, or unsuitable bogs.

In most cases the companies that have erected plants and really intended to manufacture fuel or other peat products, have never produced any quantities of fuel worth mentioning. Their principal object has been to produce a

towards the outside end, picked up into the trough just mentioned, and by the same chain on its return journey taken into the machine and delivered into $1\frac{1}{2}$ cubic yard tram cars, two of which are always on its platform. These are removed as filled, and empty ones put in place by a transfer car running on the same track as the excavator, and which travels between the machine and a track leading to the mill.

Mounted on this arm, also on the back of it, when the machine is in motion, is a second chain, carrying harrow teeth, which tear the surface and leave it ready for air-drying.

The area is laid out in such a way that when the machine has travelled its length the peat at the place of starting is again ready for collection, and return trips are always accomplished with the excavating arm lifted clear of the bog. The first trip of the machine simply harrows the surface. On the next trip the excavating arm is lowered a little and collecting begins, and during this second trip a little bank is formed at the outside end of the arm, which facilitates picking up the peat into the return trough. For the third trip the outer end is kept at the same height as in the second, while the inside end only is lowered, and so on for several trips, until the whole area slopes towards the inside sufficiently for the heavy rain to run off quickly. As soon as the inside end is sufficiently low, both ends are lowered about $1\frac{1}{2}$ inches each time until the inside end reaches the bottom, when the outside end is lowered little by little until it too reaches the same level.

The track for this machine is laid on the bottom of the bog, which consequently necessitates a level bottom and thorough drainage. The power required is furnished by a small gasoline engine, mounted on the same truck as the excavator.


The partly air-dried peat is brought to the stationary mill, which is located close to the bog and also close to the drying ground.

The mill is provided with boiler and steam engine, which furnishes the power used for driving the pulping machine, conveyers, and other miscellaneous machinery, such as hoist, pump, saw, etc.

The loaded cars are brought up a trestle by means of a cable and hoist and automatically dumped into a large bin. In the bottom of this bin is a conveyer, which conveys the peat to the pulping machine. After passing through this machine, the peat is taken up on pallets, which are specially made to fit the cars which constitute the conveyer employed for bringing it to the drying ground.

The conveyer is a miniature cable car with four wheels, each car designed to handle one pallet, and caused to travel around a system of tracks so that peat is automatically picked up at the mill and conveyed to the particular part of the drying area where charging and discharging is going on. The motion is provided by means of a cable, on which are bolted transmission knobs, which serve the double purpose of giving the cable motion and of engaging the little cars at proper intervals. Tracks for this conveyer are put down in each aisle between drying sections. A return track, at one side


PEAT PLANT

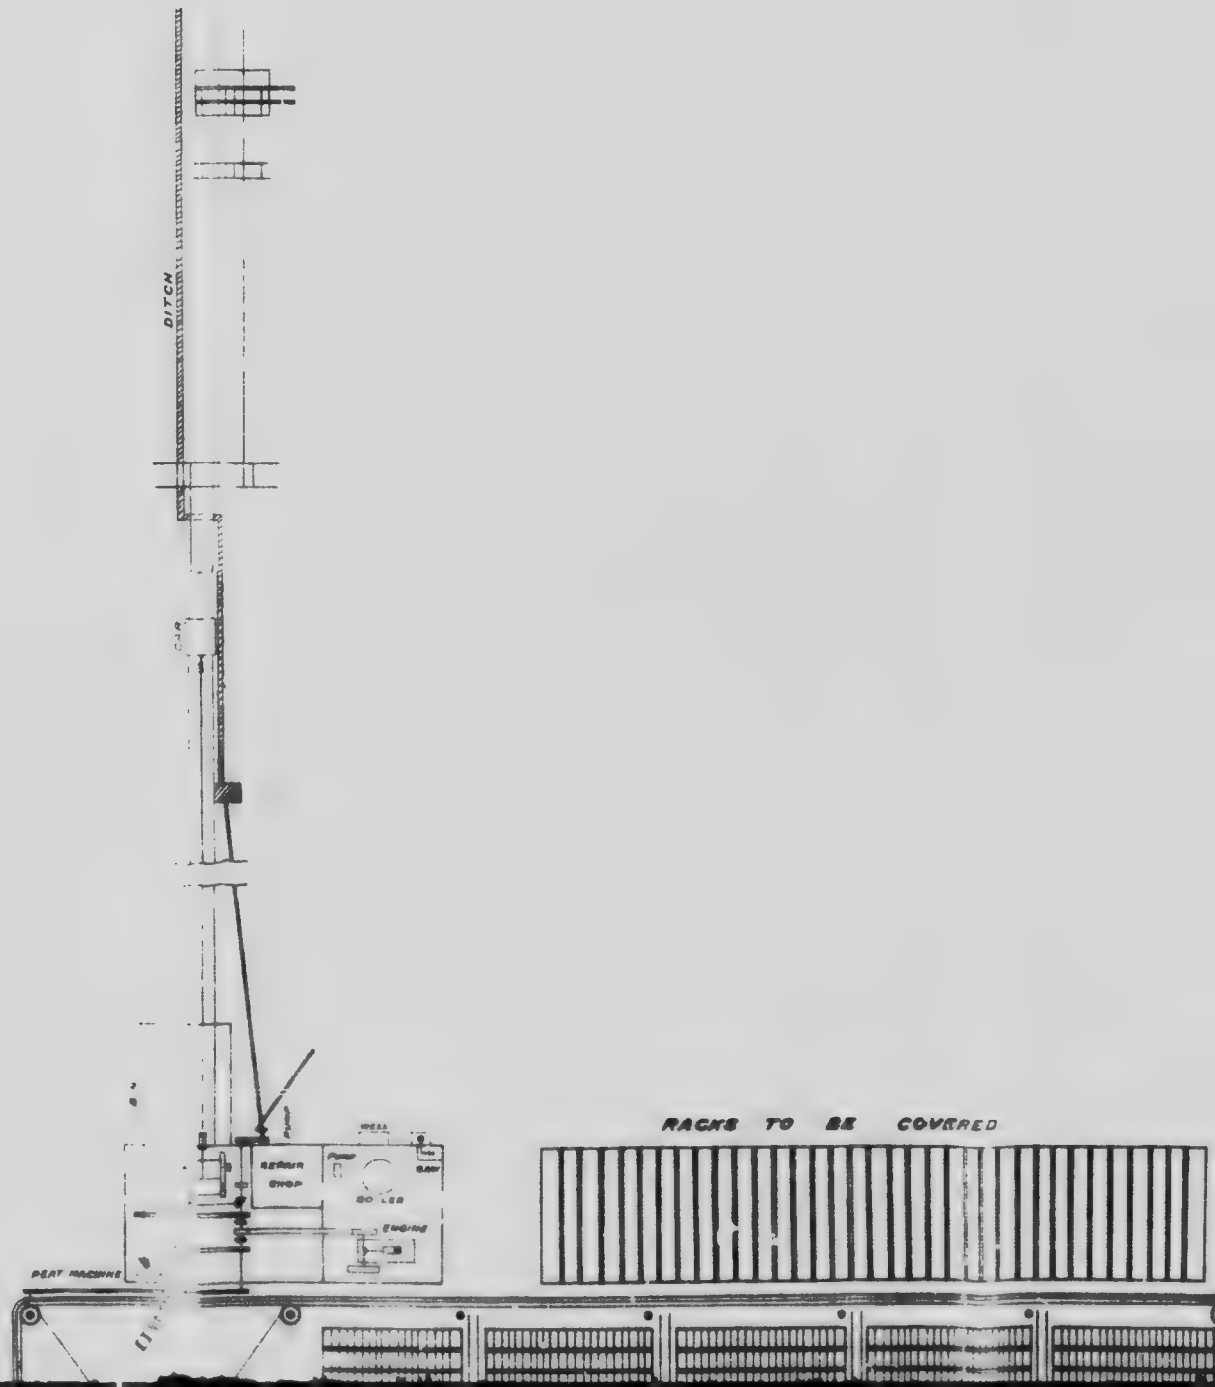

CANADA
DEPARTMENT OF MINES
MINE BRANCH

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAANEL, Ph.D., DIRECTOR.

VICTORIA ROAD

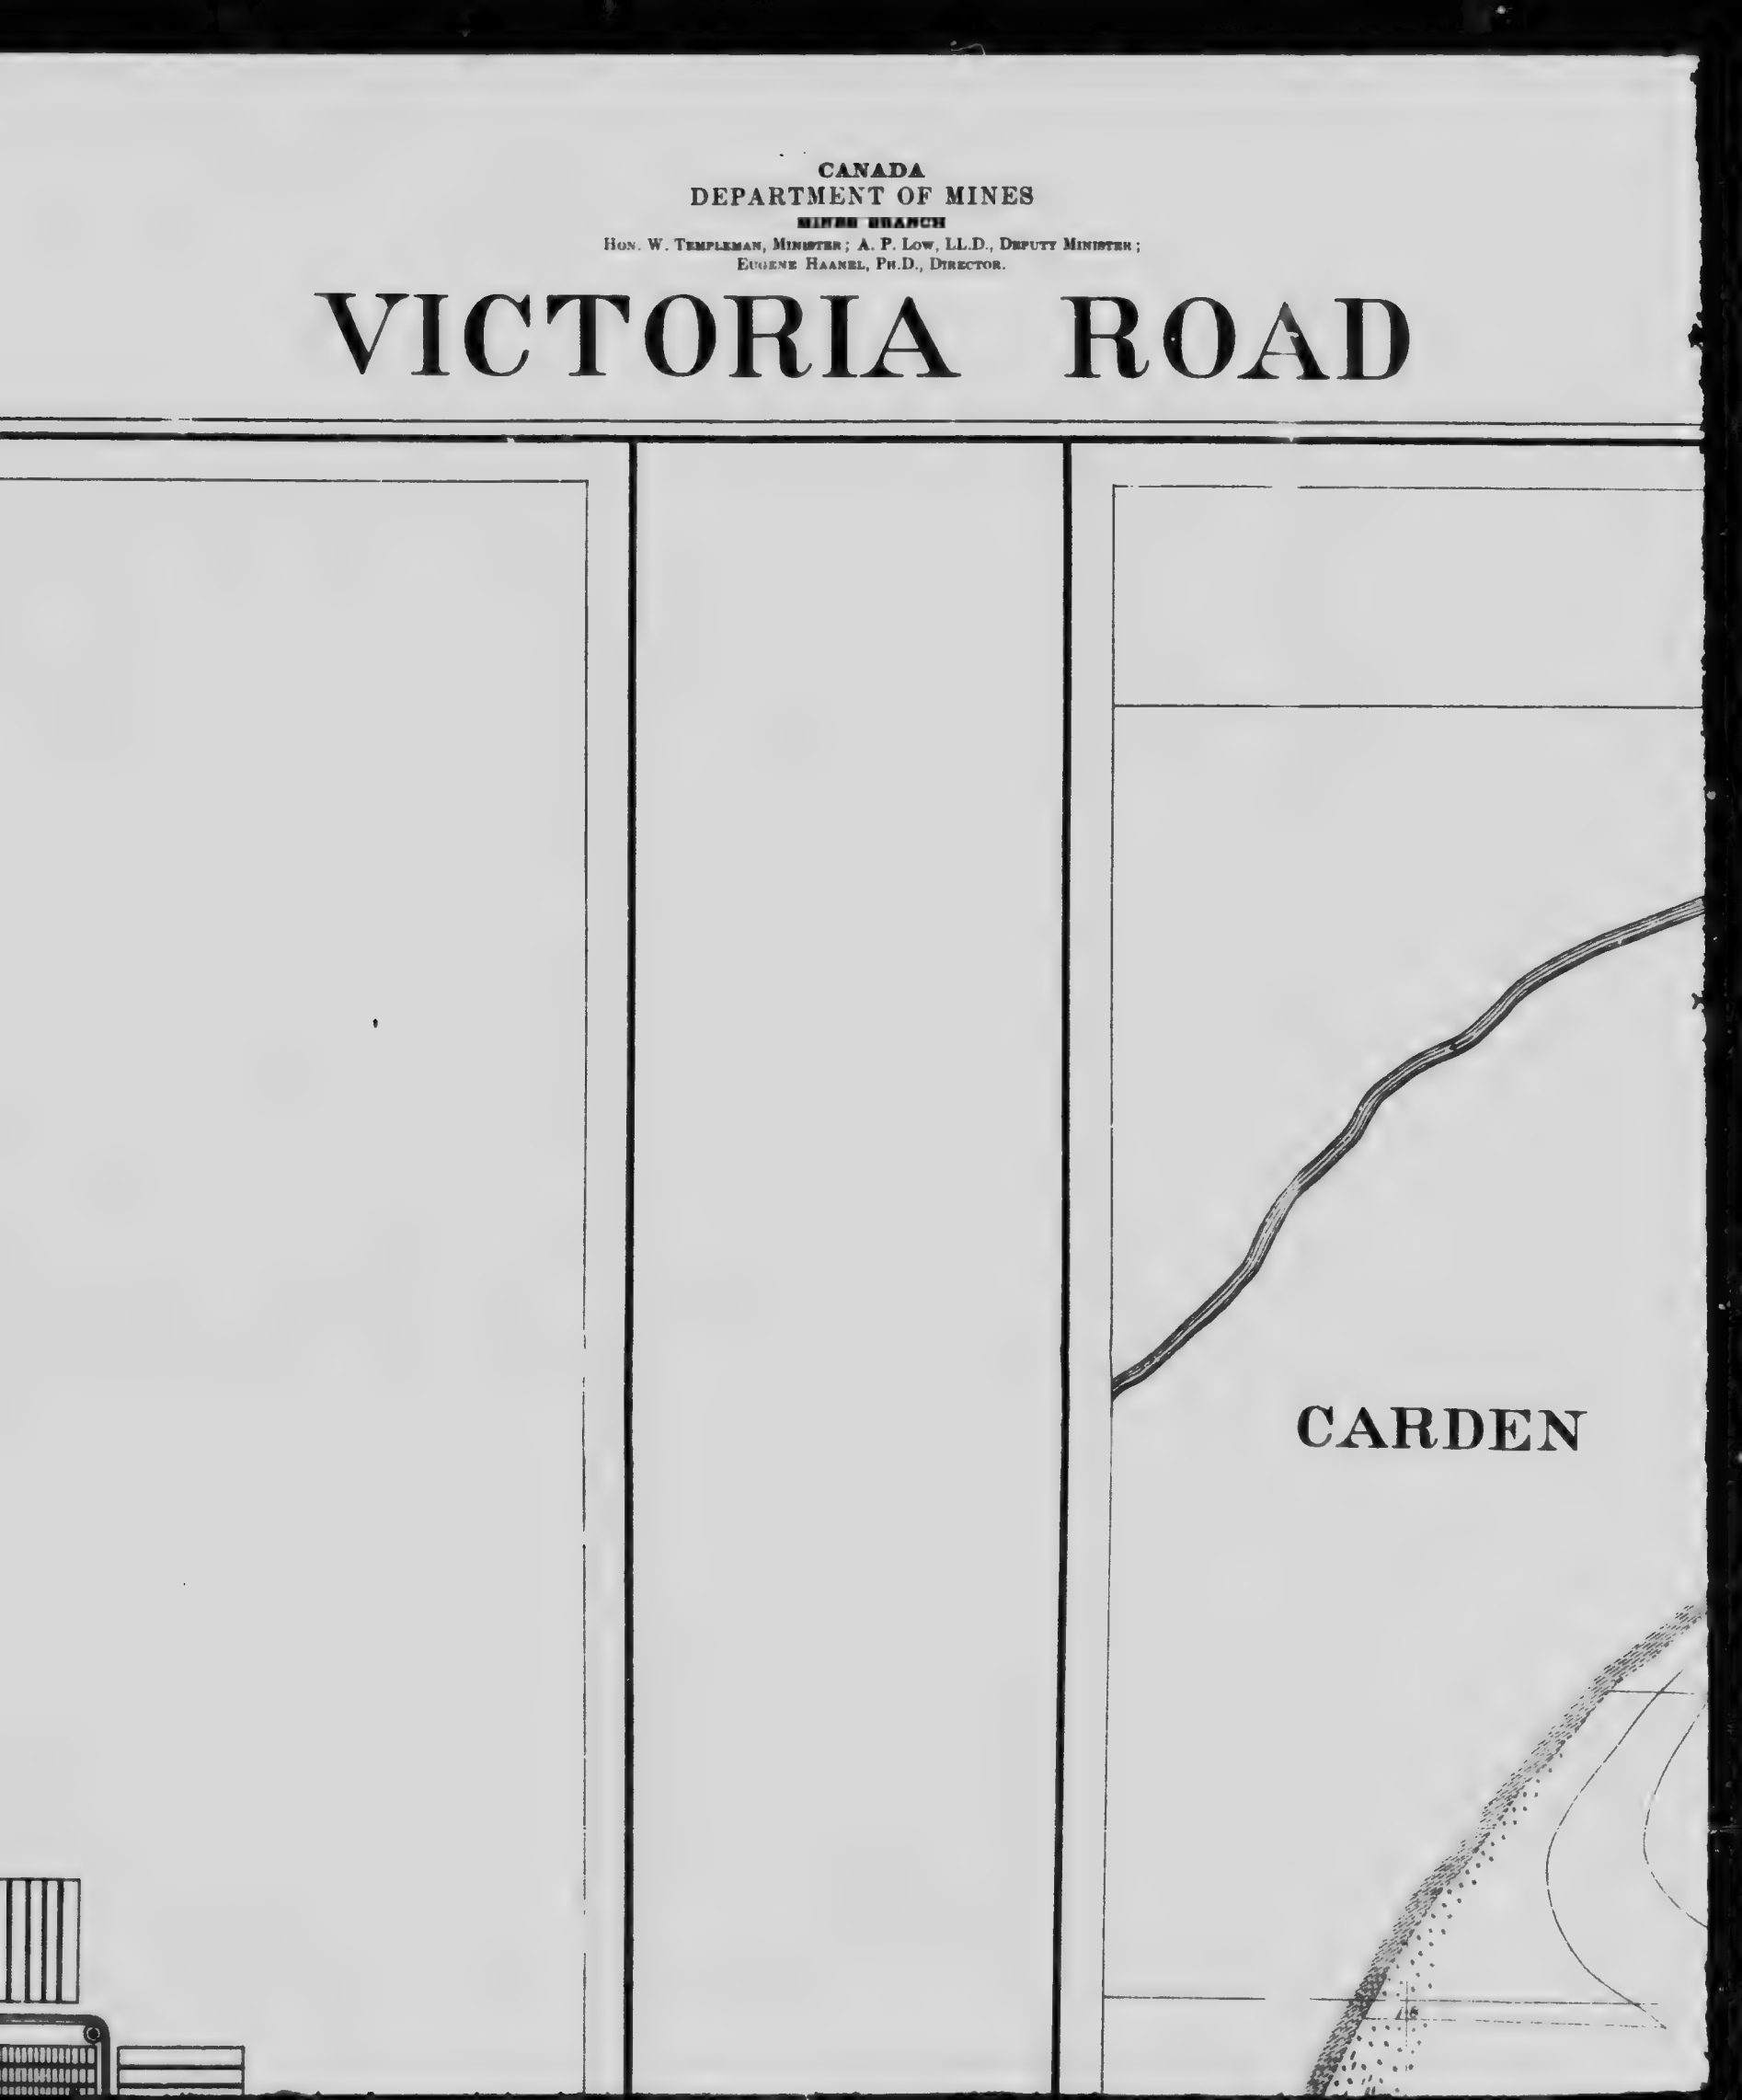

CARDEN

CANADA
DEPARTMENT OF MINES
MINES BRANCH

HON. W. TEMPLEMAN, MINISTER; A. P. LOW, LL.D., DEPUTY MINISTER;
EUGENE HAANEL, Ph.D., DIRECTOR.


VICTORIA ROAD




CARDEN





PEAT BOG

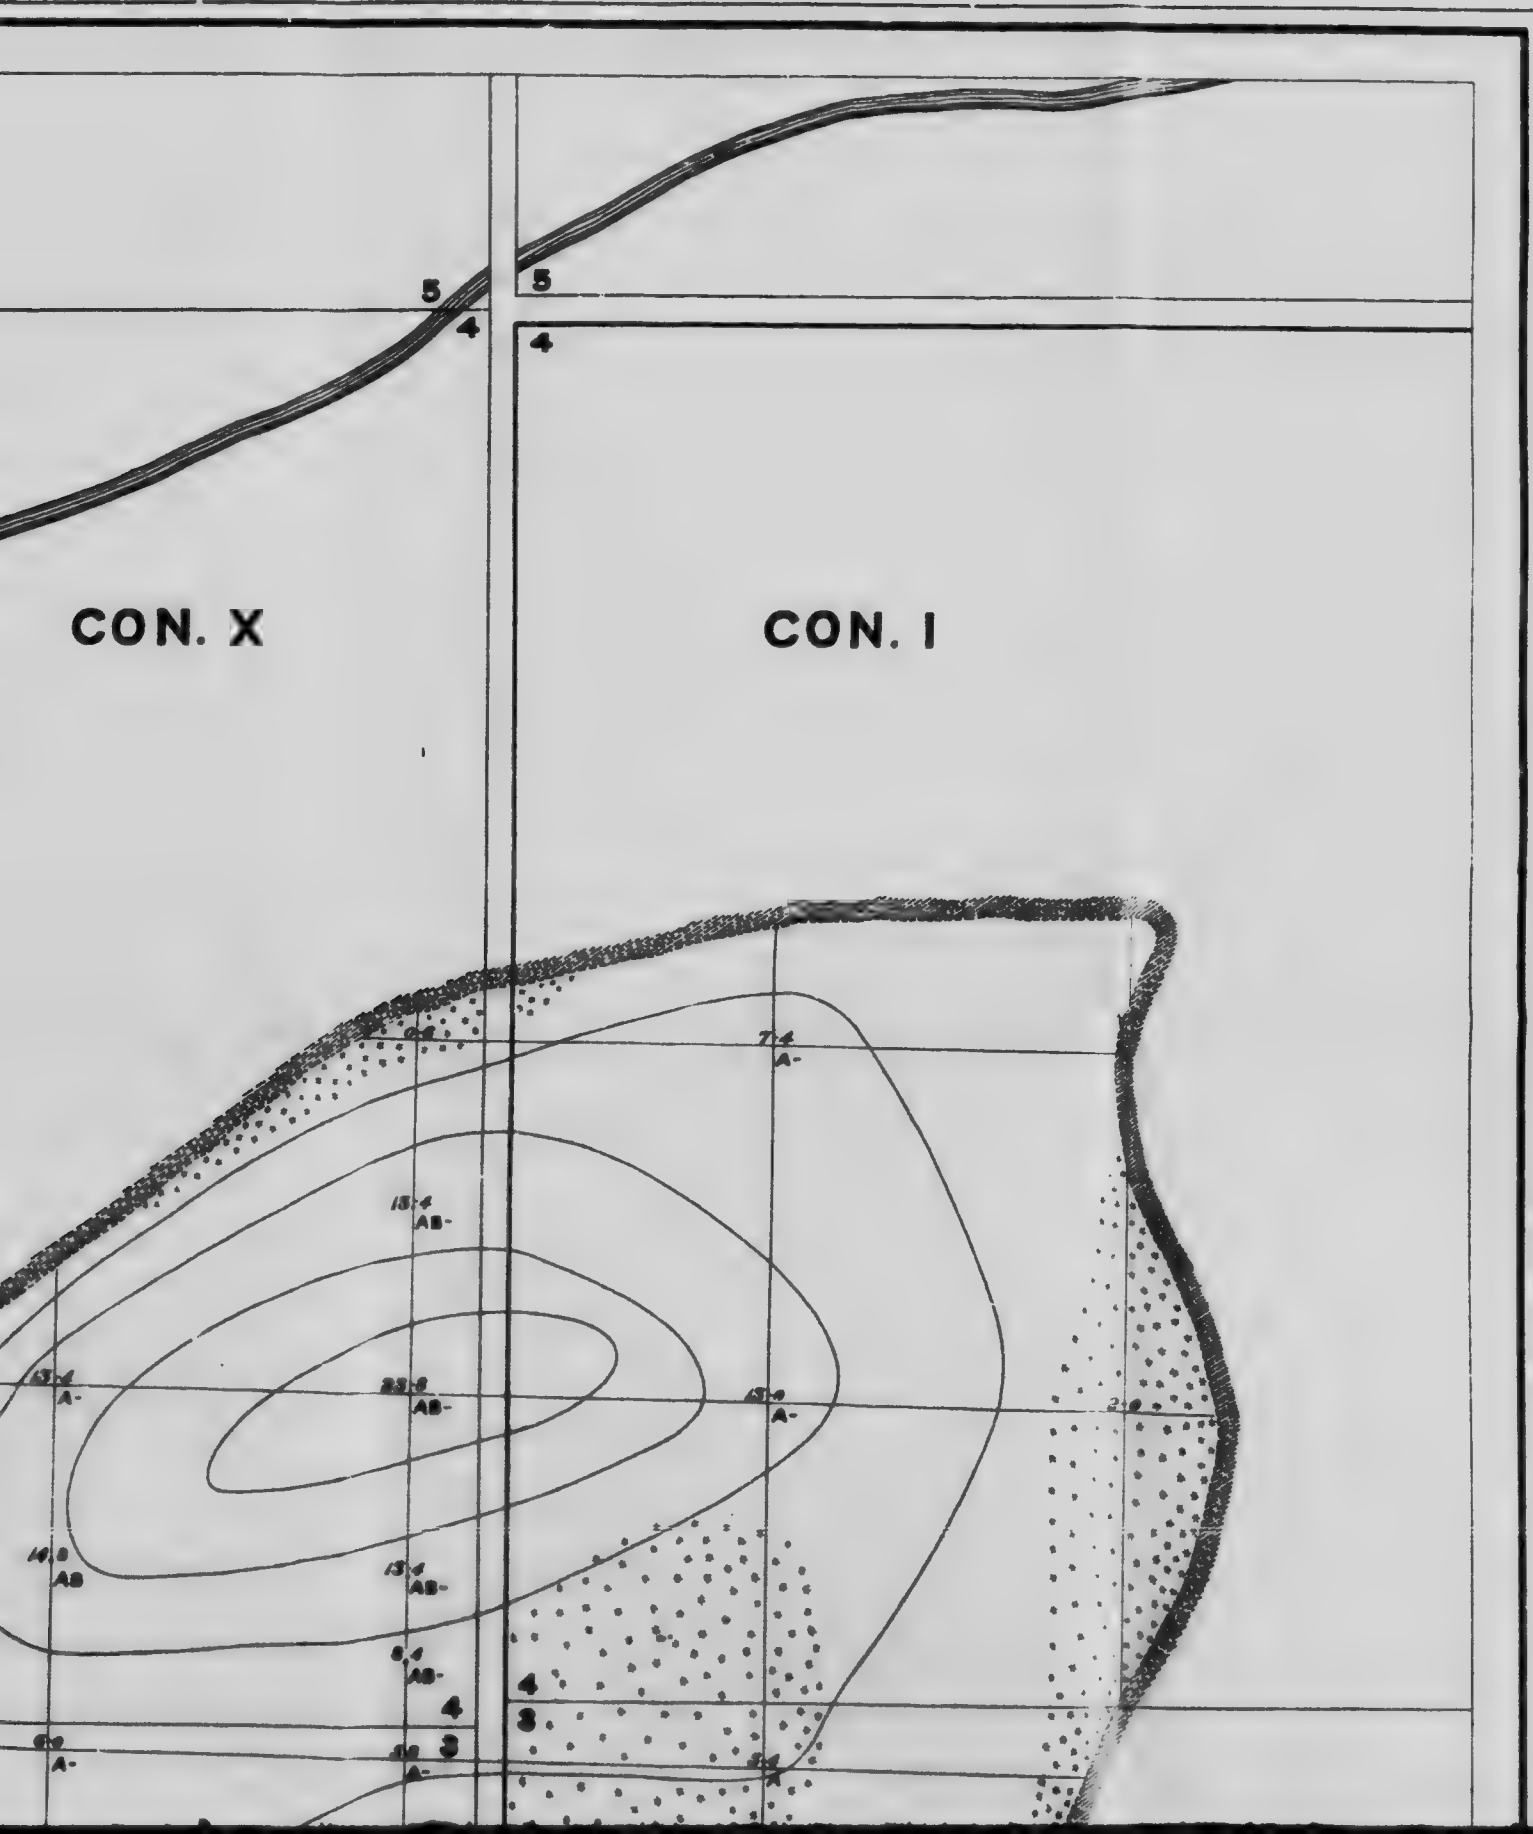

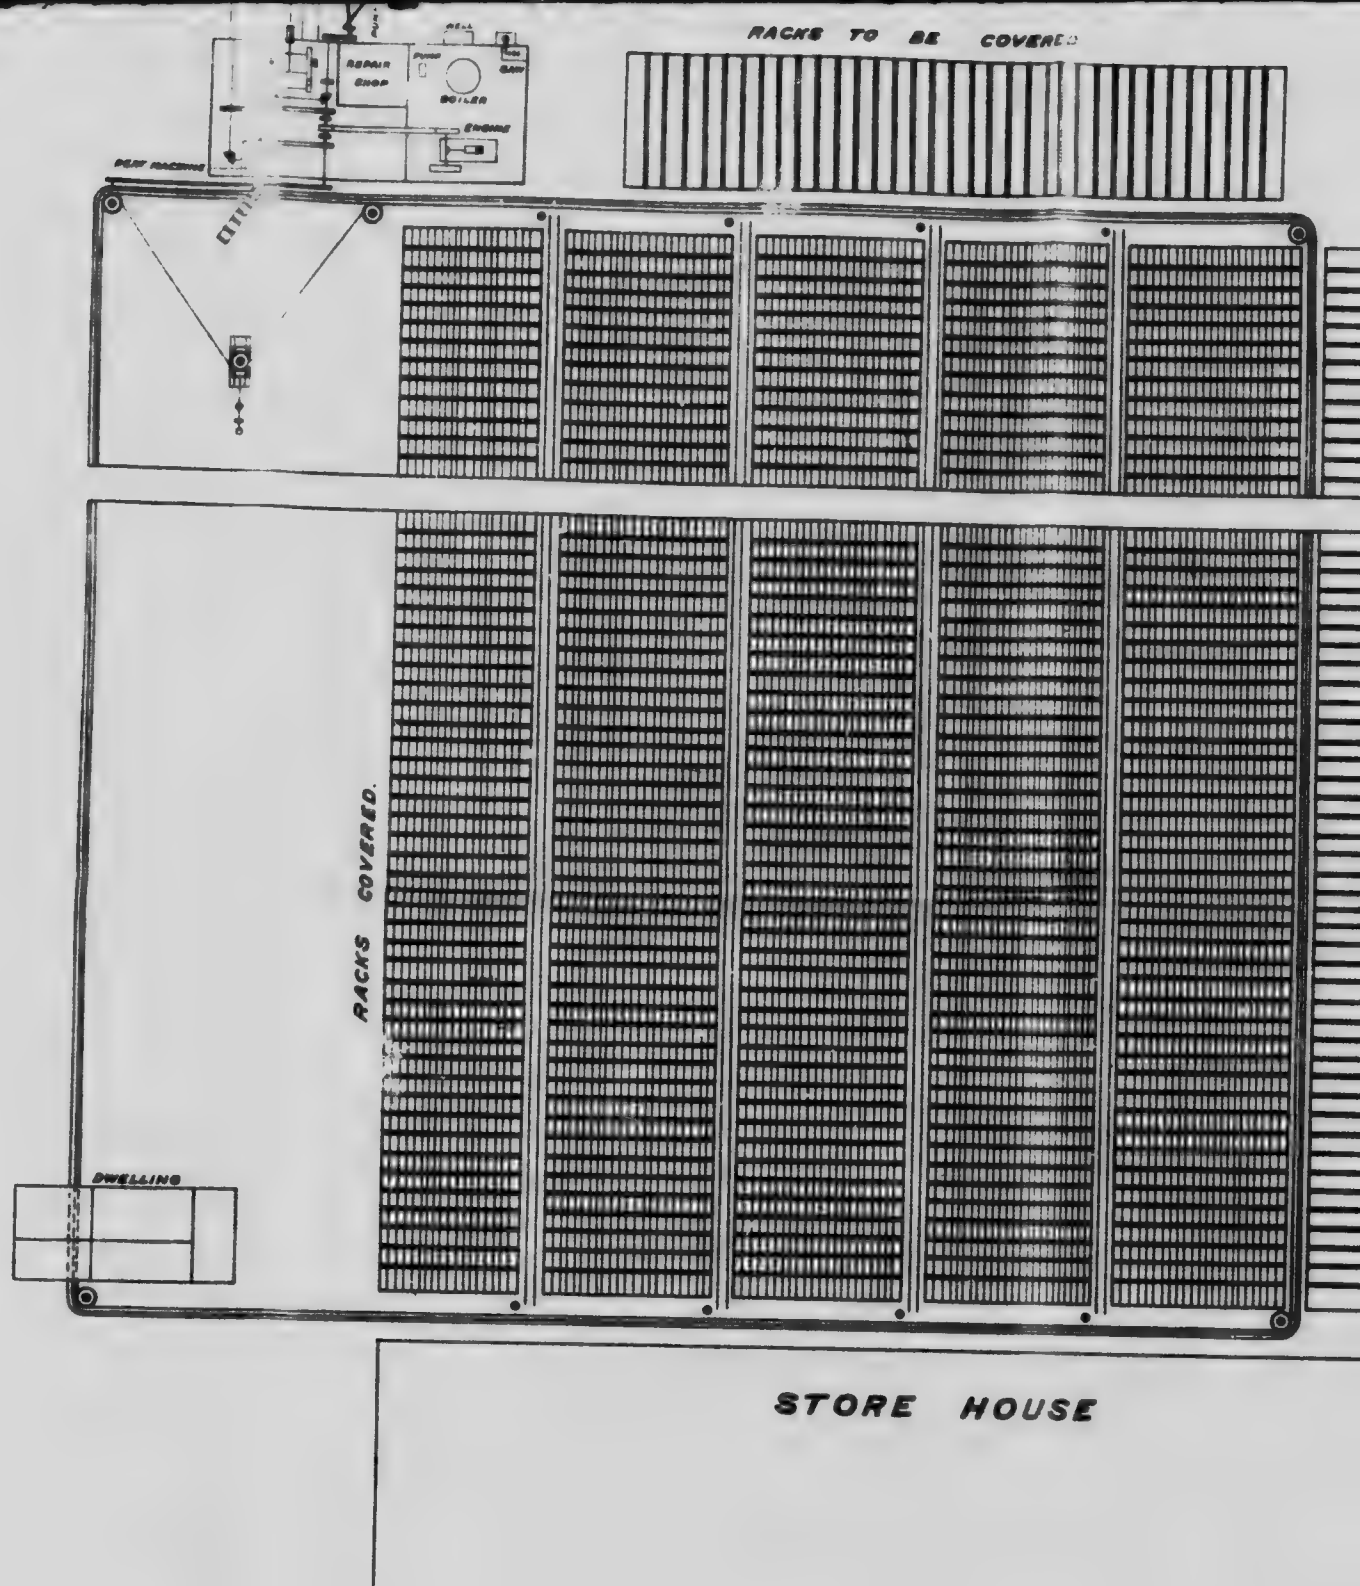


ERIK NYSTROM, Mining Engineer.
S. A. ANREP, Post Expert.

Scale, 20 feet = 1 inch.

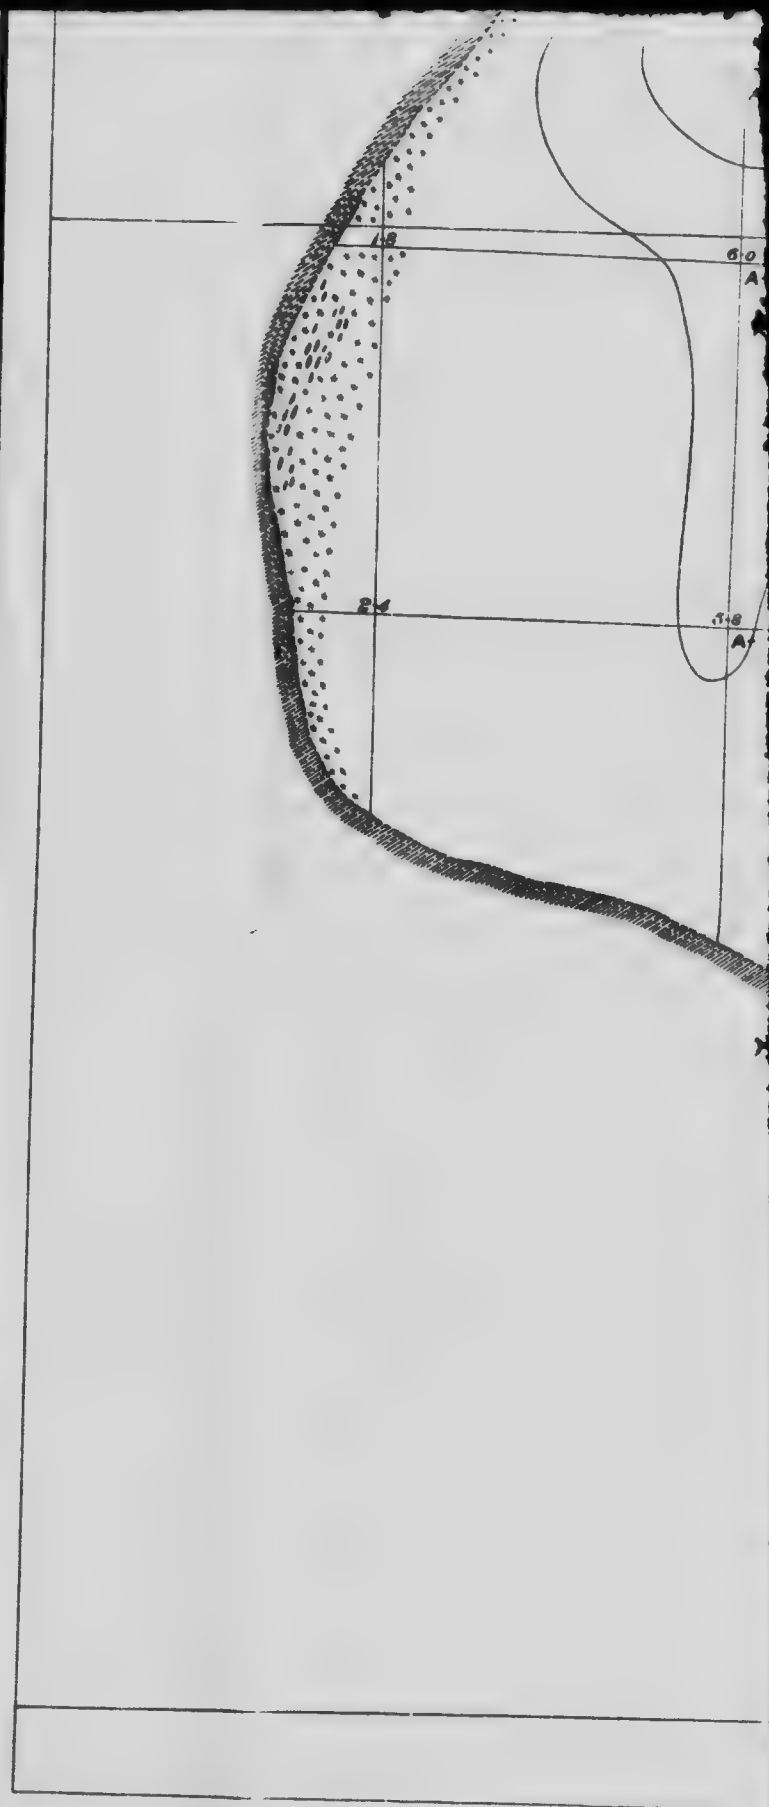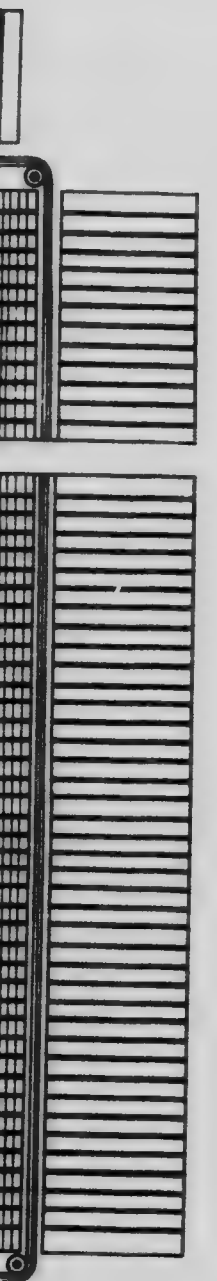


 *Margin of bog.*
 *Wooded areas.*

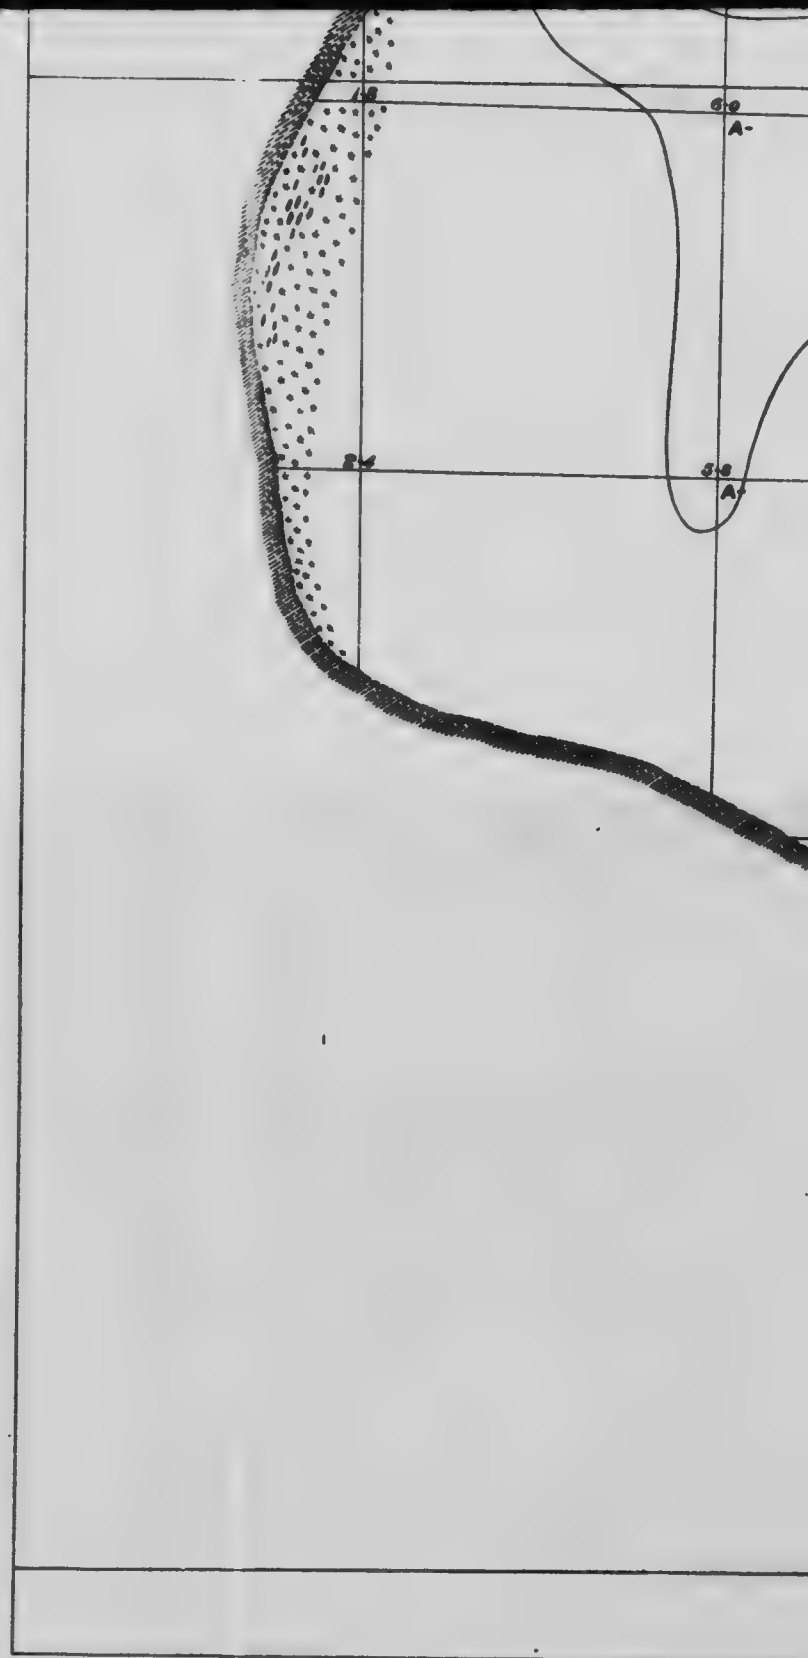

 *Margin of bog.*
 *Wooded areas.*

Sc

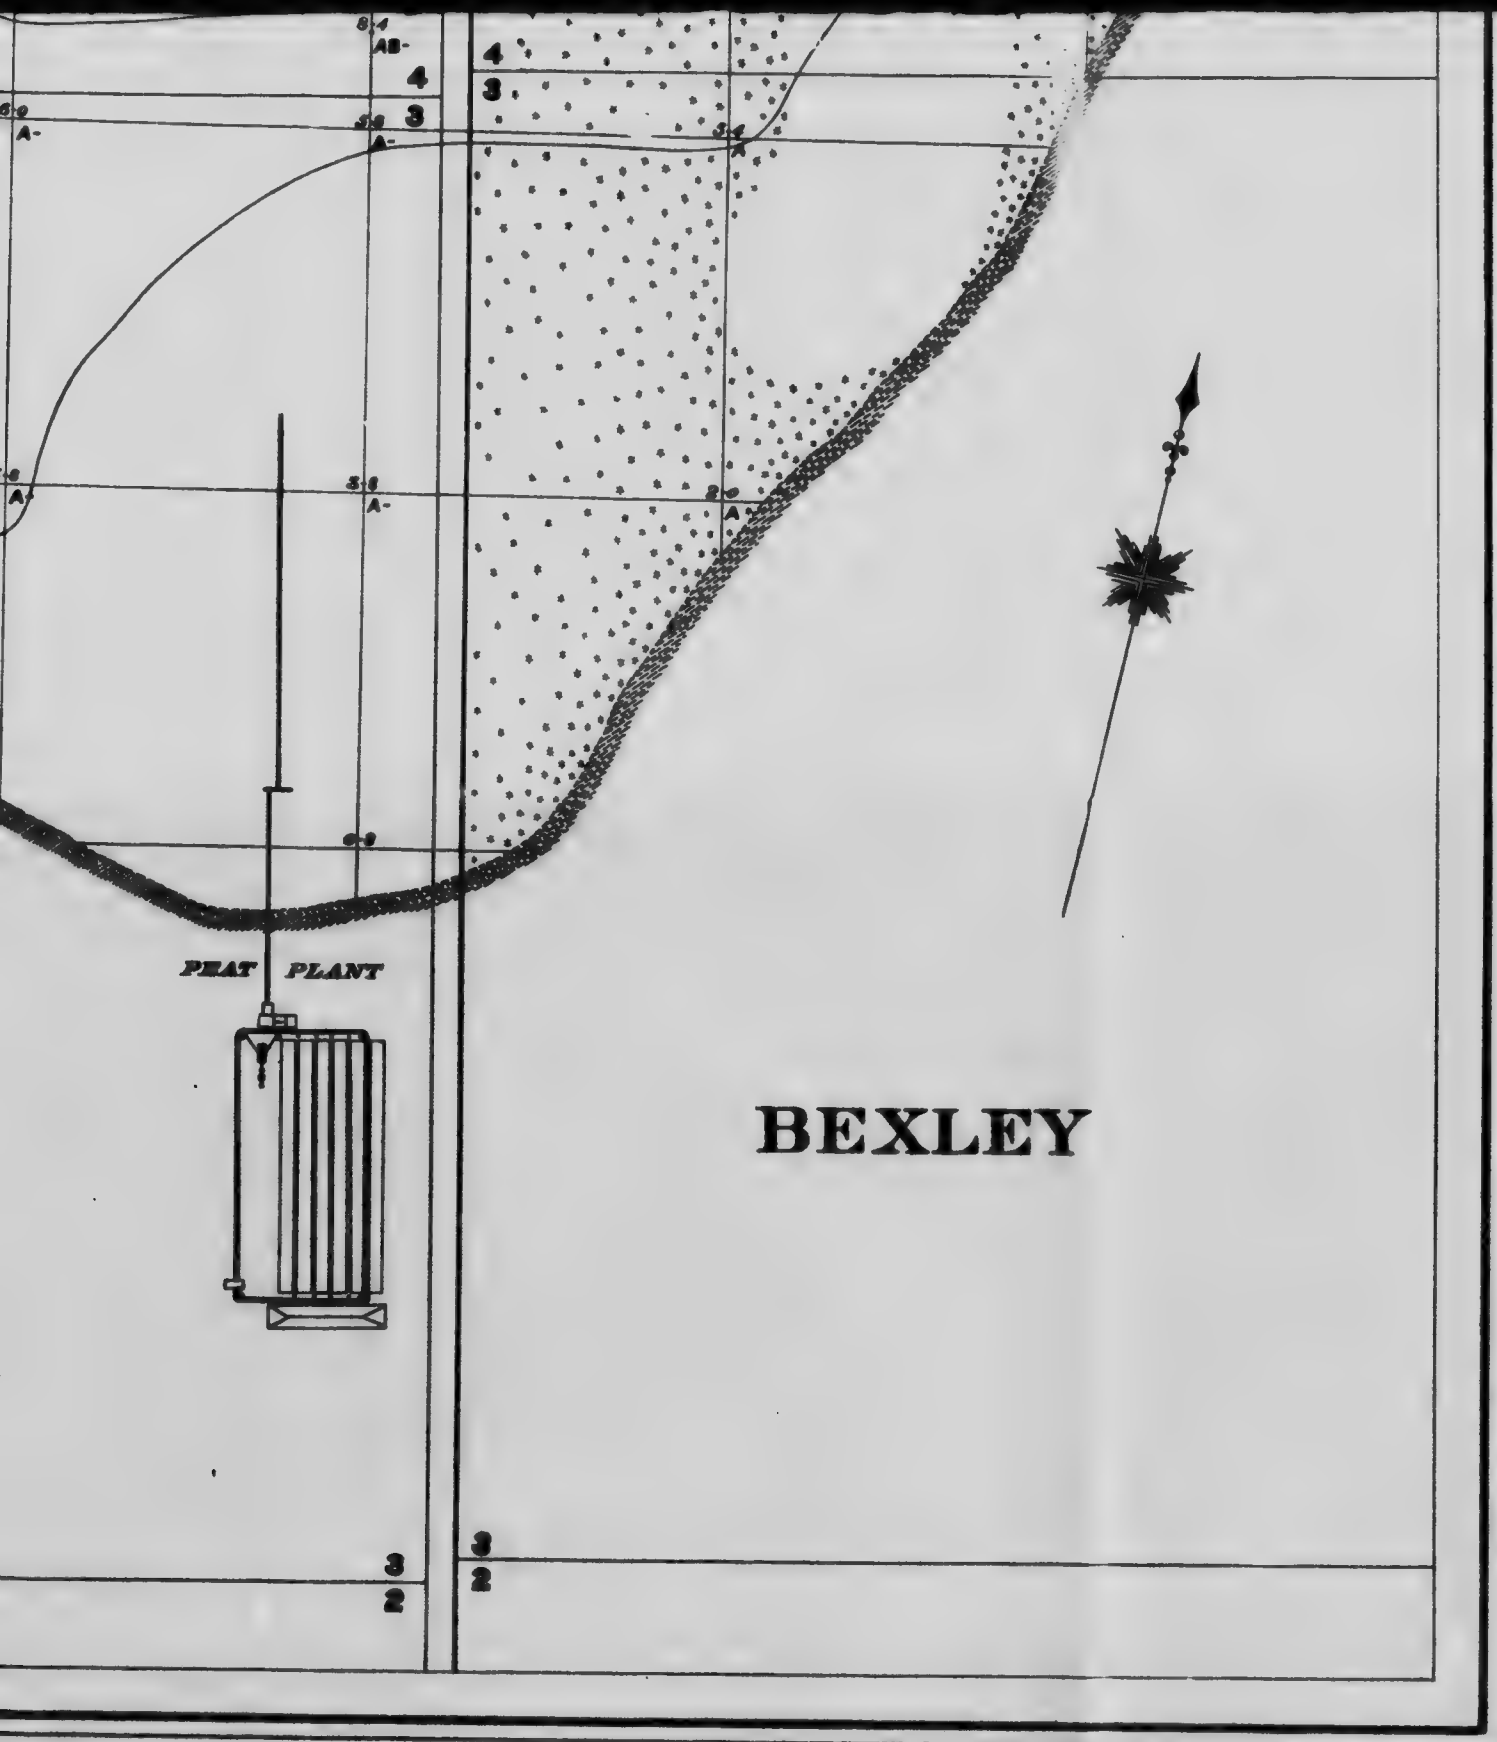

BEXLEY

No. 41

Scale, 25 inches = 1 mile.

tow
by t
into
are
on t
and

moti
and

its le
retu
the t
next
durin
whic
trip t
end
towa
as th
each
lower

quant
requi
as the
locate

power
lane

and
conve
throu
made
to the

to har
peat i
part c
motion
knobs
engagi
put de

of the drying area, and cross tracks at the top or farther end, and at the bottom or nearer end, are provided, and there is also a means of connecting any up and down track with the end tracks, using specially designed portable corners in such a way as to form with the return track a rectangular course with sharply rounded corners, the length of which is the length of the drying area, and the width the distance from the return track to that particular up and down track in use.

This plant being the only one where power and drying arrangements could be obtained for the manufacture of air-dried peat, it was decided to install the Anrep peat machine imported by the Department, as the plant was represented to be in good condition, and with a slight expenditure could be put in running order.

It was very soon found, however, that the condition of the plant was anything but good, the tracks, drying racks, and most of the other apparatus were very poorly built, and in order to make a fair trial of the plant more time and money than was available would have been required, the object being to manufacture sufficient peat fuel for the gas producer plant under erection and to test the Anrep peat machine. Work was, however, started in the early part of August. The peat machine fulfilled every expectation, and with proper arrangements could easily treat an amount of wet peat equivalent to 25 to 35 tons air-dried peat per day.

The principal objection to the plant as constructed by Mr. Moore is its complicated design. Even if the plant had been properly built, its practicability for the purpose is questionable. With sufficient area for drying purposes, the conveyer used is bound to cause trouble, and the unloading of the pallets from the cars on to the drying racks, as well as the subsequent transportation of the dried peat to the storehouse, is neither practical nor labour-saving. The excavator formerly used at this plant was dismantled and its operation and practical use could not be ascertained, but even assuming that mechanically it worked satisfactorily, it is questionable if the air-drying down to some 50 or 60% moisture before the peat is put through the pulping machine is advantageous. Such drying is liable to decrease the cohesive properties of the peat and cause it to crack and crumble to pieces more than would otherwise be the case.

GUELPH PEAT PLANT.

This plant is owned by the Imperial Peat Company, Ltd., and operations have recently been started. The object is to manufacture peat briquettes. No data as to the success of this Company are as yet to be had.

FARNHAM PEAT PLANT.

The plant near Farnham, Que., was erected by the United States Peat Fuel Company, with head office in Chicago. At my visit to this plant, during the summer, I was refused admittance, but it is evident that this Company, up to the present time at least, has no definite plan for the carrying out of the work.

LAC DU BONNET PEAT PLANT.

A peat plant, owned by the Inter-west Peat Fuel Co., of Winnipeg, Man., was erected at this place, but so far no practical results have been obtained. The plant is located at the Julius muskeg, east of Winnipeg, which covers an enormous area, but from information received it is probable that large areas of this bog are shallow and that the peat is more or less poorly humified.

DRYING, CARBONIZING, ETC.

The idea of the possibility of drying the wet peat as dug out of the bog, by means of artificial heat alone, seems still to prevail amongst a number of people interested in the peat industry. A very simple calculation shows, however, the impracticability of such an undertaking. Assuming that a drained bog contains 12½% dry peat substance, which is a good average, 100 lbs. of wet peat contains 87½ lbs. of water. Assuming further that 80% of the fuel value of the fuel used could be utilized, that 1,100 B.T.U. are required to evaporate 1 lb. water, and that the dry peat has a calorific value of 9,000 B.T.U. per lb.; in order to evaporate the water, we consequently require:—

$$\frac{87.5 \times 1,100}{0.80 \times 9,000} = 13.3 \text{ lbs. of dry peat substance, or}$$

more than is contained in the peat.

The only possibility along this line is the employment of vacuum apparatus, but no such apparatus suitable for peat has yet been produced.

To eliminate the water content by mechanical pressure down to less than about 70%, has, with this apparatus, so far as tried, also been found practically impossible. The explanation is, according to Dr. M. Ekenberg, who has thoroughly studied this subject, the presence of a slimy hydrocellulose, which substance is produced from the cell residues of decaying plants by prolonged contact with water.

The principle of the Ekenberg wet carbonizing process is based on this point; the process aims at the destruction of this slimy substance and is obtained through the heating of the wet peat at a temperature of 155° to 180° Cent., with a corresponding pressure, in order to prevent the formation of steam and the loss of heat which such formation would involve. The process is further described in my report on Peat and Lignite in Europe, pages 160–170.

In cases where the peat contains a considerable amount of nitrogen, 1.5–3% (in dried sample), Dr. Ekenberg proposes to employ Mond gas-producers to furnish the gas required for the gas engines, as well as for the heating of the carbonizing ovens. In that case the nitrogen will be recovered as ammonium sulphate, the value of which will considerably decrease the cost of manufacture.

A plant with a capacity of 50 tons of briquettes per day of 24 hours will probably be in operation in Sweden during 1909.

The peat coking plant at Beuerberg, Germany, has, during the last year, been further improved by Mr. M. Ziegler. In order to produce a good coke,

it is essential that the peat used should not contain more than 25% moisture. The air-dried peat is, however, very seldom uniform in moisture content, and the peat manufactured during the latter part of the summer very often contains more than 25% moisture. Mr. Ziegler overcomes this difficulty by employing the waste gases from the retorts for preliminary drying of the peat. The gases are mixed with air, so that a suitable temperature is obtained, and then passed through the peat in special drying chambers.

A new peat machine, with a large capacity, invented by Mr. A. Anrep, is at present being introduced in Europe, and the same inventor is also occupied with the construction of a mechanical excavator in combination with a peat plant of somewhat new design. The details of this plant are not as yet available. A new stump pulling apparatus has also been invented by Mr. Anrep.

For the manufacture of peat powder, in accordance with the process invented by Mr. H. Ekelund, of Sweden, an extensive plant was started last year and will probably be in full operation during the coming season.